

Information Series 138

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2014



This document is disseminated under the sponsorship of the U.S. Department of Transportation, Federal Highway Administration in the interest of information exchange. The United States Government assumes no liability for its contents or use of the information contained in this document.

The contents of this report reflect the views of the contractor, who is responsible for the accuracy of the data presented herein. The contents do not necessarily reflect the official policy of the Department of Transportation.

This report does not constitute a standard, specification, or regulation.

The United States Government does not endorse products or manufacturers. Trade or manufacturer's names may appear only because they are considered essential to the object of this document.



NAPA Building • 5100 Forbes Blvd. • Lanham, MD 20706-4407

Tel: 301-731-4748 • Fax: 301-731-4621

Toll free: 1-888-468-6499 • www.AsphaltPavement.org

Publication Sales: store.AsphaltPavement.org • napa-orders@abdintl.com

Toll free: 888-600-4474 • Tel: 412-741-6314 • Fax: 412-741-0609

5th Annual Asphalt Pavement Industry Survey

IS-138

Produced November 2015

Technical Report Documentation Page

1. Report No. Information Series 138 (5th edition)	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2014		5. Report Date November 2015	
		6. Performing Organization Code	
7. Author(s) Kent R. Hansen, P.E., and Audrey Copeland, Ph.D., P.E.		8. Performing Organization Report No. IS 138(5e)	
9. Performing Organization Name and Address National Asphalt Pavement Association 5100 Forbes Blvd. Lanham, MD 20706		10. Work Unit No. (TRAIS)	
		11. Contract or Grant No. DTFH61-13-H-00027	
12. Sponsoring Organization Name and Address Federal Highway Administration Office of Asset Management, Pavement and Construction 1200 New Jersey Ave. SE Washington, DC 20590		13. Type of Report and Period Covered Final Report 2014	
		14. Sponsoring Agency Code FHWA-HIAP-20	
15. Supplementary Notes FHWA Agreement Officer's Representative: Jeff Withee			
16. Abstract <p>A shared goal of the Federal Highway Administration (FHWA) and the National Asphalt Pavement Association (NAPA) is to support and promote sustainable practices, such as pavement recycling and warm-mix asphalt (WMA). The use of recycled materials, primarily reclaimed asphalt pavement (RAP) and reclaimed asphalt shingles (RAS), in asphalt pavements reduces the amount of new materials required to produce asphalt mixes, as well as the stream of material going to landfills. This is vital to the mission of environmental stewardship and extending the service life of the nation's infrastructure while lowering overall costs.</p> <p>WMA technologies have been introduced to reduce the production and compaction temperatures for asphalt mixtures as a means of reducing the energy needed and emissions associated with mix production. Additional benefits include improved compaction of asphalt mixtures leading to improved pavement performance, as well as a longer paving season. As part of FHWA's Every Day Counts initiative, WMA was chosen for accelerated deployment in federal-aid highway, state department of transportation (DOT), and local road projects.</p> <p>It is important for the industry to document the deployment of these technologies to understand where they are being used and where they may be underutilized. FHWA has established a mechanism for tracking the use of recycled materials and WMA in asphalt pavements. This mechanism has established a baseline for RAP, RAS, and WMA usage and has tracked the growth of the use of these sustainable practices in the highway industry since 2009.</p> <p>The objective of this tracking is to quantify the use of recycled materials and WMA produced annually by the asphalt pavement industry. Results show significant growth in the use of RAP, RAS, and WMA technologies from 2009 through 2014. The asphalt industry remains the country's most diligent recycler by recycling asphalt pavements at a rate of over 99 percent. The average percentage of RAP used in asphalt mixtures has increased from 15.6 percent in 2009 to 20.4 percent in 2014. In 2014, the estimated RAP tonnage used in asphalt mixes was 71.9 million tons. Assuming 5 percent liquid asphalt in RAP, this represents over 3.6 million tons (20 million barrels) of asphalt binder conserved along with replacing some 68 million tons of virgin aggregate.</p> <p>The combined saving of asphalt binder (\$550/ton) and aggregate (\$9.50/ton) by using RAP and RAS in asphalt mixes is more than \$2.8 billion. This keeps asphalt pavement mixture costs competitive and allows owners to achieve more roadway maintenance and construction activities within limited budgets.</p> <p>In 2014, WMA was about one-third of the total asphalt mixture market. WMA use increased by nearly 7 percent from 2013 to 2014, and about 577 percent since 2009. Plant foaming is used most often in producing WMA, with over 84 percent of the market. WMA additives accounted for about 16 percent of the market.</p>			
17. Key Words Reclaimed asphalt pavement, reclaimed asphalt shingles, warm-mix asphalt, RAP, RAS, WMA, recycled materials		18. Distribution Statement No restrictions.	
19. Security Classification (of this report) Unclassified.	20. Security Classification (of this page) Unclassified.	21. No. of Pages 28	22. Price NA

Table of Contents

List of Abbreviations	4
Executive Summary.....	5
Background	6
Objective and Scope	6
Survey Methodology.....	7
Survey Results	8
Sidebar: 2014 RAP Study Tour of Japan	11
Reclaimed Asphalt Pavement	13
Reclaimed Asphalt Shingles	16
Warm-Mix Asphalt	19
Other Recycled Materials.....	21
Ground Tire Rubber	21
Steel & Blast Furnace Slag.....	22
Other Recycled Materials.....	24
Summary and Conclusions.....	24
References	27

List of Abbreviations

AASHTO	American Association of State Highway and Transportation Officials
CCPR	Cold Central Plant Recycling
CIR	Cold In-Place Recycling
CRM	Crumb Rubber Modifier
DOT	Department of Transportation
FDR	Full-Depth Reclamation
FHWA	Federal Highway Administration
GTR	Ground Tire Rubber
HIR	Hot In-Place Recycling
HMA	Hot-Mix Asphalt
MWAS	Manufacturing Waste Asphalt Shingles
NAPA	National Asphalt Pavement Association
NCAT	National Center for Asphalt Technology
NCAUPG	North Central Asphalt User/Producer Group
NEAUPG	North East Asphalt User Producer Group
NSA	National Slag Association
PCAS	Post-Consumer Asphalt Shingles
PCCAS	Pacific Coast Conference on Asphalt Specifications
RAP	Reclaimed Asphalt Pavement
RAS	Recycled Asphalt Shingles
RMA	Rubber Manufacturers Association
RMAUPG	Rocky Mountain Asphalt User/Producer Group
SAPA	State Asphalt Pavement Association
SEAUPG	Southeastern Asphalt User/Producer Group
UPG	User/Producer Group
WMA	Warm-Mix Asphalt

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2014

Executive Summary

The 2014 survey results demonstrate that the asphalt pavement industry continues to improve its outstanding record of sustainable practices by further increasing the use of recycled materials and warm-mix asphalt (WMA). The use of recycled materials, particularly reclaimed asphalt pavement (RAP) and reclaimed asphalt shingles (RAS), conserve raw materials and reduce overall asphalt mixture costs while WMA technologies improve conditions for ensuring pavement performance and long life, conserve energy, reduce emissions from production and paving operations, and improve conditions for workers.

The objective of this survey was to quantify the use of recycled materials, primarily RAP and RAS, and WMA produced by the asphalt pavement industry. The National Asphalt Pavement Association (NAPA) conducted a voluntary survey of asphalt mixture producers in the United States and of state asphalt pavement associations (SAPAs). The survey was broken into five sections: general information, RAP, RAS, WMA, and other recycled materials. Asphalt mix producers from all 50 states completed the 2014 survey. A total of 228 companies/branches with 1,185 plants were represented in the 2014 construction season survey.

The following are highlights of the 2014 survey:

- The asphalt industry remains the country's most diligent recycler, recycling asphalt pavements at a rate of greater than 99 percent. All contractors/branches responding to the survey reported using RAP in 2013 and 2014. The average percent of asphalt used for all mixes has seen a steady increase of about 1 percent per year since 2009. The total estimated amount of RAP used in asphalt mixtures was 71.9 million tons in 2014, a 28 percent increase over the tons used in 2009 (56 million tons). This is a 6 percent increase over the tons used in 2013 (67.8 million tons). Assuming 5 percent liquid asphalt in RAP, this represents over 3.6 million tons (20 million barrels) of asphalt binder conserved. Use of RAP also reduced the need for some 68 million tons of virgin aggregate. The amount of RAP landfilled was only 0.17 percent, which is in line with previous years.
- Use of both manufacturing waste and post-consumer shingles in asphalt mixtures increased to an all-time high of nearly 2 million tons in 2014, nearly a 20 percent increase from 2013 (1.6 million tons). Assuming a conservative asphalt content of 20 percent for the RAS that may be used to replace virgin binder, this represents 400,000 tons (2.2 million barrels) of asphalt binder conserved, along with 982,000 tons of aggregate. Since the 2012 survey, the amount of scrap shingles collected has been less than the amount used. Contractors contacted on this issue have reported that they either have shingles stockpiled or are buying RAS from shingle processors.
- The combined saving of asphalt binder (\$550/ton) and aggregate (\$9.50/ton) by using RAP and RAS in asphalt mixes is more than \$2.8 billion. This keeps asphalt pavement mixture costs competitive and allows owners to achieve more roadway maintenance and construction activities within limited budgets.
- Information on other recycled materials was obtained for the third time in this year's survey. The most commonly used other recycled materials in asphalt mixtures were blast furnace slag, steel slag, ground tire rubber, and cellulose fibers. Less commonly used recycled materials included fly ash and foundry sand.
- Total tonnage of WMA was estimated at 113.8 million tons during 2014. This is nearly a 7 percent increase over 2013 WMA tonnage (106.4 million tons). As of 2014, WMA is now about one-third of the total asphalt mixture market. Plant foaming is used most often in producing WMA, with more than 84 percent of the market; additives accounted for about 16 percent of the market.

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2014

Background

A shared goal of the Federal Highway Administration (FHWA) and the National Asphalt Pavement Association (NAPA) is to support and promote sustainable practices, such as incorporating recycled materials in pavement mixtures and the use of warm-mix asphalt (WMA). Reclaimed asphalt pavement (RAP) is recycled at a higher rate than any other material in the United States and is vital to the mission of extending the performance and service life of the nation's infrastructure while lowering overall costs. Another recycled material used in asphalt mixtures is reclaimed asphalt shingles (RAS) from both manufacturing waste (MWAS) and post-consumer asphalt shingles (PCAS). The use of RAP and RAS in asphalt pavements can reduce the amount of new asphalt binder and aggregates required in mixes, which can help stabilize the price of asphalt mixtures and save natural resources. Other recycled materials being incorporated into asphalt pavements include ground tire rubber (GTR), steel slag, blast furnace slag, and cellulose fibers, among others. By putting waste materials to a practical use, the asphalt pavement industry helps reduce the amount of material going to landfills while improving the sustainability of asphalt mixtures.

WMA technologies reduce the mixing and compacting temperatures for asphalt mixtures. Environmental benefits include reductions in both fuel consumption and air emissions. Construction benefits include the ability to extend the paving season into the cooler months, haul material longer distances, improve compaction, and use higher percentages of RAP (Prowell et al., 2012). As part of FHWA's original group of Every Day Counts initiatives, WMA was chosen in 2010 for accelerated deployment in federal-aid highway, state department of transportation (DOT), and local road projects (FHWA, 2013). In 2013, WMA was honored with the Construction Innovation Forum's NOVA Award for its engineering, economic, and environmental benefits (CIF, 2013).

FHWA works closely with the pavement industry through associations and other stakeholders to promote pavement recycling technologies and WMA. Since 2007, the American Association of State Highway and Transportation Officials (AASHTO) has conducted a biennial survey of state DOTs' use of recycled materials (Copeland, 2011; Copeland et al., 2010; Pappas, 2011). The results of the AASHTO survey are typically presented at FHWA Expert Task Group meetings. FHWA partners with NAPA to document industry use of RAP, RAS, other recycled materials, as well as WMA technologies used by asphalt mix producers. These efforts have established a baseline for RAP, RAS, and WMA usage, and have tracked the growth of the use of these sustainable practices in the highway industry since 2009.

The industry survey first collected data for the 2009 and 2010 construction seasons and with follow up surveys for the 2011, 2012 and 2013 construction season. These surveys have shown significant growth in the use of RAP, RAS, and WMA technologies from 2009 to 2013 (Hansen & Newcomb, 2011; Hansen & Copeland, 2013a; 2013b; 2014). To continue tracking the use of these technologies, FHWA again partnered with NAPA to capture RAP, RAS, and WMA use for the 2014 construction season. This report documents the results of the 2014 industry survey, including the survey methodology, results, trends, and changes from 2009 through 2014. Since 2012, the survey has also asked about the use of other recycled materials used in asphalt mixtures. The survey questions and data by state are included in the appendices.

Objective and Scope

The objective of this effort is to quantify the use of recycled materials and WMA technologies by the asphalt pavement industry. NAPA conducted a voluntary survey of asphalt mixture producers in the United States, along with a survey of state asphalt pavement associations (SAPAs). While keeping specific producer data confidential, NAPA staff compiled the amount of asphalt mixtures being produced; the amount of RAP, RAS, and other recycled material used; and the amount

of WMA produced in the United States. The data are broken out on a state-by-state basis in Appendix B. To keep specific producer data confidential, no state specific information is provided in the tables or appendix if fewer than three producers from a state responded to the survey. Information from states with fewer than three responding companies is used to estimate national values, however.

The data are analyzed and summarized in this report. In order to accomplish this work, the following tasks were conducted:

1. Develop an online survey similar to the 2009–2013 surveys that enables an analysis of the quantities of recycled materials being used in asphalt mixtures, as well as the total amount of WMA produced nationally.
2. Conduct a voluntary survey of asphalt mix producers throughout the United States and follow up with verbal requests for information in locations where responses were low.
3. Estimate the total asphalt mixture market in each state or territory by using data provided by SAPAs and the U.S. Department of Transportation federal-aid highway apportionment to determine a weighting factor for each state and reconcile the total U.S. asphalt mix tonnage with national estimates.
4. Analyze and summarize the information nationally and by state and prepare a final report.

Survey Methodology

The survey was conducted using an online survey platform, SurveyMonkey®. Sections 1 through 4 of the survey for 2014 were identical to the surveys used for 2009 through 2012 (Hansen & Newcomb, 2011; Hansen & Copeland, 2013a; 2013b; 2014). Section 5 was first added in 2012 to collect information on the use of other recycled material in asphalt mixtures. A copy of the 2014 survey is included as Appendix A. Table 1 summarizes the questions asked in each section.

Producers were notified of the survey through several forums and electronic media. A notice was posted in NAPA’s e-newsletter, *ActionNews*, informing members of the survey and asking for their participation. SAPAs participated by placing notices on their websites and in their newsletters. Announcements were made at NAPA meetings, as well as at several state asphalt conferences. A press release was sent to construction industry trade media, and republished in print and online. Notices of the survey and links were shared through social media channels, including Twitter, Facebook, and LinkedIn. Asphalt mixture producers then went to the SurveyMonkey website to complete the survey form. Some producers submitted PDF forms and the data were entered into SurveyMonkey by NAPA. One multistate producer submitted data using a spreadsheet developed by NAPA. After the initial data was gathered and analyzed, anomalies in individual producer records were identified and reconciled.

Table 1: Survey Questions Summary

Section 1: General Information	Sections 2 and 3: RAP & RAS	Section 4: WMA	Section 5: Other Recycled Materials
Number of Plants	Tons Accepted	Average % Produced for DOT Tons	Other Recycled Materials Used
DOT Tons	Tons Used in HMA/WMA	Average % Produced for Other Agency Tons	Tons of HMA/WMA Produced Using Each Recycled Material
Other Agency Tons	Tons Used in Aggregate	Average % Produced for Commercial & Residential Tons	Tons of Other Recycled Product Used
Commercial & Residential Tons	Tons Used in Cold Mix	Chemical Additive %	
	Tons Used in Other	Additive Foaming %	
	Tons Landfilled	Plant Foaming %	
	Average % for DOT Mixes	Organic Additive %	
	Average % for Other Agency Mixes		
	Average % for Commercial & Residential Mixes		

To determine the total amount of RAP and RAS used and WMA produced in each state and in the nation, the total amount of asphalt mix produced in each state needed to be determined. Total tonnage of asphalt mix produced represents commercial (i.e., private sector) and government (i.e., DOT and Other Agency) tonnages. Estimated tonnages were provided by SAPAs in 35 states/territories, which totaled about 291 million tons. This included one SAPA that supplied DOT-estimated tonnages. For this state, the total tonnage was estimated by dividing the DOT tonnage by the percent of DOT tons provided by asphalt mix producers in that state who completed the survey. To estimate the total tons in states where a SAPA estimate of total tonnage was not available, the total asphalt mixture tonnage was estimated through a relationship developed by examining states where SAPA-estimated tons were available compared to their federal-aid highway apportionment. This is the same methodology used to estimate tonnage in the previous versions of this survey; for more details see Hansen & Newcomb (2011). This resulted in the following power curve relationship:

$$\text{Total Estimated Tons} = 0.2359 \times (\text{State Federal Apportionment})^{0.843} \quad [1]$$

Equation 1 is used to estimate the tonnage for states with no SAPA estimate based on the state's federal apportionment.

Survey Results

Asphalt mix producers from all 50 states completed the 2014 survey, which is two fewer jurisdictions than in 2013, but higher than in other survey years. No plants in the District of Columbia or any U.S. insular area contributed data for 2014. A total of 228 companies/branches with 1,185 plants are represented in the 2014 survey. This is down slightly from the 2013 survey responses, but more than in previous survey years. While the number of companies/branches and plants represented by this survey decreased, the total tons reported increased from 147.6 to 151.0 million tons. This may be due to a slight increase in total asphalt mix production and contractors shutting down less efficient plants. Table 2 summarizes the number of companies/branches and the number of plants reporting for each state. Table 3 summarizes the total responses from previous years.

Table 2: No. of Companies/Branches Completing 2014 Survey by State

State	Cos.	Plants	State	Cos.	Plants	State	Cos.	Plants
Alabama	5	37	Kentucky	7	47	Ohio	7	102
Alaska	*	*	Louisiana	*	*	Oklahoma	6	16
American Samoa	NCR	NCR	Maine	3	17	Oregon	5	14
Arizona	3	6	Maryland	5	13	Pennsylvania	6	27
Arkansas	6	19	Massachusetts	4	16	Puerto Rico	NCR	NCR
California	6	61	Michigan	6	36	Rhode Island	*	*
Colorado	5	21	Minnesota	7	26	South Carolina	6	18
Connecticut	3	16	Mississippi	5	21	South Dakota	*	*
Delaware	*	*	Missouri	4	29	Tennessee	7	53
District of Columbia	NCR	NCR	Montana	*	*	Texas	11	61
Florida	7	38	Nebraska	3	7	U.S. Virgin Islands	NCR	NCR
Georgia	4	22	Nevada	3	4	Utah	8	19
Guam	NCR	NCR	New Hampshire	4	14	Vermont	*	*
Hawaii	*	*	New Jersey	3	16	Virginia	7	33
Idaho	4	14	New Mexico	*	*	Washington	4	30
Illinois	9	29	New York	9	59	West Virginia	3	14
Indiana	4	32	North Carolina	7	32	Wisconsin	*	*
Iowa	8	18	North Dakota	*	*	Wyoming	*	*
Kansas	5	24	N. Mariana Islands	NCR	NCR			

NCR = No Contractors Reporting

* = Fewer than 3 contractors reporting

Table 3: Summary of Jurisdictions, Companies/Branches, and Plant Represented in 2009–2014 Surveys

Year	No. Jurisdictions Reporting	No. of Companies/Branches Reporting.	No. of Plants Represented in Survey	Average Tons Produced per Plant
2009	48	196	1,027	121,000
2010	48	196	1,027	117,000
2011	49	203	1,091	121,000
2012	49	213	1,141	122,000
2013	52	249	1,281	115,000
2014	50	228	1,185	127,000

Table 4 includes the estimated tonnage for each state as estimated by the SAPA or estimated from the federal apportionment using Equation 1, as well as the reported tonnage for each state from the survey results and the ratio of the tons reported in each state to the total estimated tons for 2014. The closer a state's ratio is to 100 indicates that the reported tonnage from the survey matches the estimated tonnage provided by the SAPA or the tonnage estimated from the federal apportionment. The data reported in the survey represent about 43 percent of total estimated U.S. tonnage for 2014.

Table 4: Summary of 2014 Estimated and Reported Plant Mix Asphalt Tons by State

State	Tons, Millions	Reported % of Estimated		State	Tons, Millions	Reported % of Estimated	
		Estimated	Reported			Estimated	Reported
Alabama	7.50	4.04	54%	Montana	4.18	*	*
Alaska	4.76	*	*	Nebraska	3.17	0.81	26%
Arizona	6.63	0.84	13%	Nevada	3.65	0.52	14%
Arkansas	5.10	1.67	33%	New Hampshire	1.93	1.57	81%
California	23.09	10.23	44%	New Jersey	5.00	3.31	66%
Colorado	7.00	2.86	41%	New Mexico	3.81	*	*
Connecticut	4.69	2.14	46%	New York	16.30	5.13	31%
Delaware	1.46	*	*	North Carolina	12.00	4.22	35%
District of Columbia	1.88	NCR	NCR	North Dakota	5.00	*	*
Florida	13.30	6.51	49%	Ohio	14.80	13.54	91%
Georgia	4.50	2.32	52%	Oklahoma	4.60	2.20	48%
Hawaii	1.89	*	*	Oregon	4.89	1.45	30%
Idaho	3.06	1.03	34%	Pennsylvania	17.70	3.23	18%
Illinois	13.80	3.49	25%	Puerto Rico	1.60	NCR	NCR
Indiana	9.20	4.76	52%	Rhode Island	2.44	*	*
Iowa	3.60	2.19	61%	South Carolina	4.89	1.96	40%
Kansas	4.00	2.37	59%	South Dakota	2.10	*	*
Kentucky	9.00	4.37	49%	Tennessee	7.36	4.44	60%
Louisiana	6.25	*	*	Texas	18.00	9.74	54%
Maine	2.07	1.36	66%	Utah	3.40	2.94	86%
Maryland	6.80	2.52	37%	Vermont	2.27	*	*
Massachusetts	6.50	2.62	40%	Virginia	9.75	5.24	54%
Michigan	11.30	7.39	65%	Washington	4.90	2.60	53%
Minnesota	13.00	5.55	43%	West Virginia	2.60	1.49	57%
Mississippi	3.50	2.41	69%	Wisconsin	13.00	*	*
Missouri	6.10	1.89	31%	Wyoming	2.75	*	*
				Total	352.04	150.98	43%

NCR No Companies Reporting

* Fewer than 3 companies/branches reporting

SAPA Estimated Tons

Figure 1 shows the number of plants as well as the average tons produced per plant separated by User/Producer Group (UPG) region. While the number of plants represented in each UPG decreased in 2014, the tons per plant for all UPGs increased significantly from 2013 to 2014 with both the North Central Asphalt User/Producer Group (NCAUPG) and Southeastern Asphalt User/Producer Group (SEAUPG) reaching all-time high production levels since the survey began in 2009.

Number of Plants Responding to Survey by User/Producer Group

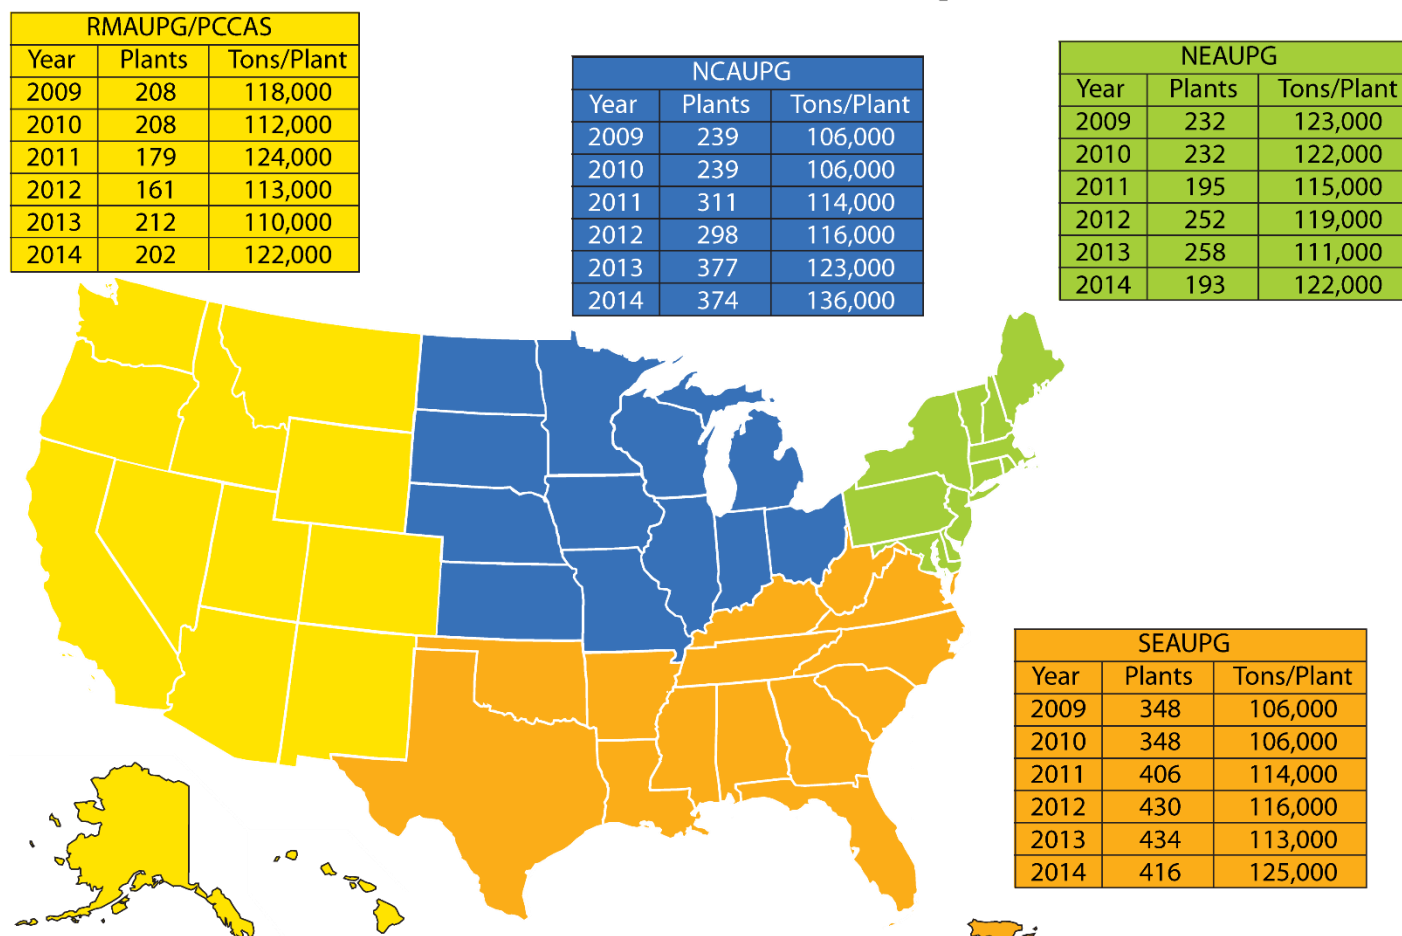


Figure 1: Number of Plants Responding to Survey by User/Producer Group Regions and Estimated Tonnage, 2009–2014

Table 5 summarizes the RAP, RAS, and WMA data from the 2014 survey alongside data from the 2013 survey (Hansen & Copeland, 2014) for comparison. The information requested in the survey is summarized in Table 1 and detailed in Appendix A. Reported Values in Table 5 are national summaries of the values from asphalt mix producers completing the survey. Estimated values for the Tons of HMA/WMA Produced were determined as outlined above in Survey Methodology.

For the amount of RAP accepted contractors were asked “How many tons of removed asphalt pavement and asphalt millings were accepted/delivered to your facilities in the state in 2014?” For the amount of RAS accepted producers were asked “How many tons of unprocessed shingles (manufacturers waste and tear-offs) were accepted/delivered to your facilities in the state in 2014?” Therefore, for RAS, this quantity would not include processed RAS acquired from shingle processors. For each state, the tons of RAS and RAP reported as accepted and used were multiplied by the ratio

of estimated production to total production, and these values were summed to arrive at the national estimated tons for these materials.

To understand the average percentage of recycled material used in mixes, producers were asked to report the average recycled content of mixes produced for each sector (DOT, Other Public Agencies, Commercial & Residential) and to use their best estimate if data was not available. These were averaged to determine the National Average All Mixes Based on % Reported for Different Sectors. In this case, it is evident that many producers provided the average percent when either product was used in a mix, resulting in a likely overestimate of the percentage for each sector as not all mixes would necessarily contain recycled product. To account for this, a National Average All Mixes Based on RAP/RAS Tons Used in HMA/WMA was calculated based on reported tons of material used in HMA/WMA mixes divided by total reported tons produced. Because RAP is more commonly used in mixes than RAS, the differences in the percentages for each sector and the National Average All Mixes Based on RAP/RAS Tons Used in HMA/WMA show less of a disparity in the RAP values. The better estimate of the average percentage for either product is the percentage based on reported tons used. Producers were not asked about allowable RAP or binder replacement requirements, which can have an effect on demand for mixes that incorporate these materials.

Producers were asked to give their best estimate of the percent of WMA produced for each sector when the technology resulted in temperature reduction of 10°F to 100°F. These percentages were multiplied by the total mix production for each sector to determine the total estimated tons of WMA produced for each sector. The survey methodology was designed so that only mixes produced at reduced temperatures are reported. Because some WMA additives are used for construction benefits unrelated to the goal of reducing production temperatures, the use of some WMA additives in HMA production may not be captured in this question.

2014 RAP Study Tour of Japan

In 2014, NAPA led a study tour of Japanese asphalt mix producers and road construction projects to learn about the use of high levels of RAP in that country. The tour included U.S. asphalt mix producers, state department of transportation officials, and representatives from FHWA. On average, Japan uses about 47 percent RAP in its asphalt pavements, and in some prefectures the average is around 51 percent. Through analysis of pavement performance on hundreds of projects and experimentation in the lab and field, Japan has developed standards and practices that have proven to provide equal performance for high RAP content mixes and virgin mixes. Although some of these factors and practices are unique to the Japanese pavement industry, the tour gained many insights that can be applied in the U.S. These are detailed in the NAPA publication *High RAP Asphalt Pavements: Japan Practice — Lessons Learned* (West & Copeland, 2015).

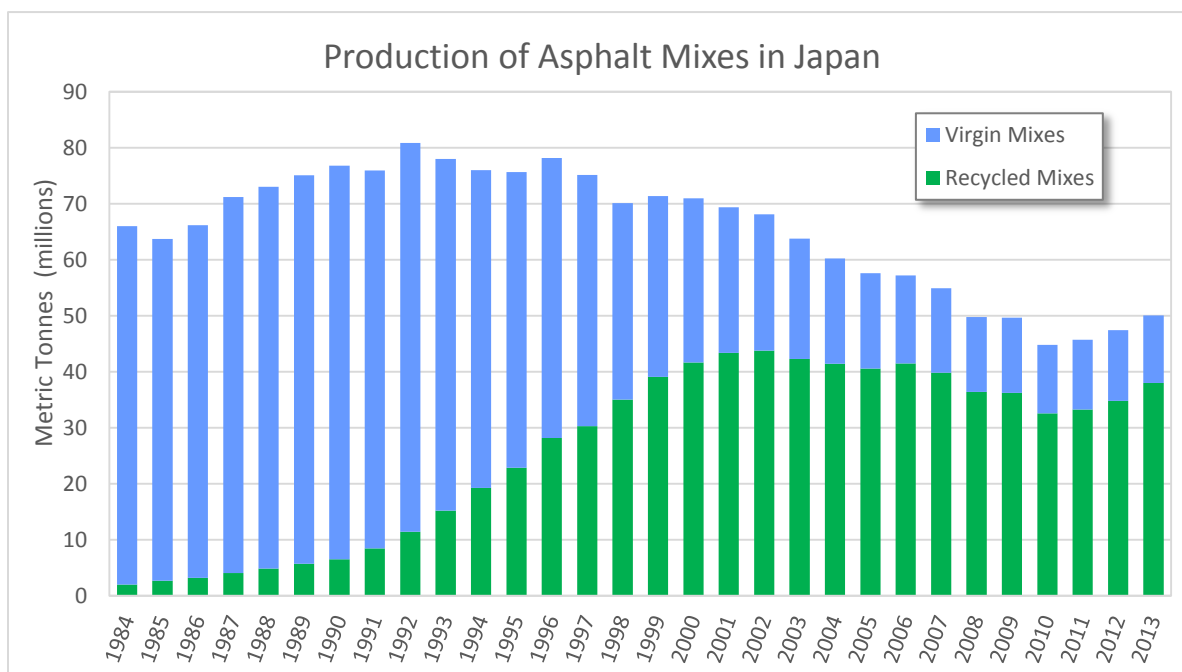


Table 5: Summary of RAP, RAS, WMA Data

		Reported Values		Estimated Values	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons, Millions		Tons, Millions	
	Total	147.6	151.0	350.7	352.0
	DOT	67.4	68.7	160.1	160.2
	Other Agency	40.6	38.9	96.5	90.7
	Commercial and Residential	39.6	43.3	94.1	101.1
	Companies/Branches Reporting	249	228		
RAP		Tons, Millions		Tons, Millions	
	Accepted	34.9	33.8	76.1	75.8
	Used in HMA/WMA	29.5	32.2	67.8	71.9
	Used in Aggregate	1.7	2.9	4.0	8.5
	Used in Cold Mix	0.1	0.1	0.2	0.2
	Used in Other	0.3	0.2	1.5	0.6
	Landfilled	0.1	0.1	0.1	0.2
		Average % Used in Mixes			
	Average % for DOT Mixes ¹	19.5%	19.6%		
	Average % for Other Agency Mixes ¹	19.3%	19.8%		
	Average % for Commercial & Residential ¹	22.7%	22.7%		
	National Average All Mixes Based on % Reported for Different Sectors ¹	19.3%	20.4%		
	National Average All Mixes Based on RAP Tons Used in HMA/WMA ²	20.0%	21.3%		
	Companies/Branches Reporting Using RAP	249	228		
RAS		Tons, Millions		Tons, Millions	
	Accepted	0.685	0.692	1.599	1.664
	Used in HMA/WMA	0.718	0.809	1.647	1.964
	Used in Aggregate	0.028	0.018	0.082	0.043
	Used in Cold Mix	0	0	0	0
	Used in Other	0.002	0.002	0.005	0.006
	Landfilled	0	0	0	0
		Average % Used in Mixes			
	Average % for DOT Mixes ¹	0.85%	0.72%		
	Average % for Other Agency Mixes ¹	1.08%	0.95%		
	Average % for Commercial & Residential ¹	1.24%	1.47%		
	National Average All Mixes Based on RAS Tons Used in HMA/WMA ²	0.49%	0.54%		
	Companies/Branches Reporting Using RAP	97	87		
WMA		% of Total Production		Tons, Millions	
	DOT	37.3%	37.8%	55.7	56.9
	Other Agency	32.4%	34.9%	27.9	28.4
	Commercial and Residential	25.9%	29.4%	22.8	28.5
	Total			106.4	113.8
		% of Market			
	Chemical Additive %	12.1%	15.0%		
	Additive Foaming %	0.3%	0.0%		
	Plant Foaming %	87.0%	84.5%		
	Organic Additive %	0.7%	0.5%		
	Companies/Branches Reporting Using WMA	193	174		

¹ Average percent based on contractor's reported percentage for each sector.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

Reclaimed Asphalt Pavement

Table 5 includes the summary of RAP data from the 2014 survey. The information requested in the survey is detailed in Appendix A and summarized in Table 1. Figure 2 is a visual representation of the estimated total tons of RAP used in asphalt mixes, aggregate, cold mix, other uses, and landfilled compared to the RAP tons accepted from 2009 to 2014. The overwhelming majority of RAP is used in asphalt mixtures, which is the most optimal use of RAP. For 2014, as in 2012, more RAP was used for all purposes than was received. This is primarily due to increased use of RAP in asphalt mixtures. Discarding RAP in construction and demolition landfills is rare. Since the beginning of the survey in 2009, the average amount of RAP landfilled is less than 150,000 tons per year, or 0.20 percent. For 2014 the amount of RAP landfilled was 0.22 percent.

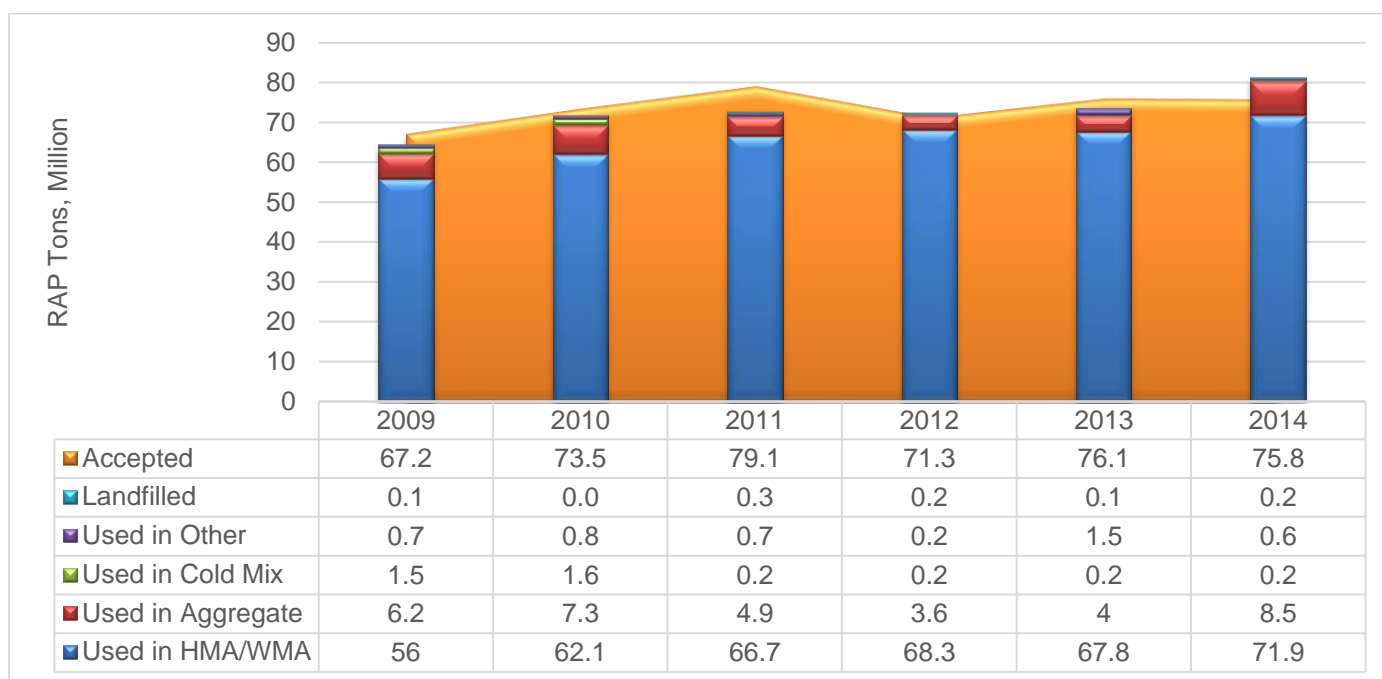


Figure 2: Comparison of Tons of RAP Accepted and Tons of RAP Used (Million Tons)

Figure 3 shows the total estimated amount of RAP used in the different industry sectors. These values were calculated using the average percentages of RAP reported for the different sectors and adjusted to account for differences between reported RAP tonnage and tons calculated from the percentage by sector.

The sectors are divided into Commercial & Residential (private sector) and DOT and Other Agency (public sector). The Other Agency grouping includes mix produced for public works agencies, city and county transportation departments, and the U.S. military, and federal agencies, such as the Federal Aviation Administration.

Figure 4 shows the average percentage of RAP used by each sector and total percentage RAP used. The average percent RAP used by all sectors has seen variable growth from 2009 to 2014. However, the change in the total percentage of RAP use by all sectors has increased steadily since 2009 at a rate of about 1 percent per year. Fluctuations in RAP tonnages used by each sector, as is illustrated in Figure 5, are primarily due to changes in the total tonnage used by each sector. It is interesting that while total tonnage for the DOT sector decreased in 2014, the percentage of RAP used DOT mixes increased, indicating that states and contractors are making greater use of RAP in their mixes.

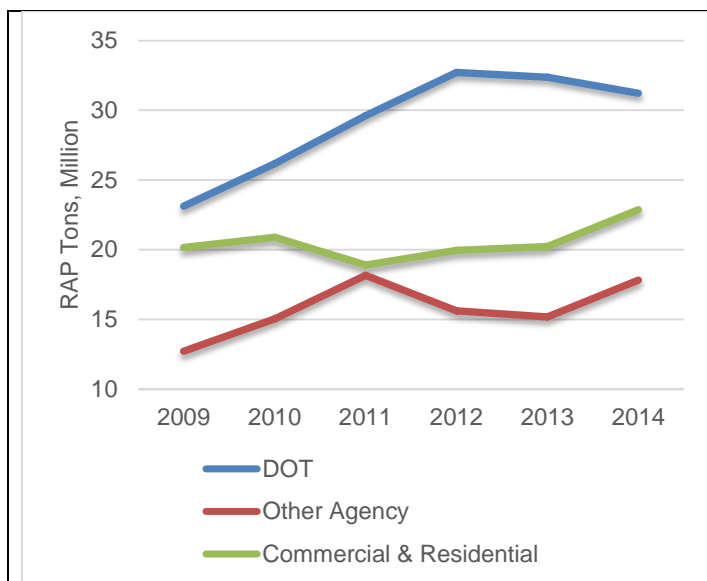


Figure 3: RAP Use by Sector (Million Tons)

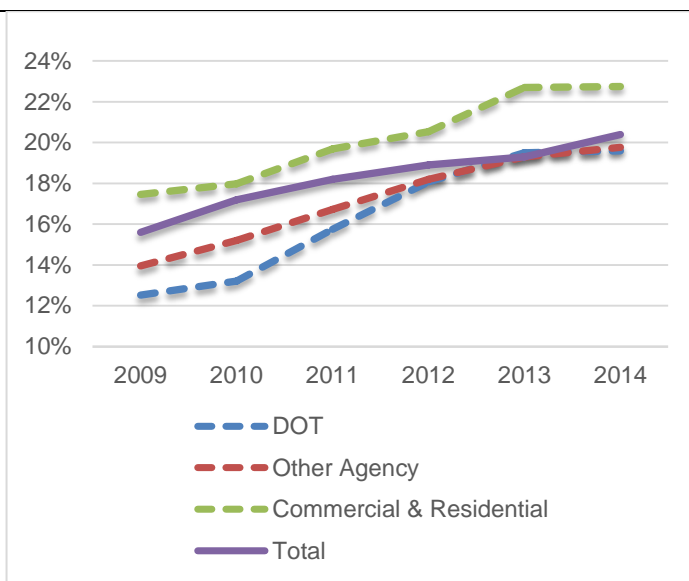


Figure 4: Average Percent RAP Used by Sector

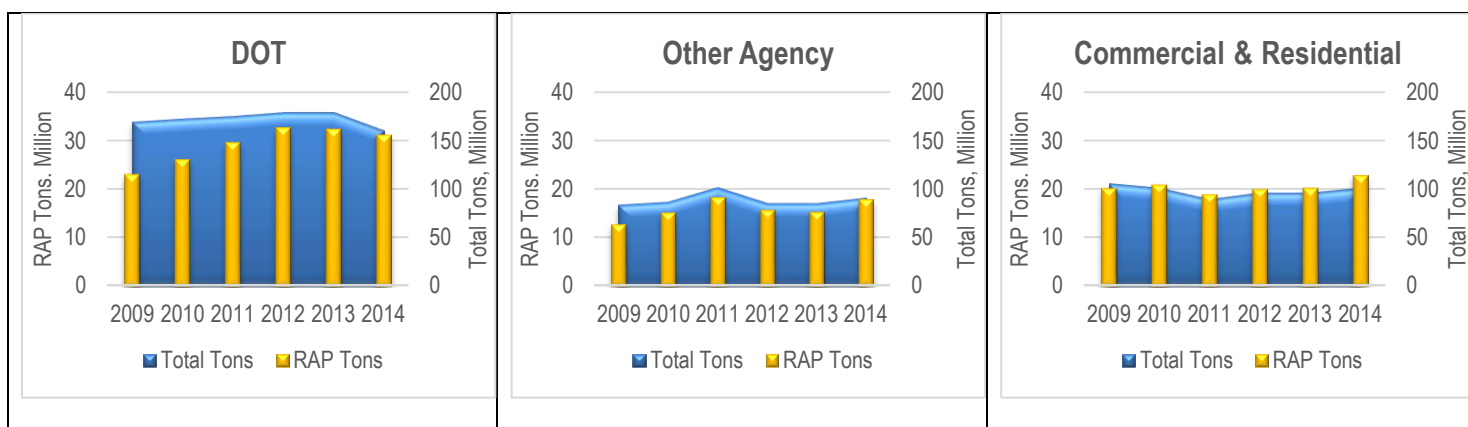


Figure 5: RAP Tons and Total Mix Tons Comparison (Million Tons)

Figure 6 and Table 6 show the average percent of RAP used in each state based on reported RAP and total tonnage. It should be noted that the accuracy of data for individual states will vary depending on the number of responses received from each state and the total number of tons accounted for in the responses. Comparing the maps in Figure 6, the number of states averaging more than 20 percent RAP in HMA/WMA (colored green and dark green) increased steadily from seven states in 2009 to 23 states in 2014. The use of increased amounts of RAP has spread quickly in the Midwest and West. For example, average percent RAP in Idaho increased steadily from 6 percent in 2009 to 25 percent or more since 2012.

For 2013 and 2014, all (100 percent) of the contractors/branches responding to the survey reported using RAP, and more than 91 percent of contractors reported having excess RAP on hand in 2014. In 2011 and 2012, 98 percent of respondents reported using RAP. From 2013 to 2014, the amount of RAP used in HMA/WMA increased from 67.8 million to 71.9 million tons. The average percent RAP used in mixes increased from 19.3 percent in 2013 to 20.4 percent in 2014.

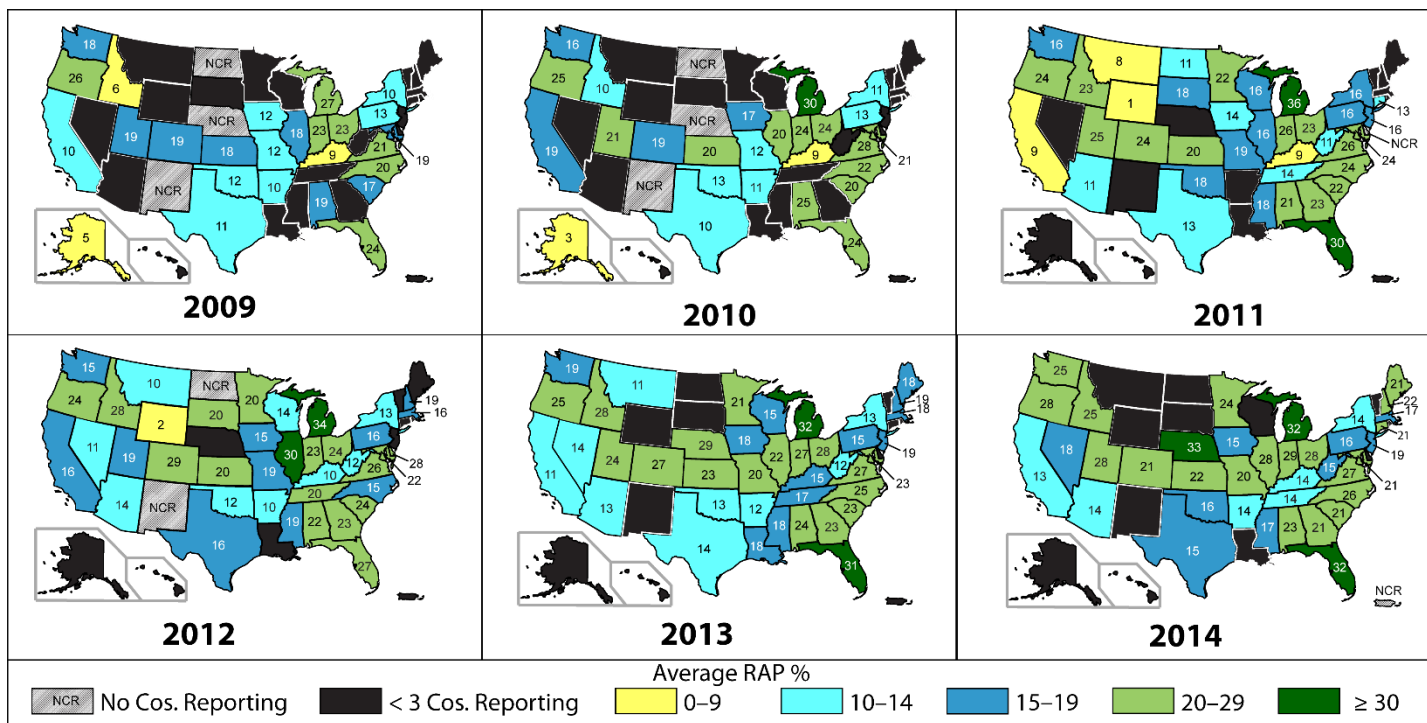


Figure 6: Estimated Average Percent of RAP by State

Table 6: Average Estimated RAP Percent

State	Average RAP Percent						State	Average RAP Percent					
	2009	2010	2011	2012	2013	2014		2009	2010	2011	2012	2013	2014
Alabama	19%	25%	21%	22%	24%	23%	Montana			8%	10%	11%	
Alaska	5%	3%					Nebraska	NCR	NCR			29%	33%
Arizona			11%	14%	13%	14%	Nevada				11%	14%	18%
Arkansas	10%	11%		10%	12%	14%	New Hampshire				19%	19%	22%
California	10%	19%	9%	16%	11%	13%	New Jersey			16%		19%	19%
Colorado	19%	19%	24%	29%	27%	21%	New Mexico	NCR	NCR		NCR		
Connecticut			13%			21%	New York	10%	11%	16%	13%	13%	14%
Delaware			NCR	28%			North Carolina	20%	22%	24%	15%	25%	26%
District of Columbia	NCR	NCR	NCR	NCR		NCR	North Dakota	NCR	NCR	11%	NCR		
Florida	24%	24%	30%	27%	31%	32%	Ohio	23%	24%	23%	24%	28%	28%
Georgia			23%	23%	23%	21%	Oklahoma	12%	13%	18%	12%	13%	16%
Hawaii							Oregon	26%	25%	24%	24%	25%	28%
Idaho	6%	10%	23%	28%	28%	25%	Pennsylvania	13%	13%	16%	16%	15%	16%
Illinois	18%	20%	16%	30%	22%	28%	Puerto Rico						NCR
Indiana	23%	24%	26%	23%	27%	29%	Rhode Island						
Iowa	12%	17%	14%	15%	18%	15%	South Carolina	17%	20%	22%	24%	23%	21%
Kansas	18%	20%	20%	20%	23%	22%	South Dakota			18%	20%		
Kentucky	9%	9%	9%	10%	15%	14%	Tennessee			14%	20%	17%	14%
Louisiana					18%		Texas	11%	10%	13%	16%	14%	15%
Maine					18%	21%	Utah	19%	21%	25%	19%	24%	28%
Maryland	19%	21%	24%	22%	23%	21%	Vermont						
Massachusetts				16%	18%	17%	Virginia	21%	28%	26%	26%	27%	27%
Michigan	27%	30%	36%	34%	32%	32%	Washington	18%	16%	16%	15%	19%	25%
Minnesota			22%	20%	21%	24%	West Virginia			11%	12%	12%	15%
Mississippi			18%	19%	18%	17%	Wisconsin			16%	14%	15%	
Missouri	12%	12%	19%	19%	20%	20%	Wyoming			1%	2%		
No Contractors Reporting	< 3 Contractors Reporting		0–9%		10–14%		15–19%		20–29%		≥ 30%		

Figure 7 show the number of states reporting average RAP percentages for various ranges. The number of states reporting average RAP percentages greater than 20 percent has increased significantly, rising from 14 states in 2009 to 27 states in 2014; the number of states reporting RAP percentages less than 15 percent has decreased from 19 states in 2009 to just nine states in 2014.

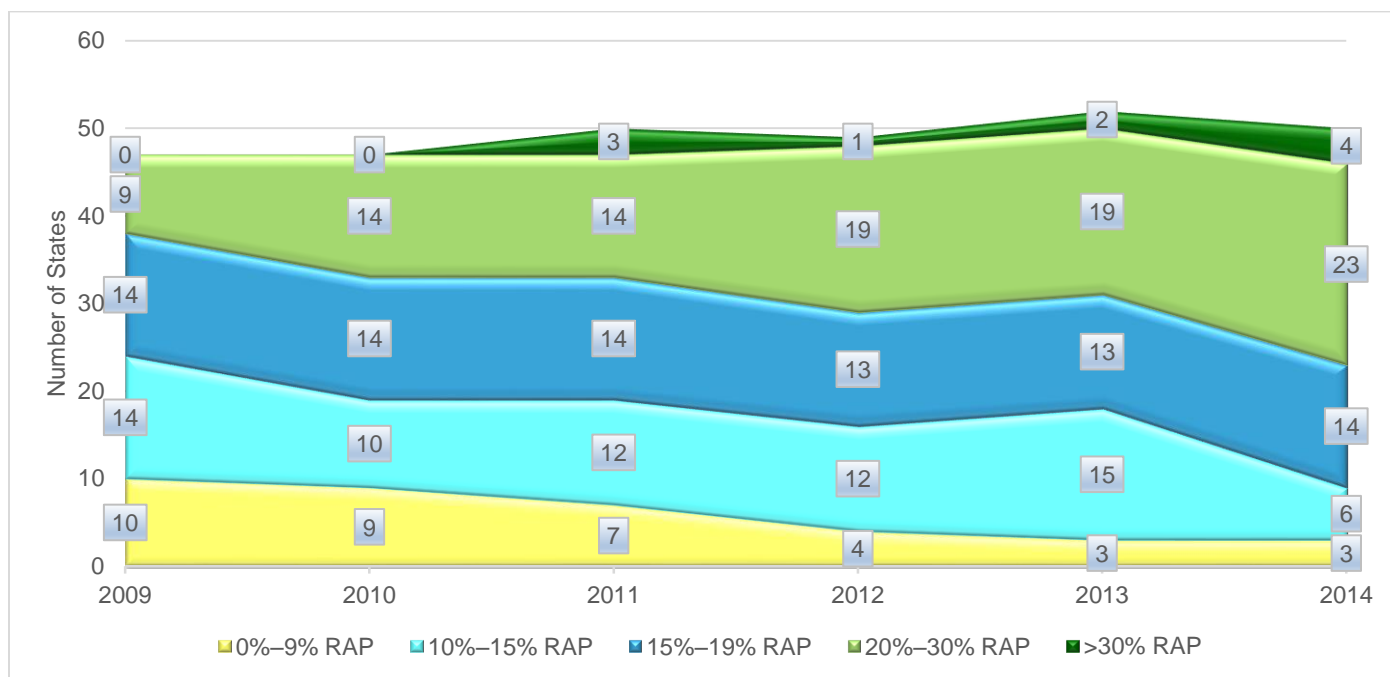


Figure 7: Count of States at Different Average RAP Percentages

Not measured in this survey is the use of in-place asphalt pavement recycling techniques, such as full-depth reclamation (FDR), cold in-place recycling (CIR), and hot in-place recycling (HIR). Some cold central plant recycling (CCPR) may be included in the tons reported as used in other or used in cold mix.

Reclaimed Asphalt Shingles

Table 5 includes the summary of RAS data from the 2014 survey. The information requested in the survey is detailed in Appendix A and summarized in Table 1. Producers were not asked about allowable RAS or binder replacement requirements for their states. For the 2009–2011 surveys, more unprocessed shingles were received than were used for all purposes, including landfilling. Beginning in 2012 this changed with a total of 224,000, 135,000, and 349,000 more tons of RAS being used than was received in 2012, 2013, and 2014 respectively. When it was first noticed that contractors were reporting using RAS in greater quantities than they received, they were contacted to confirm these values. All contractors contacted indicated that they either had RAS stockpiled or were purchasing it from shingle processors. It is assumed that other contractors reporting similar values also had shingles stockpile or were purchasing them from shingle processors. From 2013 to 2014, the amount of RAS accepted by producers increased by 4.1 percent, following declines of 31 and 7 percent from 2011 to 2012 and 2012 to 2013, respectively. Most RAS is used in asphalt pavement mixtures with the second highest use being with aggregate. RAS use in aggregates increased from 6,000 tons in 2009 to 82,000 tons in 2013, but declined to 43,000 tons in 2014. No RAS was reported as being landfilled in 2009 or 2012–2014; in 2010 and 2011, the amount landfilled was about 7,000 and 200 tons, respectively.

Figure 8 shows the total estimated amount of RAS used and for which purpose. Total RAS use increased rapidly from 2009 to 2010 and from 2011 to 2012 at rates of about 48 and 54 percent. From 2012 to 2013 there was a moderate decrease of 11 percent, in total RAS used, but this rebounded by 16 percent from 2013 to 2014. This increase is due to an increase in the average percent of RAS being used in Commercial & Residential sector mixes, as well as an increase in

the total tons of asphalt mix produced for that sector. From the first survey in 2009 to 2014, RAS use in asphalt mixtures has increased nearly 180 percent.

As with RAP, RAS is primarily used in asphalt mixtures. Figure 9 summarizes how RAS was used in the different sectors of the paving market. These values were calculated using the average percentages of RAS reported for the different sectors and were adjusted to account for differences between reported RAS tons and tons calculated from the percentage by sector. There was a moderate decrease in the tons of RAS used by DOTs from 2013 to 2014, due to the decline in total DOT mix tonnage. During this same period, RAS use by Other Agencies increased slightly while the Commercial & Residential sector saw significant increases in RAS use. Figure 10 shows the average RAS percent used in asphalt mixes for the three sectors. These values were calculated using the average percentages of RAS reported for the different sectors and adjusted to account for differences between reported RAS tonnage and tons calculated from the percentage by sector. Overall, RAS use has seen relatively steady growth in all sectors from 2009 to 2014 amid some year-to-year variation. Growth has been greatest in the Commercial and Residential (0.1 percent per year) and Other Agency (0.08 percent per year) sectors with slower growth in the DOT sector (0.05 percent per year). The number of companies/branches using RAS increased steadily from 44 in 2009 to 97 from 2012 to 2013, but decreased to 87 in 2014. Part of this decrease is likely due to the decrease in the number of companies responding to the survey. The percentage of companies reporting using RAS has declined steadily from 41 percent in 2012 to 38 percent in 2014.

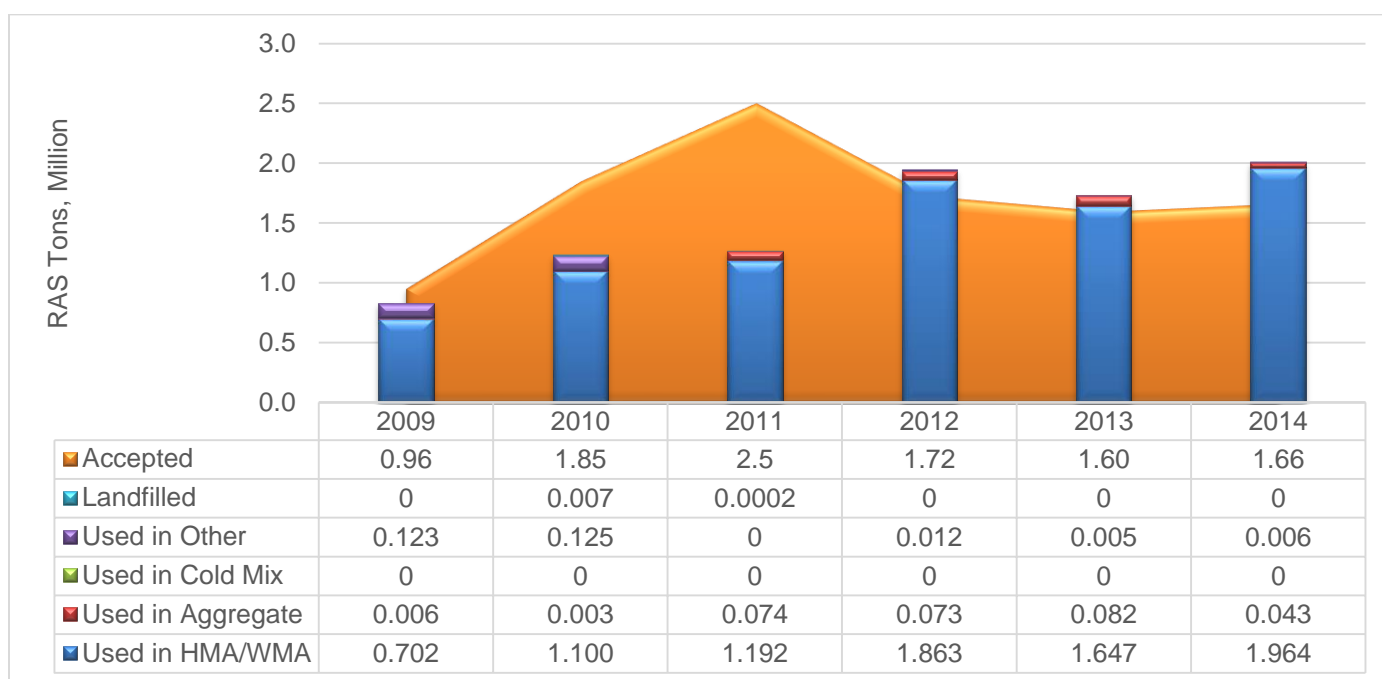


Figure 8: Summary of RAS Use (Million Tons)

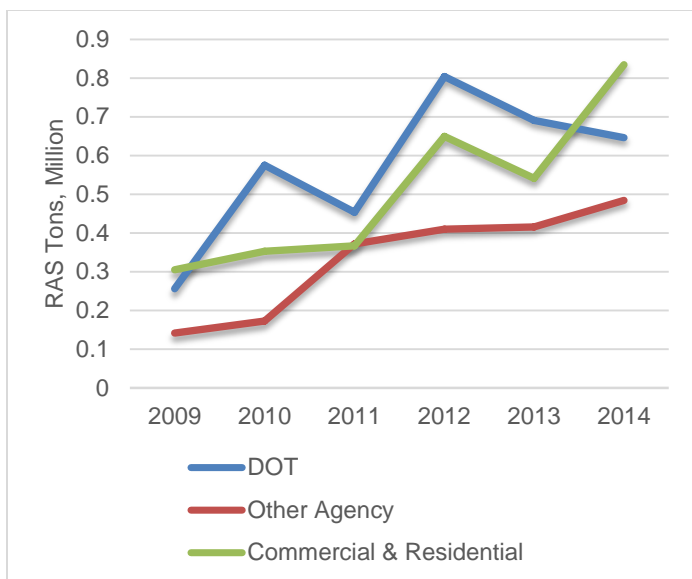


Figure 9: Estimated RAS Use by Sector (Million Tons)

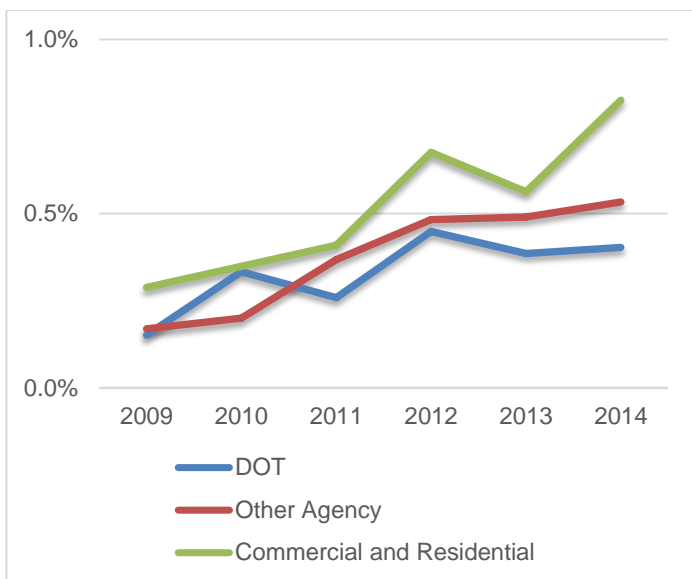


Figure 10: Average Percent RAS Used by Sector

Figure 11 shows states where plant-mix producers reported using RAS in 2009 through 2014. Red indicates states where RAS use was not reported for that year. The number of states where plant-mix producers reported using RAS increased each year from 22 in 2009 to 38 in 2013, but decreased to 36 in 2014. Four states — Georgia, Louisiana, New Jersey and Wyoming — reported RAS use in 2013 but did not report using RAS in 2014. North Dakota reported using RAS in for the first time in 2014. Colorado reported RAS use from 2009 to 2012, but not in 2013; for 2014 the state, again reported using RAS. Table 6 shows the states where producers reported using RAS for 2009–2014.

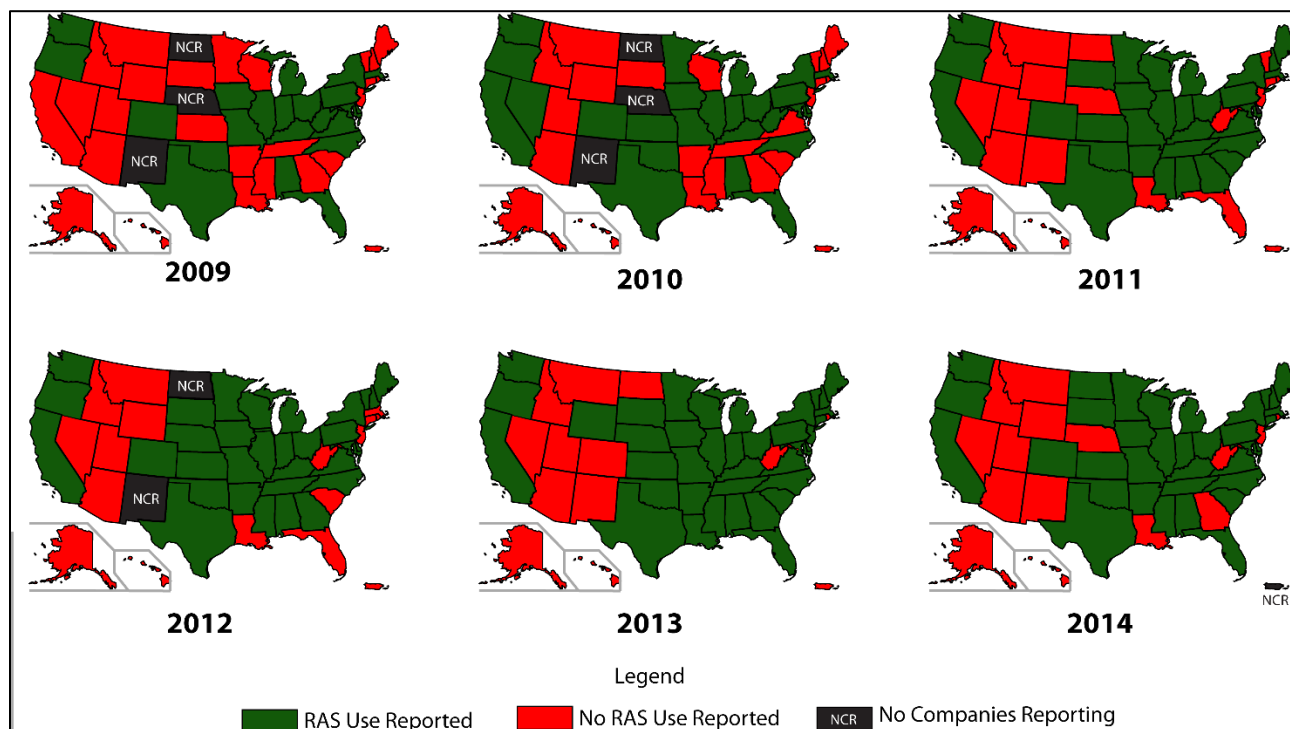


Figure 11: States with Companies/Branches Reporting Using RAS

Table 7: States Reporting RAS Use

State	RAS Used?						State	RAS Used?					
	2009	2010	2011	2012	2013	2014		2009	2010	2011	2012	2013	2014
Alabama	Yes	Yes	Yes	Yes	Yes	Yes	Montana	No	No	No	No	No	No
Alaska	No	No	No	No	No	No	Nebraska	NCR	NCR	No	Yes	Yes	No
Arizona	No	No	No	No	No	No	Nevada	No	Yes	No	No	No	No
Arkansas	No	No	Yes	Yes	Yes	Yes	New Hampshire	No	No	Yes	Yes	Yes	Yes
California	No	Yes	Yes	Yes	Yes	Yes	New Jersey	No	No	No	No	Yes	No
Colorado	Yes	Yes	Yes	Yes	No	Yes	New Mexico	NCR	NCR	No	NCR	No	No
Connecticut	No	No	No	No	Yes	Yes	New York	Yes	Yes	Yes	Yes	Yes	Yes
Delaware	Yes	Yes	NCR	Yes	Yes	Yes	North Carolina	Yes	Yes	Yes	Yes	Yes	Yes
District of Columbia	NCR	NCR	NCR	NCR	No	NCR	North Dakota	NCR	NCR	No	NCR	No	Yes
Florida	Yes	Yes	No	No	Yes	Yes	Ohio	Yes	Yes	Yes	Yes	Yes	Yes
Georgia	No	No	Yes	Yes	Yes	No	Oklahoma	Yes	Yes	Yes	Yes	Yes	Yes
Hawaii	No	No	No	No	No	No	Oregon	Yes	Yes	Yes	Yes	Yes	Yes
Idaho	No	No	No	No	No	No	Pennsylvania	Yes	Yes	Yes	Yes	Yes	Yes
Illinois	Yes	Yes	Yes	Yes	Yes	Yes	Puerto Rico	No	No	No	No	No	NCR
Indiana	Yes	Yes	Yes	Yes	Yes	Yes	Rhode Island	No	No	No	No	No	No
Iowa	Yes	Yes	Yes	Yes	Yes	Yes	South Carolina	No	No	Yes	No	Yes	Yes
Kansas	No	Yes	Yes	Yes	Yes	Yes	South Dakota	No	No	Yes	Yes	Yes	Yes
Kentucky	Yes	Yes	Yes	Yes	Yes	Yes	Tennessee	No	No	Yes	Yes	Yes	Yes
Louisiana	No	No	No	No	Yes	No	Texas	Yes	Yes	Yes	Yes	Yes	Yes
Maine	No	No	Yes	Yes	Yes	Yes	Utah	No	No	No	No	No	No
Maryland	Yes	Yes	Yes	Yes	Yes	Yes	Vermont	No	No	No	Yes	Yes	Yes
Massachusetts	Yes	Yes	Yes	No	Yes	Yes	Virginia	Yes	No	Yes	Yes	Yes	Yes
Michigan	Yes	Yes	Yes	Yes	Yes	Yes	Washington	Yes	Yes	Yes	Yes	Yes	Yes
Minnesota	No	Yes	Yes	Yes	Yes	Yes	West Virginia	Yes	Yes	No	No	No	No
Mississippi	No	No	Yes	Yes	Yes	Yes	Wisconsin	No	No	Yes	Yes	Yes	Yes
Missouri	Yes	Yes	Yes	Yes	Yes	Yes	Wyoming	No	No	No	No	Yes	No
NCR	= No Contractors Reporting												
Yes	= RAS Use Reported												
No	= No RAS Use Reported												

Warm-Mix Asphalt

Table 5 includes the summary WMA data from the survey. The survey asked producers their estimated percentages of tons produced for the different sectors and the percent of which technologies were used.

The percent of companies/branches using WMA saw rapid increases from 2009 to 2011 but only modest increases from 2011 to 2013, with a slight decrease in 2014, as shown in Figure 12. Figure 13 shows a steady increase in the number of tons of WMA produced from 2011 to 2013, with a modest increase in 2014. WMA use reached almost 114 million tons in 2014, which is a little less than one-third of the total asphalt mix production for the year, as is shown in Figure 14. This is probably attributable to increased acceptance of WMA by all industry sectors as illustrated in Figure 13.

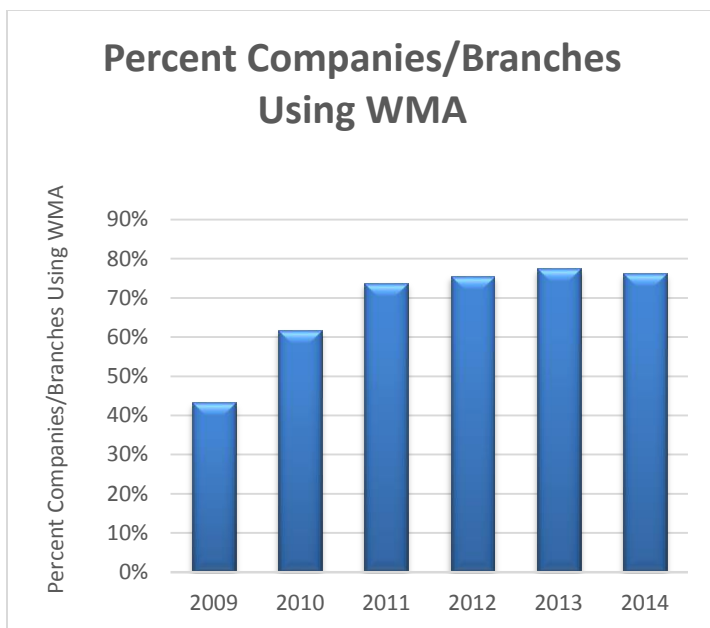


Figure 12: Number of Companies/Branches Using WMA

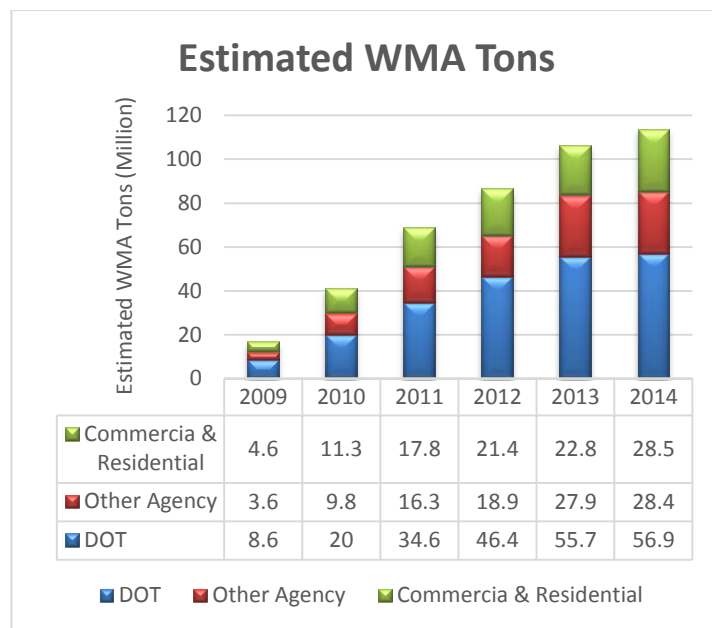


Figure 13: Estimated Tons (in Millions) WMA by Industry Sector

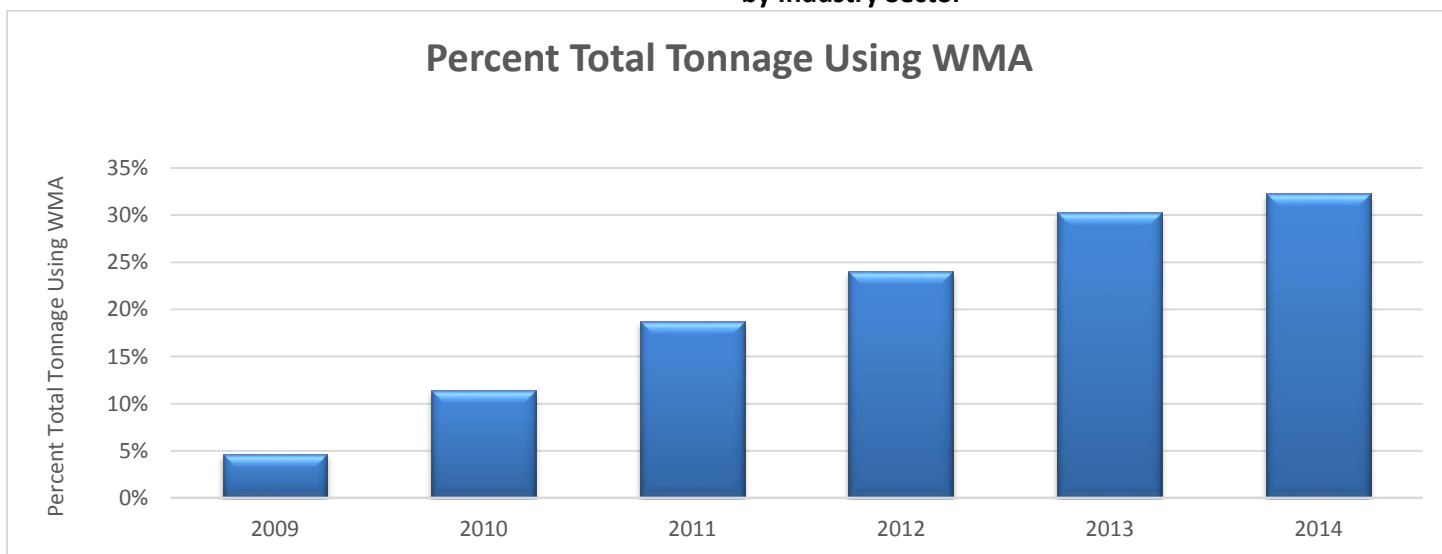


Figure 14: Percent of Total Tonnage Using WMA

Figure 15 shows the estimated total tons of WMA produced in each state. It should be noted that the accuracy of data for individual states will vary depending on the number of responses received from each state and the total number of tons represented by the responses.

From 2013 to 2014, 20 states saw an increase of 5 percent or greater in WMA production, while 13 states had a decrease of 5 percent or greater in WMA production. Three states — Colorado, Minnesota, and South Dakota — had an increase of 25 percent or greater in WMA production. Wyoming had a dramatic 53 percent increase. Idaho made a 28 percent increase from 2012 to 2013 and a 24 percent increase from 2013 to 2014. One state — New Jersey — had a decrease of 25 percent in WMA production. The reasons for these fluctuations are uncertain. WMA makes up over half of total asphalt mix production in 15 states, up from eight states in 2013, and six of them — Delaware, Kansas, Louisiana, Mississippi, Ohio, and Virginia — reported WMA as 75 percent or more of total production in 2014. Nevada and Rhode Island did not report the use of WMA in 2014.

Nationally, the total tons of WMA increased from 106.4 million tons in 2013 to 113.8 million tons in 2014, a 7 percent increase.

Plant foaming is most commonly used technology in the production of WMA. Use of WMA additives increased from 13.1 percent in 2013 to 15.5 percent in 2014. This is still below the 17 percent market share noted in 2009, but given that WMA tonnage has increased by more than 577 percent since 2009, the volume of additives used, along with plant foaming, has increased significantly. WMA additives can have compaction, antistrip, and other benefits that may encourage use even when a reduction in production temperature is not sought or achieved by the producer.

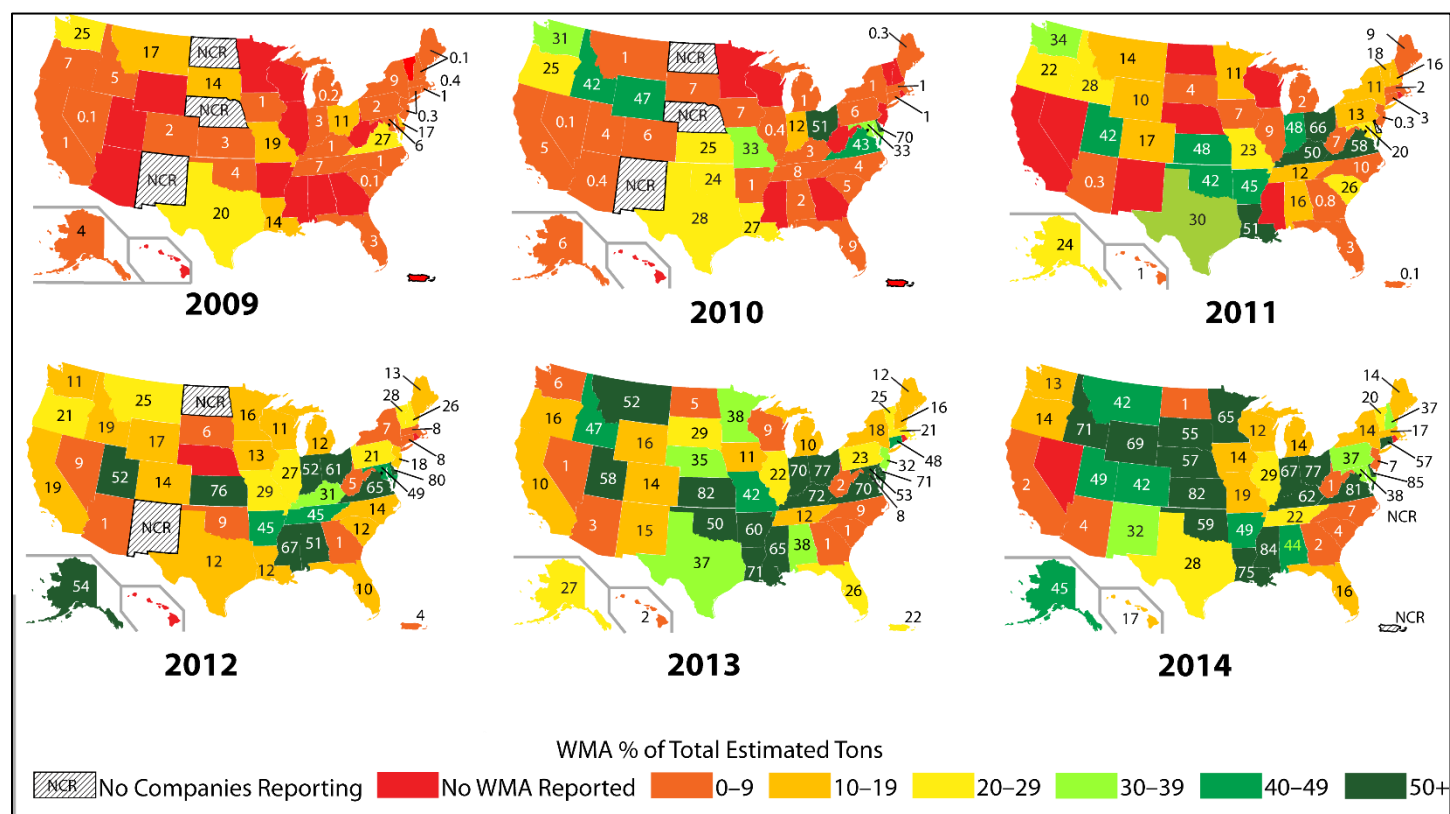


Figure 15: Estimated Percent of Total Production Using WMA

Other Recycled Materials

Starting with the 2012 survey, a series of questions was asked about the use of other recycled materials used in asphalt mixtures. Table 1 summarizes the questions in this section. The full questionnaire is included as Appendix A.

Producers were asked how many tons of mix were produced that incorporated other recycled materials, as well as how many tons of specific materials were used in mix production during 2014. Three recycled materials — ground tire rubber (GTR), steel slag, and blast furnace slag — were specifically listed in the survey. Respondents were able to specify up to two additional recycled materials that were used in mixes. Because the response rate to these questions about other recycled materials was expected to be low and because producers may not track the use of these materials, state and national estimates of total quantities used for these materials were not calculated. **All values in this section are reported values and do not represent estimates of the total quantity of these materials by state or nationally.** A total of 51 contractors from 24 states reported using other recycled materials in asphalt mixtures for 2014.

Ground Tire Rubber

Table 8 summarizes information on the use of ground tire rubber. 19 producers from nine states reported using GTR in some mixes. It must be noted that Arizona, which is known to use large quantities of GTR in mixes, had a relatively low participation rate in the survey, while Georgia had a very high participation rate. This likely explains why Georgia's reported quantity of GTR is higher than Arizona. The total reported tons of asphalt pavement mix using GTR stayed relatively flat from 2013 to 2014, rising from 1,195,594 tons in 2013 to 1,200,181 tons in 2014.

While reporting of tons produced that incorporate GTR is relatively straightforward to track and report, the tons of GTR used is harder to document due to different methods of producing mixes that incorporate GTR — the wet process, which uses GTR as an asphalt cement (AC) modifier, and the dry process, which incorporates GTR as a fine aggregate (Bahia, 2011) — and the likelihood that the GTR is either preblended at with AC at the terminal or it is blended onsite by a third party. Given these factors, producer reports of tons of GTR used versus tons of mix produced using GTR were given a heightened level of scrutiny to determine if the reported data was in a reasonable range. When reported tons of GTR were outside of the expected range producers were contacted to obtain correct values.

To give a picture of the total market size for GTR, the Rubber Manufacturers Association reports that 24.4 percent of U.S. scrap tires were processed into GTR in 2013. After removing wire, fluff, and agglomerated rubber, some 7 percent by weight of GTR produced (about 45,000 tons) was used in asphalt pavements in 2013 (RMA, 2014), including asphalt pavement mixtures, chip seals, and seal coats. Based on the RMA (2014) estimate, the GTR use reported in this survey represents about 28 percent of total GTR used in asphalt mixtures in the United States.

Table 8: Reported Tons Ground Tire Rubber

State	Reported Tons of Mix Using GTR			Reported Tons of GTR Used		
	2012	2013	2014	2012	2013	2014
Arizona	33,590	26,300	12,000	532	380	142
California	101,000	523,213	623,953	—	3,748	9,173
Florida	86,441	250,779	198,046	195	531	419
Georgia	281,958	65,000	162,000	—	260	750
Illinois	—	4,500	—	—	20	—
Indiana	—	13,000	—	—	30	—
Louisiana	25,000	104,395	—	—	550	—
Maine	—	14,000	—	—	219	—
Massachusetts	—	24,897	81,882	—	324	1,146
Michigan	2,400	12,000	9,300	20	71	51
Missouri	100,000	50,000	—	300	180	—
New Hampshire	—	28,000	50,000	—	358	780
New York	—	10	—	—	—	—
Ohio	36,200	1,500	23,000	—	8	150
Pennsylvania	—	18,000	—	—	140	—
Puerto Rico	—	10,000	NCR	—	170	—
Texas	25,000	50,000	40,000	—	—	200
Total	691,589	1,195,594	1,200,181	1,047	6,989	12,811
No. of Contractors	15	29	19			

Steel & Blast Furnace Slag

Tables 9 and 10 summarize the reported use of steel slag and blast furnace slag in asphalt mixes, respectively. Ten states reported using steel slag and seven states reported using blast slag in 2014. It is interesting to note that while the total tons of mix and materials for each slag type vary from year to year, there has been a consistent increase in the combined use of both slags as illustrated in Figure 16. Since slag aggregates are often used to improve skid resistance, this increase may be due to an increased emphasis on safety by pavement owners.

The National Slag Association estimates that 20 million tons of slag is produced and marketed annually (NSA, 2015). With 1.2 million tons of slag reported as used in asphalt mixes for 2014, this survey captures the use of more than 6 percent of total available slag. Because reported total tons of asphalt mixes from states using slag is about 55 percent of their total estimated tons, it is likely that asphalt pavements incorporate about 10 percent of total available slag.

Table 9: Reported Tons for Steel Slag, 2012–2014

State	Reported Tons of Mix Using Steel Slag			Reported Tons of Steel Slag Used		
	2012	2013	2014	2012	2013	2014
Alabama	625,000	750,000	837,083	133,441	165,000	112,480
Arkansas	120,000	25,000	84,900	12,000	2,500	12,735
Illinois	23,000	43,700	56,407	8,000	16,300	21,991
Indiana	70,000	161,115	111,800	44,000	61,985	41,500
Iowa	20,000	97,500	57,689	—	10,200	9,432
Kentucky	5,714	508,000	125,000	800	173,265	15,000
Michigan	—	750,000	754,131	—	95,000	136,382
Minnesota	145,500	200,000	238,000	21,800	30,000	34,000
Ohio	150,000	185,319	185,125	42,030	79,085	60,133
Tennessee	30,000	—	—	6,000	—	—
Washington	450,000	586,000	416,000	80,000	82,954	60,000
Total	1,639,214	3,306,634	2,866,135	348,071	716,289	503,653

Table 10: Reported Tons for Blast Furnace Slag, 2012–2014

State	Reported Tons of Mix Using Blast Furnace Slag			Reported Tons of Blast Furnace Slag Use		
	2012	2013	2014	2012	2013	2014
Alabama	100,000	110,000	100,000	10,100	12,500	10,000
Illinois	—	—	40,000	—	—	10,000
Indiana	1,487,000	116,500	375,000	304,000	57,000	150,000
Iowa	—	5,000	15,000	—	500	1,500
Kentucky	—	16,000	828,243	—	7,500	191,067
Michigan	500,000	700,000	329,000	50,000	107,000	43,750
Ohio	208,028	416,250	794,6000	72,400	110,613	145,105
Virginia	54,520	—	—	16,356	—	—
West Virginia	588,120	504,704	1,065,382	180,308	155,032	190,000
Total	2,937,668	1,868,454	3,547,225	633,164	450,145	741,422

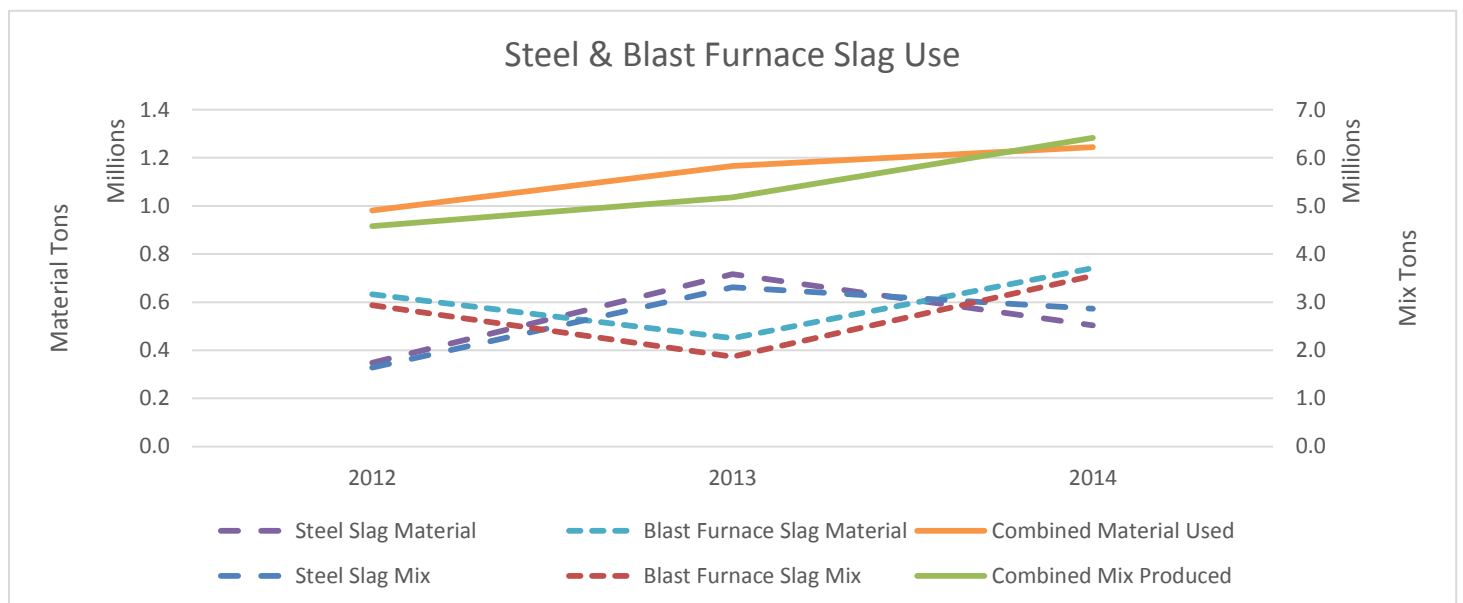


Figure 16: Steel and Blast Furnace Slag Use, 2012–2014

Other Recycled Materials

Table 11 summarizes other recycled materials used in asphalt mixtures. Other reported recycled materials include fly ash, cellulose fiber, foundry sand, and recycled glass. Recycled glass was only reported by Virginia in 2012 and has not been reported since. Fly ash use has been reported in Mississippi and Texas each year of the survey; Wisconsin reported using fly ash for the first time in 2014. Six states — Florida, Louisiana, Maryland, New York, Texas, and Virginia — reported using cellulose fibers in 2014. Georgia, which is known to use SMA and OGFC mixes that typically require fibers, reported using cellulose fibers in 2013, but did not report their use in 2014.

Table 11: Other Recycled Materials

State & Type of Other Recycled Material	Reported Tons of Mix Produced Using Other Recycled Material			Reported Tons of Other Recycled Material Used		
	2012	2013	2014	2012	2013	2014
Cellulose Fiber						
Florida	—	20,204	73,600	—	71	311
Georgia	—	43,000	—	—	129	—
Indiana	—	6,000	—	—	60	—
Louisiana	—	31,651	1,500	—	63	30
Maryland	—	145,000	120,000	—	440	360
Minnesota	—	5,000	—	—	15	—
Mississippi	76,000	—	—	250	—	—
New York	—	—	700	—	—	1
Texas	—	30,600	36,000	—	90	44
Virginia	—	—	74,000	—	—	120
Total	76,000	281,455	305,800	250	868	866
Fly Ash						
Mississippi	50,000	50,000	15,000	2,400	2,500	600
Texas	18,000	25,000	20,000	1,200	1,700	1,000
Wisconsin	—	—	26,000	—	—	1,500
Total	68,000	75,000	61,000	3,600	4,200	3,100
Bottom Ash						
South Dakota	52,000	—	—	4,280	—	—
Foundry Sand						
Missouri	5,000	15,130	22,310	500	1,514	2,231
Recycled Glass						
Virginia	173	—	—	34	—	—

Summary and Conclusions

The objective of this survey was to quantify the use of recycled materials and WMA produced by the asphalt pavement industry during the 2014 construction season. Asphalt mix producers from all 50 states completed the 2014 survey, and data was collected from a total of 228 companies/branches with 1,185 plants.

The estimated total asphalt mix production saw a slight increase from 350.7 million to 352.0 million tons from 2013 to 2014. The estimated DOT tonnage remained constant at 160 million tons for 2013 and 2014, while Other Agency tonnage decreased from 96.5 million to 90.7 million tons from 2013 to 2014. There was an increase in Commercial & Residential tonnage from 94.1 million ton 101.1 million tons.

The use of recycled material continues to increase slightly. The survey shows:

- The percent of producers reporting using RAP increased from 96 percent in 2009 and 2010 to 98 percent in 2011 and 2012 to 100 percent in 2013 and 2014.

- The average percent RAP used by all sectors has seen variable growth from 2009 to 2014. However, the change in the total percentage of RAP use by all sectors has increased steadily since 2009 at a rate of about 1 percent per year. The average estimated percent RAP used in all mixes has increased from 15.6 percent in 2009 to 20.4 percent in 2014.
- The estimated tons of RAP used in asphalt mixes reached 71.9 million tons in 2014. This represents greater than a 28 percent increase in the amount of tons used from 2009 to 2014.
- Contractors/branches reported having excess RAP increased from 87 to 91 percent from 2013 to 2014. For the second time in the survey's history, the estimated amount of RAP used for all purposes in 2014, including landfilling, exceeded the amount accepted. RAP use exceeded RAP received by 1.2 million tons in 2012 and 5.6 million tons in 2014.
- Use of both recycled manufacturing waste and post-consumer asphalt shingles in asphalt mixes increased from 1.65 million tons in 2013 to 1.96 million tons in 2014, which is the highest amount used since the survey began in 2009. This represents an 18.8 percent increase from 2013 to 2014, and a nearly 180 percent increase since 2009.
- The amount of RAS accepted by asphalt mix producers increased from 1.6 million tons in 2013 to 1.7 million tons in 2014, but remains below the high of 2.5 million tons in 2010. Since 2012, more RAS accepted been used for all purposes each year than is accepted. In 2014, 349,000 more tons of RAS was used for all purposes than was accepted. This is attributed to contractors having stockpiles of RAS and purchasing RAS from shingle processors. Eighty-two percent of contractors/branches using RAS reported having excess RAS for 2014.
- Of the RAS used in 2014, about 98 percent was used in asphalt mixtures. The remainder was primarily combined with aggregates. No RAS was landfilled.
- The number of states with reported RAS use decreased from 38 states in 2013 to 36 states in 2014.
- The combined saving of asphalt binder (\$550/ton) and aggregate (\$9.50/ton) by using RAP and RAS in asphalt mixes is more than \$2.8 billion. This keeps asphalt pavement mixture costs competitive and allows owners to achieve more roadway maintenance and construction activities within limited budgets.
- The number of states reporting use of ground tire rubber (GTR) in asphalt mixtures decreased from 17 in 2013 to nine in 2014, although the reported tonnage of mix produced using GTR remained essentially flat.
- The number of states reporting use of steel or blast furnace slags remained constant at 11 states in 2013 and 2014, although a slight but steady increase in the use of these materials is being reported.
- Three states, Mississippi, Texas and Wisconsin, reported using fly ash in asphalt mixtures in 2014. Mississippi and Texas reported using fly ash in both 2012 and 2013.
- The number of states reporting use of cellulose fibers decreased from seven states in 2013 to six states in 2014.
- Less commonly reported recycled materials in 2014 included foundry sand.

The use of WMA continues to increase, but at a slower rate. The survey shows:

- The estimated total production of WMA for 2014 was about 114 million tons. This was about a 7 percent increase over 2013 WMA (106 million tons) and more than 577 percent increase over 2009.
- WMA was about one-third of the total estimated asphalt mixture market in 2014.
- Plant foaming, representing over 84 percent of the market, is the most commonly used warm-mix technology; additives accounted for about 16 percent of the market.

The 2014 survey results show that the asphalt pavement industry continues to improve its outstanding record of sustainable practices by further increasing the use of recycled materials and WMA. RAP use has seen a steady increase of about 1 percent per year since 2009. In 2012 and 2014, more RAP was used than accepted. This was primarily due to a decrease in the amount of RAP collected compared to previous years. The reason for this decrease is uncertain, but it may be partially due to reduced construction activity, as indicated by lower total production volumes since 2011. While slightly more RAP was used than received in 2014, 91 percent of producers indicated they have excess RAP on hand, revealing that opportunities remain to increase the amount of RAP used in asphalt mixes through permissive specifications and through improved RAP processing, production equipment and procedures, and education.

RAS use saw a strong increase in 2014 to an all-time high of more than 1.96 million tons used in asphalt mixes. This represents nearly 15 percent of the estimated 13.2 million ton waste shingle market (1.2 million tons of MWAS and 12 million tons of PCAS).¹ As with RAP, permissive specifications, improved processing, production equipment and procedures, and education will help improve the amount and percentages used in asphalt mixes.

The asphalt pavement industry repurposes many products from other industries. The survey shows that steel and blast furnace slag use was reported in 11 states in 2013 and 2014, GTR use was reported in 16 jurisdictions in 2013 and nine states in 2014; cellulose fiber use was reported in one state in 2012, seven states in 2013, and six states in 2014; and fly ash in two states for 2012 and 2013, and three states in 2014. One state has reported using foundry sand each year since 2012.

WMA use again increased, but at a lower rate, in 2014 with a total production of a little less than 114 million tons, which represents nearly one-third of the total estimated asphalt mix production. All states, with the exceptions of Nevada and Rhode Island, reported using WMA in 2014. WMA use is expected to continue to grow as contractors and agencies gain experience and more states implement permissive specifications.

¹ According to the Asphalt Roofing Manufacturers Association (ARMA, 2015), about 13.2 million waste shingles are generated annually — about 12 million tons of post-consumer asphalt shingles (PCAS) and 1.2 million tons of manufacturing waste (MWAS). This is an increase from the traditionally cited figure of 11 million tons (NAHB, 1998), reflecting changes in housing stock and the housing market since 1998.

References

- ARMA (2015). Personal communication from R.X. Gumucio, Asphalt Roofing Manufacturers Association, Washington, D.C.
- Bahai, H.U. (2011). *Synthesis of Use of Crumb Rubber in Hot Mix Asphalt*. Final Report for RMRC Project 54. Recycled Materials Resource Center. Madison, Wisconsin.
- CIF (2013). 2013 NOVA Award Winner — Warm Mix Asphalt. Construction Innovation Forum, Walbridge, Ohio. <http://youtu.be/q47p1SAy4g4> [Accessed 14 August 2014]
- Copeland, A. (2011). *Reclaimed Asphalt Pavement in Asphalt Mixtures: State of the Practice*. Report FHWA-HRT-11-021. Federal Highway Administration, McLean, Virginia.
- Copeland, A., C.L. Jones, & J. Bukowski (2010). Reclaiming Roads. *Public Roads*, Vol. 73, No. 5 (March/April). Publication FHWA-HRT-10-001. <http://www.fhwa.dot.gov/publications/publicroads/10mar/06.cfm> [Accessed 14 August 2014]
- FHWA (2013). Every Day Counts: Warm Mix Asphalt [website]. Federal Highway Administration, Washington, D.C. <https://www.fhwa.dot.gov/everydaycounts/technology/asphalt/intro.cfm> [Accessed 14 August 2014]
- Hansen, K.R., & A. Copeland (2013a). *2nd Annual Asphalt Pavement Industry Survey on Reclaimed Asphalt Pavement, Reclaimed Asphalt Shingles, and Warm-Mix Asphalt Usage: 2009–2011* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2013b). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2009–2012, 3rd Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2014). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2009–2013, 4th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & D.E. Newcomb (2011). *Asphalt Pavement Mix Production Survey: Reclaimed Asphalt Pavement, Reclaimed Asphalt Shingles, Warm-Mix Asphalt Usage: 2009–2010* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- NAHB (1998). *From Roofs to Roads... Recycling Asphalt Roofing Shingles into Paving Materials*. NAHB Research Center, National Association of Home Builders, Upper Marlboro, Maryland.
- NSA (2015). *Slag ... A Green Product in Its Own Right!* (Document 207-2). National Slag Association, Pleasant Grove, Utah. <http://nationalslag.org/sites/nationalslag/files/documents/SLAG-A%20Green%20Product.pdf> [Accessed 22 September 2015]
- Pappas, J. (2011). Recycling Materials Survey. Presented at the RAP Expert Task Group May Meeting, May 2011, Irvine, California. <http://www.morerap.us/files/meetings/05-11/pappas-recycling-materials-survey.pdf> [Accessed 14 August 2014]
- Prowell, B.D., G.C. Hurley, & B. Frank (2012). *Warm-Mix Asphalt: Best Practices, 3rd Edition* (QIP 125). National Asphalt Pavement Association, Lanham, Maryland.
- RMA (2014). *2013 U.S. Scrap Tire Management Summary*. Rubber Manufacturers Association, Washington, D.C. http://www.rma.org/download/scrap-tires/market-reports/US_STMarket2013.pdf [Accessed 22 September 2015]
- West, R.C., & A. Copeland (2015). *High RAP Asphalt Pavements: Japan Practice — Lessons Learned* (IS 139). National Asphalt Pavement Association, Lanham, Maryland.



National Asphalt Pavement Association

NAPA Building

5100 Forbes Blvd.

Lanham, Maryland 20706-4407

www.AsphaltPavement.org

napa@AsphaltPavement.org

Tel: 301-731-4748

Toll Free: 1-888-468-6499

Fax: 301-731-4621

Publication Sales:

store.AsphaltPavement.org

napa-orders@abdintl.com

Toll Free: 888-600-4474

Tel: 412-741-6314

Fax: 412-741-0609

**5th Annual Asphalt Pavement Industry Survey
IS-138**



Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2014

Appendix A:
Survey Forms

Recycled Materials and WMA Survey 2013

Purpose

The National Asphalt Pavement Association is working with the Federal Highway Administration to determine the amount of hot-mix asphalt (HMA), warm-mix asphalt (WMA), and recycled materials being produced and used in each state. This survey will be used to collect this data.

It is important to the industry that you complete this survey so that we have accurate information regarding the use of recycled materials and Warm-Mix Asphalt and to identify areas needing assistance in implementation.

DATA FROM THIS SURVEY WILL BE CONFIDENTIAL AND WILL BE USED ONLY FOR THE PURPOSES OF DETERMINING THESE QUANTITIES. IT WILL NOT BE USED FOR ANY OTHER PURPOSE. DATA WILL BE REPORTED BY STATE ONLY. NO COMPANY-SPECIFIC INFORMATION WILL BE DISCLOSED OR USED IN ANY WAY.

Survey results will be shared with industry and government agencies and officials to help in the implementation of recycling and warm-mix technologies.

By completing this survey you will be eligible to receive a complimentary copy of the full report.

Your participation is greatly appreciated.

Recycled Materials and WMA Survey 2013

Contact Information

The following information will be used only to confirm that we do not get duplicate information from a company and to contact you if we have any questions regarding your answers.

Contact Kent Hansen, khansen@asphaltpavement.org, or Audrey Copeland, acopeland@asphaltpavement.org, or by phone at 888-468-6499 at NAPA if you have any questions.

***1. Company/Branch Name:**

***2. Contact Person's Name & Address**

***3. Contact Person's Email**

***4. Contact Person's Phone Number**

Recycled Materials and WMA Survey 2013

State

Please select the state for which you are providing the information.

If your branch operates in more than one state, please complete a separate questionnaire for each state. If a plant provides mix for more than one state, please divide the tonnage accordingly, using your best estimate if specific data is not available.

*5. Which state is the information provided for?

- | | | |
|--------------------------------------------|------------------------------------------------|-----------------------------------------|
| <input type="radio"/> Alabama | <input type="radio"/> Kentucky | <input type="radio"/> Ohio |
| <input type="radio"/> Alaska | <input type="radio"/> Louisiana | <input type="radio"/> Oklahoma |
| <input type="radio"/> American Samoa | <input type="radio"/> Maine | <input type="radio"/> Oregon |
| <input type="radio"/> Arizona | <input type="radio"/> Maryland | <input type="radio"/> Pennsylvania |
| <input type="radio"/> Arkansas | <input type="radio"/> Massachusetts | <input type="radio"/> Puerto Rico |
| <input type="radio"/> California | <input type="radio"/> Michigan | <input type="radio"/> Rhode Island |
| <input type="radio"/> Colorado | <input type="radio"/> Minnesota | <input type="radio"/> South Carolina |
| <input type="radio"/> Connecticut | <input type="radio"/> Mississippi | <input type="radio"/> South Dakota |
| <input type="radio"/> Delaware | <input type="radio"/> Missouri | <input type="radio"/> Tennessee |
| <input type="radio"/> District of Columbia | <input type="radio"/> Montana | <input type="radio"/> Texas |
| <input type="radio"/> Florida | <input type="radio"/> Nebraska | <input type="radio"/> US Virgin Islands |
| <input type="radio"/> Georgia | <input type="radio"/> Nevada | <input type="radio"/> Utah |
| <input type="radio"/> Guam | <input type="radio"/> New Hampshire | <input type="radio"/> Vermont |
| <input type="radio"/> Hawaii | <input type="radio"/> New Jersey | <input type="radio"/> Virginia |
| <input type="radio"/> Idaho | <input type="radio"/> New Mexico | <input type="radio"/> Washington |
| <input type="radio"/> Illinois | <input type="radio"/> New York | <input type="radio"/> West Virginia |
| <input type="radio"/> Indiana | <input type="radio"/> North Carolina | <input type="radio"/> Wisconsin |
| <input type="radio"/> Iowa | <input type="radio"/> North Dakota | <input type="radio"/> Wyoming |
| <input type="radio"/> Kansas | <input type="radio"/> Northern Mariana Islands | |

*6. How many plants does this survey response cover?

Number of plants

Recycled Materials and WMA Survey 2013

Total Asphalt Tonnage for 2013

Please complete the following information for the total tonnage of all asphalt production in 2013.

***7. What was your total tonnage of asphalt mixes in 2013 for the following sectors? (Use best estimate if data is not available.)**

State DOT

Other Agency (City, County, FAA, Military)

Commercial & Residential

Recycled Materials and WMA Survey 2013

RAP Supply and Use 2013

Please complete the following information on the amount of RAP received and used for 2013.

***8. Did you accept, process, or use RAP in the state during 2013?**

☐ Yes

☐ No

Recycled Materials and WMA Survey 2013

RAP Supply and Use 2013

Please complete the following information regarding the amount of RAP received and used for 2013.

***9. How many tons of removed asphalt pavement and asphalt millings were accepted/delivered to your facilities in the state in 2013?**

Tons:

***10. How many tons of RAP were used in 2013 for the following purposes? (Use best estimate if data not available.)**

Recycled Back into HMA/WMA Mixes:

Aggregate Base:

Cold Mix:

Other:

Landfilled:

***11. What was the average RAP percentage used in asphalt mixes during 2013 for the following sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military)

Commercial & Residential

***12. At the end of the year 2013 did you have excess RAP (processed or unprocessed) in inventory?**

☐ Yes

☐ No

Recycled Materials and WMA Survey 2013

Reclaimed Asphalt Shingles (RAS) Supply and Use for 2013

Please complete the following information on the amount of waste shingles received (processed and unprocessed) and used for 2013.

***13. Did you accept waste shingles and/or process or use reclaimed asphalt shingles (RAS) in 2013?**

☐ Yes

☐ No

Recycled Materials and WMA Survey 2013

Reclaimed Asphalt Shingles (RAS) Supply and Use for 2013

Please complete the following information regarding the amount of waste shingles received (processed and unprocessed) and used during 2013.

***14. How many tons of unprocessed shingles (manufacturers waste and tear-offs) were accepted/delivered to your facilities in the state in 2013?**

Tons:

***15. How many tons of reclaimed asphalt shingles (RAS) were used for the following purposes in 2013? (Use best estimate if data not available.)**

Recycled into HMA/WMA Mixes:

Aggregate Base:

Cold Mix:

Other:

Landfilled:

***16. What was average RAS percentage used in asphalt mixes in 2013 for the following sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military)

Commercial & Residential

***17. At the end of the year 2013 did you have any excess RAS? (Include processed and unprocessed shingles.)**

☐ Yes

☐ No

Recycled Materials and WMA Survey 2013

Warm-Mix Asphalt Production for 2013

Warm-mix asphalt is the generic term for a variety of technologies that allow the producers of asphalt pavement material to lower the temperatures at which the material is mixed and placed on the road by 10 to 100 degrees F.

***18. Did any of your plants in this state use Warm-Mix Asphalt technologies in 2013?**

- ☐ Yes
- ☐ No

Recycled Materials and WMA Survey 2013

Warm-Mix Asphalt Production for 2013

Warm-mix asphalt is the generic term for a variety of technologies that allow the producers of asphalt pavement material to lower the temperatures at which the material is mixed and placed on the road by 10 to 100 degrees F.

***19. What was average percent of mixes produced using warm-mix asphalt technologies in 2013 for the different sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military)

Commercial & Residential

***20. What percentage of the total warm-mix asphalt (WMA) for 2013 was produced using the following technologies? (Use best estimate if data not available.)**

Chemical Admixture

Additive (Zeolite) Foaming

Plant Foaming

Organic (Wax) Additive

Recycled Materials and WMA Survey 2013

Other Recycled Materials for 2013

Please let us know if you used any other recycled materials in HMA/WMA mixes in 2013.

Other Recycled Material

***21. Did you use other recycled materials (excluding RAP and RAS) in your mixes in 2013?**

(This includes materials added to the mix such as: ground tire rubber, blast furnace slag, steel slag, glass, fly ash, bottom ash, foundry sand, cellulose fibers, etc.)

☐ Yes

☐ No

Recycled Materials and WMA Survey 2013

*22. What other recycled material (excluding RAP and RAS) did you use in your mixes in 2013?

	Yes	No
Ground Tire Rubber	<input type="radio"/>	<input type="radio"/>
Steel Slag	<input type="radio"/>	<input type="radio"/>
Blast Furnace Slag	<input type="radio"/>	<input type="radio"/>
Other 1*	<input type="radio"/>	<input type="radio"/>
Other 2*	<input type="radio"/>	<input type="radio"/>
Other 3*	<input type="radio"/>	<input type="radio"/>

* Please describe the other recycled materials used.

*23. How many tons of HMA/WMA was produced using this product. (Use best estimate if data not available.)

Ground Tire Rubber	<input type="text"/>
Steel Slag	<input type="text"/>
Blast Furnace Slag	<input type="text"/>
Other 1	<input type="text"/>
Other 2	<input type="text"/>
Other 3	<input type="text"/>

24. How many tons of the recycled product was used in 2013? (Enter 0 if you do not have a reasonable estimate of this quantity)

Ground Tire Rubber	<input type="text"/>
Steel Slag	<input type="text"/>
Blast Furnace Slag	<input type="text"/>
Other 1	<input type="text"/>
Other 2	<input type="text"/>
Other 3	<input type="text"/>

Thank You

25. Would you like a complimentary copy of the final report?

- ☐ Yes
- ☐ No

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2014

Appendix B:
State-by-State Use of
Recycled Materials and Warm-Mix Asphalt
in Asphalt Pavement Mixtures

Alabama

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	3.9	4.0	8.0	7.5
	DOT	2.5	2.5	5.1	4.6
	Other Agency	0.5	0.6	1.1	1.1
	Commercial and Residential	0.9	0.9	1.8	1.7
	Companies/Branches Reporting	5	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.0	0.9	2.1	1.6
	Used in HMA/WMA	0.9	0.9	1.9	1.7
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	21.6%	34.0%		
	Average % for Other Agency Mixes	20.2%	29.3%		
	Average % for Commercial & Residential	34.0%	38.0%		
	State Average All Mixes Based on % Reported for Different Sectors	24.2%	34.2%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	23.9%	23.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	99.5	112.4	205.6	208.6
	Used in HMA/WMA	85.2	89.8	176.1	166.7
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	2.28%	2.35%		
	Average % for Other Agency Mixes	2.42%	1.88%		
	Average % for Commercial & Residential	1.86%	2.10%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	2.20%	2.22%		
	% Companies/Branches Reporting Using RAS	100%	100%		
WMA		% Total Production		Tons (Millions)	
	DOT	43%	54%	2.2	2.5
	Other Agency	42%	37%	0.5	0.4
	Commercial and Residential	24%	20%	0.4	0.3
	Total			3.1	3.3
	% of Market				
	Chemical Additive %	19%	26%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	81%	74%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	20%	16%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Alaska

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	4.9	4.8
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Arizona

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.0	0.8	6.8	6.6
	DOT	0.1	0.1	0.8	0.9
	Other Agency	0.4	0.2	2.8	1.3
	Commercial and Residential	0.5	0.6	3.2	4.5
	Companies/Branches Reporting	3	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.1	0.1	0.4	0.8
	Used in HMA/WMA	0.1	0.1	0.9	0.9
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	13.6%	13.8%		
	Average % for Other Agency Mixes	12.4%	12.2%		
	Average % for Commercial & Residential	19.6%	18.7%		
	State Average All Mixes Based on % Reported for Different Sectors	15.9%	16.9%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	13.2%	13.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.0	0.0	0.0	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	0%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	29%	17%	0.2	0.1
	Other Agency	0%	3%	0.0	0.0
	Commercial and Residential	0%	2%	0.0	0.1
	Total			0.2	0.3
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	11%	22%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Arkansas

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.0	1.7	4.2	5.1
	DOT	0.7	1.0	3.0	3.1
	Other Agency	0.1	0.2	0.5	0.5
	Commercial and Residential	0.2	0.5	0.7	1.5
	Companies/Branches Reporting	3	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.1	0.3	0.5	0.8
	Used in HMA/WMA	0.1	0.2	0.5	0.7
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	14.3%	19.3%		
	Average % for Other Agency Mixes	13.1%	15.2%		
	Average % for Commercial & Residential	15.0%	18.9%		
	State Average All Mixes Based on % Reported for Different Sectors	14.3%	18.8%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	12.2%	13.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	7.2	14.7	31.8	44.8
	Used in HMA/WMA	5.6	14.1	24.5	43.1
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	2.0	0.0	6.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.15%	0.24%		
	Average % for Other Agency Mixes	1.23%	1.50%		
	Average % for Commercial & Residential	2.09%	1.86%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.58%	0.84%		
	% Companies/Branches Reporting Using RAS	100%	50%		
WMA		% Total Production		Tons (Millions)	
	DOT	55%	42%	1.7	1.3
	Other Agency	81%	50%	0.4	0.2
	Commercial and Residential	67%	62%	0.4	0.9
	Total			2.5	2.5
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	33%	11%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

California

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	11.1	10.2	24.3	23.1
	DOT	2.9	4.1	6.3	9.4
	Other Agency	4.1	2.8	9.0	6.3
	Commercial and Residential	4.1	3.3	9.0	7.4
	Companies/Branches Reporting	7	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	2.1	1.4	4.6	3.2
	Used in HMA/WMA	1.2	1.3	2.7	2.9
	Used in Aggregate	0.2	0.3	0.5	0.6
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	14.3%	14.3%		
	Average % for Other Agency Mixes	15.0%	15.2%		
	Average % for Commercial & Residential	17.2%	17.8%		
	State Average All Mixes Based on % Reported for Different Sectors	15.6%	15.7%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	11.1%	12.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	9.9	4.5	21.7	10.2
	Used in HMA/WMA	8.9	6.6	19.5	14.9
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.01%		
	Average % for Commercial & Residential	0.22%	0.19%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.08%	0.06%		
	% Companies/Branches Reporting Using RAS	43%	50%		
WMA		% Total Production		Tons (Millions)	
	DOT	3%	3%	0.2	0.2
	Other Agency	12%	4%	1.1	0.2
	Commercial and Residential	13%	1%	1.2	0.1
	Total			2.5	0.6
	% of Market				
	Chemical Additive %	1%	23%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	99%	77%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	12%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Colorado

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.0	2.9	7.0	7.0
	DOT	0.5	0.8	1.8	2.0
	Other Agency	0.7	1.2	2.3	3.0
	Commercial and Residential	0.8	0.8	2.9	2.0
	Companies/Branches Reporting	6	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.4	0.8	1.3	2.0
	Used in HMA/WMA	0.5	0.6	1.9	1.4
	Used in Aggregate	0.1	0.1	0.2	0.3
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	18.4%	21.8%		
	Average % for Other Agency Mixes	16.8%	21.8%		
	Average % for Commercial & Residential	20.2%	23.7%		
	State Average All Mixes Based on % Reported for Different Sectors	18.6%	22.3%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	27.3%	20.6%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.2	0.1	0.7	0.2
	Used in HMA/WMA	0.0	8.5	0.0	20.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	1.06%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.30%		
	% Companies/Branches Reporting Using RAS	17%	60%		
WMA		% Total Production		Tons (Millions)	
	DOT	5%	39%	0.1	0.8
	Other Agency	14%	42%	0.3	1.3
	Commercial and Residential	19%	46%	0.6	0.9
	Total			1.0	3.0
	% of Market				
	Chemical Additive %	4%	23%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	96%	77%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	14%	16%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Connecticut

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	2.1	4.9	4.7
	DOT	*	0.9	*	2.0
	Other Agency	*	0.6	*	1.2
	Commercial and Residential	*	0.7	*	1.4
	Companies/Branches Reporting	*	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	0.5	*	1.0
	Used in HMA/WMA	*	0.4	*	1.0
	Used in Aggregate	*	0.0	*	0.1
	Used in Cold Mix	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	*	18.8%		
	Average % for Other Agency Mixes	*	19.8%		
	Average % for Commercial & Residential	*	25.3%		
	State Average All Mixes Based on % Reported for Different Sectors	*	21.1%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	21.0%		
	% Companies/Branches Reporting Using RAP	*	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	0.2	*	0.5
	Used in HMA/WMA	*	0.2	*	0.5
	Used in Aggregate	*	0.0	*	0.0
	Used in Cold Mix	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	*	0.00%		
	Average % for Other Agency Mixes	*	0.00%		
	Average % for Commercial & Residential	*	0.03%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	0.01%		
	% Companies/Branches Reporting Using RAS	*	33%		
WMA		% Total Production		Tons (Millions)	
	DOT	*	58%	*	1.2
	Other Agency	*	54%	*	0.7
	Commercial and Residential	*	56%	*	0.8
	Total			*	2.6
	% of Market				
	Chemical Additive %	*	0%		
	Additive Foaming %	*	2%		
	Plant Foaming %	*	98%		
	Organic Additive %	*	0%		
	% Companies/Branches Reporting Using WMA	*	11%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Delaware

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	1.3	1.5
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

District of Columbia

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	NCR	1.9	1.9
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial and Residential	*	NCR	*	NCR
	Companies/Branches Reporting	*	NCR		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	NCR	*	NCR
	Used in HMA/WMA	*	NCR	*	NCR
	Used in Aggregate	*	NCR	*	NCR
	Used in Cold Mix	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
		Average % Used in Mixes			
	Average % for DOT Mixes	*	NCR		
	Average % for Other Agency Mixes	*	NCR		
	Average % for Commercial & Residential	*	NCR		
	State Average All Mixes Based on % Reported for Different Sectors	*	NCR		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	NCR		
	% Companies/Branches Reporting Using RAP	*	NCR		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	NCR	*	NCR
	Used in HMA/WMA	*	NCR	*	NCR
	Used in Aggregate	*	NCR	*	NCR
	Used in Cold Mix	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
		Average % Used in Mixes			
	Average % for DOT Mixes	*	NCR		
	Average % for Other Agency Mixes	*	NCR		
	Average % for Commercial & Residential	*	NCR		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	NCR		
	% Companies/Branches Reporting Using RAS	*	NCR		
WMA		% Total Production		Tons (Millions)	
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial and Residential	*	NCR	*	NCR
	Total			*	NCR
		% of Market			
	Chemical Additive %	*	NCR		
	Additive Foaming %	*	NCR		
	Plant Foaming %	*	NCR		
	Organic Additive %	*	NCR		
	% Companies/Branches Reporting Using WMA	*	NCR		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Florida

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	6.1	6.5	12.0	13.3
	DOT	3.5	2.8	6.8	5.8
	Other Agency	0.9	1.2	1.7	2.4
	Commercial and Residential	1.8	2.5	3.5	5.1
	Companies/Branches Reporting	7	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	2.1	2.1	4.2	4.4
	Used in HMA/WMA	1.9	2.1	3.7	4.3
	Used in Aggregate	0.1	0.1	0.2	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	28.3%	27.9%		
	Average % for Other Agency Mixes	32.0%	34.3%		
	Average % for Commercial & Residential	38.2%	39.1%		
	State Average All Mixes Based on % Reported for Different Sectors	31.7%	33.4%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	31.1%	32.2%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	3.0	0.0	6.1
	Used in HMA/WMA	0.8	2.5	1.6	5.1
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.09%		
	Average % for Commercial & Residential	0.05%	0.06%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.01%	0.04%		
	% Companies/Branches Reporting Using RAS	14%	14%		
WMA		% Total Production		Tons (Millions)	
	DOT	35%	17%	2.4	1.0
	Other Agency	14%	23%	0.2	0.6
	Commercial and Residential	15%	12%	0.5	0.6
	Total			3.1	2.2
	% of Market				
	Chemical Additive %	18%	8%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	82%	92%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	6%	4%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Georgia

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	5.2	2.3	6.8	4.5
	DOT	1.9	1.0	2.5	2.0
	Other Agency	1.2	0.5	1.6	1.0
	Commercial and Residential	2.1	0.8	2.7	1.6
	Companies/Branches Reporting	5	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	3.1	0.5	4.0	1.0
	Used in HMA/WMA	1.2	0.5	1.6	0.9
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	23.2%	26.9%		
	Average % for Other Agency Mixes	23.7%	25.1%		
	Average % for Commercial & Residential	23.5%	27.5%		
	State Average All Mixes Based on % Reported for Different Sectors	23.5%	26.7%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	23.5%	21.0%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.7	0.0	0.9	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.03%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.01%	0.00%		
	% Companies/Branches Reporting Using RAS	20%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	2%	3%	0.1	0.1
	Other Agency	1%	0%	0.0	0.0
	Commercial and Residential	1%	2%	0.0	0.0
	Total			0.1	0.1
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	4%	6%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Hawaii

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	2.0	1.9
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	0.8	1.0	3.1	3.1
	DOT	0.4	0.6	1.7	1.7
	Other Agency	0.1	0.2	0.6	0.6
	Commercial and Residential	0.2	0.3	0.8	0.8
	Companies/Branches Reporting	4	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	0.2	1.1	0.5
	Used in HMA/WMA	0.2	0.3	0.8	0.8
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	31.7%	28.4%		
	Average % for Other Agency Mixes	21.6%	27.9%		
	Average % for Commercial & Residential	31.7%	28.9%		
	State Average All Mixes Based on % Reported for Different Sectors	29.8%	28.4%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	27.6%	24.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.0	0.0	0.0	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	0%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	61%	75%	1.0	1.3
	Other Agency	27%	80%	0.2	0.4
	Commercial and Residential	32%	58%	0.3	0.5
	Total			1.4	2.2
	% of Market				
	Chemical Additive %	0%	8%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	92%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	19%	25%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Illinois

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.3	3.5	12.5	13.8
	DOT	0.9	1.6	4.9	6.4
	Other Agency	0.9	1.0	4.8	4.0
	Commercial and Residential	0.5	0.9	2.7	3.5
	Companies/Branches Reporting	9	9		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.7	1.4	3.5	5.5
	Used in HMA/WMA	0.5	1.0	2.8	3.8
	Used in Aggregate	0.0	0.3	0.2	1.3
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	22.1%	24.9%		
	Average % for Other Agency Mixes	23.4%	27.2%		
	Average % for Commercial & Residential	31.2%	27.1%		
	State Average All Mixes Based on % Reported for Different Sectors	24.6%	26.1%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	22.1%	27.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.2	42.9	1.1	169.8
	Used in HMA/WMA	17.3	68.2	92.3	269.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.70%	1.81%		
	Average % for Other Agency Mixes	0.57%	2.12%		
	Average % for Commercial & Residential	1.10%	2.05%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.74%	1.95%		
	% Companies/Branches Reporting Using RAS	56%	56%		
WMA		% Total Production		Tons (Millions)	
	DOT	40%	22%	2.0	1.4
	Other Agency	9%	46%	0.4	1.8
	Commercial and Residential	14%	24%	0.4	0.8
	Total			2.8	4.1
	% of Market				
	Chemical Additive %	42%	30%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	58%	70%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	5%	5%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Indiana

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	4.1	4.8	9.0	9.2
	DOT	1.9	2.0	4.1	3.8
	Other Agency	1.0	1.8	2.2	3.4
	Commercial and Residential	1.2	1.0	2.7	2.0
	Companies/Branches Reporting	7	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.2	1.9	2.6	3.7
	Used in HMA/WMA	1.1	1.4	2.4	2.7
	Used in Aggregate	0.0	0.0	0.0	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	26.0%	23.2%		
	Average % for Other Agency Mixes	26.9%	26.3%		
	Average % for Commercial & Residential	29.2%	27.0%		
	State Average All Mixes Based on % Reported for Different Sectors	27.2%	25.2%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	27.2%	29.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	31.0	20.0	68.3	38.7
	Used in HMA/WMA	50.0	33.5	110.2	64.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.84%	0.73%		
	Average % for Other Agency Mixes	1.51%	0.68%		
	Average % for Commercial & Residential	1.57%	0.70%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	1.22%	0.70%		
	% Companies/Branches Reporting Using RAS	86%	100%		
WMA		% Total Production		Tons (Millions)	
	DOT	71%	67%	2.9	2.5
	Other Agency	68%	64%	1.5	2.2
	Commercial and Residential	73%	70%	2.0	1.4
	Total			6.3	6.1
	% of Market				
	Chemical Additive %	0%	3%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	97%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	14%	25%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	3.4	2.2	4.2	3.6
	DOT	2.0	1.3	2.5	2.2
	Other Agency	1.1	0.6	1.4	1.0
	Commercial and Residential	0.3	0.3	0.4	0.5
	Companies/Branches Reporting	10	8		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.5	0.4	0.7	0.6
	Used in HMA/WMA	0.6	0.3	0.7	0.5
	Used in Aggregate	0.0	0.0	0.0	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	18.0%	16.8%		
	Average % for Other Agency Mixes	16.6%	18.7%		
	Average % for Commercial & Residential	17.3%	18.6%		
	State Average All Mixes Based on % Reported for Different Sectors	17.5%	17.6%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	17.5%	15.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	13.5	10.5	16.6	17.3
	Used in HMA/WMA	27.7	14.0	34.1	23.1
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.82%	0.59%		
	Average % for Other Agency Mixes	0.92%	0.98%		
	Average % for Commercial & Residential	0.40%	0.15%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.82%	0.64%		
	% Companies/Branches Reporting Using RAS	60%	38%		
WMA		% Total Production		Tons (Millions)	
	DOT	10%	13%	0.2	0.3
	Other Agency	16%	15%	0.2	0.1
	Commercial and Residential	3%	20%	0.0	0.1
	Total			0.5	0.5
	% of Market				
	Chemical Additive %	0%	3%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	97%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	5%	6%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Kansas

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.7	2.4	4.5	4.0
	DOT	0.9	1.3	2.3	2.2
	Other Agency	0.5	0.7	1.4	1.2
	Commercial and Residential	0.3	0.3	0.8	0.6
	Companies/Branches Reporting	5	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.4	0.7	1.1	1.2
	Used in HMA/WMA	0.4	0.5	1.1	0.9
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	26.1%	20.1%		
	Average % for Other Agency Mixes	21.9%	21.4%		
	Average % for Commercial & Residential	29.4%	25.2%		
	State Average All Mixes Based on % Reported for Different Sectors	25.4%	21.3%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	23.4%	22.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	10.0	4.6	26.6	7.8
	Used in HMA/WMA	2.7	14.0	7.1	23.7
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.06%	0.99%		
	Average % for Other Agency Mixes	0.20%	0.05%		
	Average % for Commercial & Residential	0.35%	0.18%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.16%	0.59%		
	% Companies/Branches Reporting Using RAS	20%	60%		
WMA		% Total Production		Tons (Millions)	
	DOT	92%	88%	2.1	2.0
	Other Agency	70%	76%	1.0	0.9
	Commercial and Residential	72%	72%	0.6	0.4
	Total			3.7	3.3
	% of Market				
	Chemical Additive %	28%	22%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	72%	78%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	20%	16%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Kentucky

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	4.6	4.4	7.0	9.0
	DOT	3.2	3.1	4.9	6.4
	Other Agency	0.9	0.8	1.4	1.6
	Commercial and Residential	0.5	0.5	0.8	1.0
	Companies/Branches Reporting	7	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.7	0.5	1.1	1.0
	Used in HMA/WMA	0.7	0.6	1.0	1.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	16.6%	15.5%		
	Average % for Other Agency Mixes	16.5%	18.5%		
	Average % for Commercial & Residential	18.4%	19.1%		
	State Average All Mixes Based on % Reported for Different Sectors	16.8%	16.4%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	14.8%	13.6%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	7.7	34.0	11.8	70.0
	Used in HMA/WMA	12.7	32.2	19.4	66.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.29%	0.92%		
	Average % for Other Agency Mixes	0.05%	0.34%		
	Average % for Commercial & Residential	0.61%	0.23%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.28%	0.74%		
	% Companies/Branches Reporting Using RAS	71%	29%		
WMA		% Total Production		Tons (Millions)	
	DOT	72%	60%	3.5	3.8
	Other Agency	74%	71%	1.0	1.2
	Commercial and Residential	72%	61%	0.5	0.6
	Total			5.0	5.6
	% of Market				
	Chemical Additive %	23%	18%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	77%	82%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	14%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Louisiana

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.0	*	6.0	6.3
	DOT	1.3	*	3.9	*
	Other Agency	0.4	*	1.2	*
	Commercial and Residential	0.3	*	0.9	*
	Companies/Branches Reporting	3	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	*	0.9	*
	Used in HMA/WMA	0.3	*	1.1	*
	Used in Aggregate	0.0	*	0.0	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	19.1%	*		
	Average % for Other Agency Mixes	16.5%	*		
	Average % for Commercial & Residential	18.5%	*		
	State Average All Mixes Based on % Reported for Different Sectors	18.5%	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	17.7%	*		
	% Companies/Branches Reporting Using RAP	100%	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	1.5	*	4.6	*
	Used in HMA/WMA	0.5	*	1.5	*
	Used in Aggregate	0.0	*	0.0	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	0.00%	*		
	Average % for Other Agency Mixes	0.00%	*		
	Average % for Commercial & Residential	0.16%	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.03%	*		
	% Companies/Branches Reporting Using RAS	33%	*		
WMA		% Total Production		Tons (Millions)	
	DOT	76%	*	2.9	*
	Other Agency	70%	*	0.9	*
	Commercial and Residential	50%	*	0.5	*
	Total			4.3	*
		% of Market			
	Chemical Additive %	1%	*		
	Additive Foaming %	0%	*		
	Plant Foaming %	99%	*		
	Organic Additive %	0%	*		
	% Companies/Branches Reporting Using WMA	33%	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Maine

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.9	1.4	2.0	2.1
	DOT	0.8	0.7	0.9	1.0
	Other Agency	0.4	0.3	0.4	0.5
	Commercial and Residential	0.7	0.4	0.7	0.5
	Companies/Branches Reporting	3	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.1	0.1	0.1	0.1
	Used in HMA/WMA	0.3	0.3	0.4	0.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	16.3%	17.4%		
	Average % for Other Agency Mixes	17.0%	16.9%		
	Average % for Commercial & Residential	17.8%	22.1%		
	State Average All Mixes Based on % Reported for Different Sectors	17.0%	18.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	17.9%	21.4%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	3.9	0.0	5.9
	Used in HMA/WMA	16.9	10.8	17.7	16.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.98%	0.87%		
	Average % for Other Agency Mixes	0.90%	0.82%		
	Average % for Commercial & Residential	0.74%	0.62%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.88%	0.79%		
	% Companies/Branches Reporting Using RAS	67%	67%		
WMA		% Total Production		Tons (Millions)	
	DOT	4%	11%	0.0	0.1
	Other Agency	15%	13%	0.1	0.1
	Commercial and Residential	21%	21%	0.2	0.1
	Total			0.2	0.3
	% of Market				
	Chemical Additive %	3%	3%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	97%	114%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	11%	22%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Maryland

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	3.8	2.5	5.8	6.8
	DOT	1.5	1.0	2.3	2.6
	Other Agency	1.1	1.0	1.7	2.6
	Commercial and Residential	1.2	0.6	1.9	1.6
	Companies/Branches Reporting	9	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.5	0.8	2.3	2.1
	Used in HMA/WMA	0.9	0.5	1.3	1.4
	Used in Aggregate	0.3	0.1	0.4	0.3
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	21.0%	22.3%		
	Average % for Other Agency Mixes	25.3%	18.4%		
	Average % for Commercial & Residential	29.2%	16.3%		
	State Average All Mixes Based on % Reported for Different Sectors	24.9%	19.4%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	23.1%	20.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	16.0	9.5	24.3	25.6
	Used in HMA/WMA	9.5	9.5	14.4	25.6
	Used in Aggregate	0.0	0.0	0.0	1.3
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.26%		
	Average % for Other Agency Mixes	0.18%	0.32%		
	Average % for Commercial & Residential	0.61%	0.65%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.25%	0.38%		
	% Companies/Branches Reporting Using RAS	22%	60%		
WMA		% Total Production		Tons (Millions)	
	DOT	45%	33%	1.0	0.9
	Other Agency	60%	35%	1.0	0.9
	Commercial and Residential	57%	51%	1.1	0.8
	Total			3.1	2.6
	% of Market				
	Chemical Additive %	8%	53%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	92%	47%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	9%	20%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Massachusetts

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.0	2.6	6.1	6.5
	DOT	0.9	0.8	2.8	2.0
	Other Agency	0.4	0.9	1.1	2.1
	Commercial and Residential	0.7	1.0	2.2	2.4
	Companies/Branches Reporting	4	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.4	0.5	1.3	1.1
	Used in HMA/WMA	0.4	0.4	1.1	1.1
	Used in Aggregate	0.1	0.0	0.2	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	19.5%	16.3%		
	Average % for Other Agency Mixes	20.5%	17.7%		
	Average % for Commercial & Residential	19.5%	17.1%		
	State Average All Mixes Based on % Reported for Different Sectors	19.7%	17.1%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	18.1%	16.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	8.6	0.0	21.3
	Used in HMA/WMA	3.0	3.7	9.1	9.2
	Used in Aggregate	0.0	0.0	82.4	39.7
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.12%	0.12%		
	Average % for Other Agency Mixes	0.14%	0.18%		
	Average % for Commercial & Residential	0.19%	0.12%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.15%	0.14%		
	% Companies/Branches Reporting Using RAS	50%	50%		
WMA		% Total Production		Tons (Millions)	
	DOT	38%	50%	1.1	1.0
	Other Agency	0%	2%	0.0	0.1
	Commercial and Residential	11%	3%	0.2	0.1
	Total			1.3	1.1
	% of Market				
	Chemical Additive %	39%	50%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	23%	8%		
	Organic Additive %	38%	43%		
	% Companies/Branches Reporting Using WMA	25%	25%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Michigan

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	5.4	7.4	10.3	11.3
	DOT	1.8	2.3	3.5	3.5
	Other Agency	1.3	1.8	2.5	2.8
	Commercial and Residential	2.2	3.2	4.2	5.0
	Companies/Branches Reporting	5	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.5	2.7	2.9	4.1
	Used in HMA/WMA	1.7	2.4	3.3	3.6
	Used in Aggregate	0.0	0.1	0.0	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	22.8%	21.1%		
	Average % for Other Agency Mixes	28.8%	24.3%		
	Average % for Commercial & Residential	32.2%	32.0%		
	State Average All Mixes Based on % Reported for Different Sectors	28.1%	26.7%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	31.7%	32.1%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	12.0	0.0	23.0	0.0
	Used in HMA/WMA	12.0	10.0	23.0	15.3
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.33%	0.00%		
	Average % for Other Agency Mixes	0.22%	0.00%		
	Average % for Commercial & Residential	0.13%	0.31%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.22%	0.14%		
	% Companies/Branches Reporting Using RAS	20%	17%		
WMA		% Total Production		Tons (Millions)	
	DOT	8%	19%	0.3	0.7
	Other Agency	12%	21%	0.3	0.6
	Commercial and Residential	9%	7%	0.4	0.3
	Total			1.0	1.6
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	12%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Minnesota

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	7.0	5.5	13.5	13.0
	DOT	2.3	1.3	4.4	2.9
	Other Agency	3.0	2.8	5.8	6.6
	Commercial and Residential	1.7	1.5	3.2	3.4
	Companies/Branches Reporting	10	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.9	1.4	3.6	3.4
	Used in HMA/WMA	1.5	1.3	2.8	3.1
	Used in Aggregate	0.2	0.0	0.4	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	20.6%	22.6%		
	Average % for Other Agency Mixes	21.3%	21.7%		
	Average % for Commercial & Residential	21.1%	21.6%		
	State Average All Mixes Based on % Reported for Different Sectors	21.0%	21.9%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	21.0%	23.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	26.0	3.0	50.0	7.1
	Used in HMA/WMA	25.0	13.1	48.1	30.6
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.32%	0.03%		
	Average % for Other Agency Mixes	0.38%	0.40%		
	Average % for Commercial & Residential	0.36%	0.10%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.36%	0.24%		
	% Companies/Branches Reporting Using RAS	50%	43%		
WMA		% Total Production		Tons (Millions)	
	DOT	26%	56%	1.2	1.7
	Other Agency	42%	67%	2.5	4.4
	Commercial and Residential	47%	69%	1.5	2.4
	Total			5.1	8.4
	% of Market				
	Chemical Additive %	0%	2%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	98%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	7%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Mississippi

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.3	2.4	4.0	3.5
	DOT	1.4	1.4	2.5	2.1
	Other Agency	0.6	0.5	1.0	0.8
	Commercial and Residential	0.3	0.4	0.5	0.6
	Companies/Branches Reporting	5	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.6	0.4	1.0	0.5
	Used in HMA/WMA	0.4	0.4	0.7	0.6
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	19.1%	16.1%		
	Average % for Other Agency Mixes	20.4%	17.0%		
	Average % for Commercial & Residential	19.9%	21.0%		
	State Average All Mixes Based on % Reported for Different Sectors	19.5%	17.2%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	18.0%	16.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	4.0	1.5	7.0	2.2
	Used in HMA/WMA	1.1	0.1	1.9	0.1
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.14%	0.00%		
	Average % for Commercial & Residential	0.10%	0.02%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.05%	0.00%		
	% Companies/Branches Reporting Using RAS	20%	20%		
WMA		% Total Production		Tons (Millions)	
	DOT	80%	90%	2.0	1.9
	Other Agency	45%	90%	0.5	0.7
	Commercial and Residential	34%	57%	0.2	0.4
	Total			2.6	2.9
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	20%	20%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Missouri

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.3	1.9	6.2	6.1
	DOT	1.1	1.1	2.8	3.6
	Other Agency	0.6	0.1	1.7	0.4
	Commercial and Residential	0.6	0.6	1.7	2.1
	Companies/Branches Reporting	3	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	0.5	0.9	1.7
	Used in HMA/WMA	0.5	0.4	1.2	1.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	17.4%	23.7%		
	Average % for Other Agency Mixes	28.0%	23.4%		
	Average % for Commercial & Residential	28.5%	21.2%		
	State Average All Mixes Based on % Reported for Different Sectors	23.3%	22.8%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	19.8%	20.2%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	56.3	48.8	148.6	157.5
	Used in HMA/WMA	73.0	25.2	193.0	81.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	2.33%	1.33%		
	Average % for Other Agency Mixes	2.47%	1.47%		
	Average % for Commercial & Residential	5.07%	1.31%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	3.11%	1.33%		
	% Companies/Branches Reporting Using RAS	100%	100%		
WMA		% Total Production		Tons (Millions)	
	DOT	72%	11%	2.0	0.4
	Other Agency	16%	15%	0.3	0.1
	Commercial and Residential	18%	32%	0.3	0.7
	Total			2.6	1.1
	% of Market				
	Chemical Additive %	3%	10%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	97%	90%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	33%	19%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Montana

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	0.5	*	4.2	4.2
	DOT	0.3	*	2.1	*
	Other Agency	0.1	*	0.7	*
	Commercial and Residential	0.2	*	1.3	*
	Companies/Branches Reporting	3	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.0	*	0.4	*
	Used in HMA/WMA	0.1	*	0.5	*
	Used in Aggregate	0.0	*	0.1	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.1	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	14.5%	*		
	Average % for Other Agency Mixes	6.9%	*		
	Average % for Commercial & Residential	27.3%	*		
	State Average All Mixes Based on % Reported for Different Sectors	17.3%	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	11.0%	*		
	% Companies/Branches Reporting Using RAP	100%	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	*	0.0	*
	Used in HMA/WMA	0.0	*	0.0	*
	Used in Aggregate	0.0	*	0.0	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	0.00%	*		
	Average % for Other Agency Mixes	0.00%	*		
	Average % for Commercial & Residential	0.00%	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	*		
	% Companies/Branches Reporting Using RAS	0%	*		
WMA		% Total Production		Tons (Millions)	
	DOT	39%	*	0.8	*
	Other Agency	39%	*	0.3	*
	Commercial and Residential	78%	*	1.1	*
	Total			2.2	*
		% of Market			
	Chemical Additive %	0%	*		
	Additive Foaming %	0%	*		
	Plant Foaming %	100%	*		
	Organic Additive %	0%	*		
	% Companies/Branches Reporting Using WMA	33%	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Nebraska

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.0	0.8	3.1	3.2
	DOT	0.6	0.4	1.9	1.7
	Other Agency	0.3	0.2	0.8	0.6
	Commercial and Residential	0.1	0.2	0.3	0.8
	Companies/Branches Reporting	3	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	0.3	1.0	1.3
	Used in HMA/WMA	0.3	0.3	0.9	1.0
	Used in Aggregate	0.1	0.0	0.2	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	28.5%	35.6%		
	Average % for Other Agency Mixes	24.0%	24.7%		
	Average % for Commercial & Residential	16.4%	15.5%		
	State Average All Mixes Based on % Reported for Different Sectors	25.9%	28.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	28.8%	32.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.4	0.0	1.2	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.04%	0.00%		
	Average % for Other Agency Mixes	0.06%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.04%	0.00%		
	% Companies/Branches Reporting Using RAS	33%	33%		
WMA		% Total Production		Tons (Millions)	
	DOT	52%	79%	1.0	1.4
	Other Agency	10%	52%	0.1	0.3
	Commercial and Residential	5%	11%	0.0	0.1
	Total			1.1	1.8
	% of Market				
	Chemical Additive %	5%	16%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	95%	84%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	22%	22%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Nevada

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	0.4	0.5	3.8	3.7
	DOT	0.1	0.2	1.1	1.4
	Other Agency	0.0	0.1	0.4	0.5
	Commercial and Residential	0.3	0.3	2.3	1.8
	Companies/Branches Reporting	3	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.0	0.1	0.3	0.5
	Used in HMA/WMA	0.1	0.1	0.5	0.6
	Used in Aggregate	0.0	0.1	0.0	0.5
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	14.8%	20.6%		
	Average % for Other Agency Mixes	17.1%	13.7%		
	Average % for Commercial & Residential	15.3%	23.2%		
	State Average All Mixes Based on % Reported for Different Sectors	15.4%	20.9%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	13.6%	17.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.0	0.0	0.0	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	0%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	0%	0%	0.0	0.0
	Other Agency	0%	0%	0.0	0.0
	Commercial and Residential	1%	0%	0.0	0.0
	Total			0.0	0.0
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	22%	11%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

New Hampshire

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.5	1.6	1.9	1.9
	DOT	0.3	0.4	0.4	0.5
	Other Agency	0.3	0.4	0.4	0.5
	Commercial and Residential	0.8	0.8	1.1	1.0
	Companies/Branches Reporting	4	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.1	0.2	0.2	0.3
	Used in HMA/WMA	0.3	0.4	0.4	0.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	19.0%	22.3%		
	Average % for Other Agency Mixes	18.6%	22.9%		
	Average % for Commercial & Residential	18.7%	24.5%		
	State Average All Mixes Based on % Reported for Different Sectors	18.8%	23.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	18.9%	22.4%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	3.6	5.1	4.7	6.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.30%	0.00%		
	Average % for Other Agency Mixes	0.23%	0.39%		
	Average % for Commercial & Residential	0.23%	0.46%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.24%	0.32%		
	% Companies/Branches Reporting Using RAS	75%	50%		
WMA		% Total Production		Tons (Millions)	
	DOT	10%	54%	0.0	0.3
	Other Agency	17%	26%	0.1	0.1
	Commercial and Residential	18%	32%	0.2	0.3
	Total			0.3	0.7
	% of Market				
	Chemical Additive %	3%	20%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	97%	200%		
	Organic Additive %	0%	10%		
	% Companies/Branches Reporting Using WMA	6%	6%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

New Jersey

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	3.4	3.3	8.8	5.0
	DOT	0.7	0.9	1.7	1.3
	Other Agency	1.9	1.8	4.9	2.7
	Commercial and Residential	0.8	0.7	2.2	1.0
	Companies/Branches Reporting	4	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.2	1.3	3.0	2.0
	Used in HMA/WMA	0.6	0.6	1.6	0.9
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.1	0.0	0.1
	Average % Used in Mixes				
	Average % for DOT Mixes	15.0%	15.1%		
	Average % for Other Agency Mixes	17.1%	17.5%		
	Average % for Commercial & Residential	24.0%	25.0%		
	State Average All Mixes Based on % Reported for Different Sectors	18.4%	18.4%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	18.6%	18.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.1	0.0	0.2	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.01%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	25%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	0%	1%	0.0	0.0
	Other Agency	52%	10%	2.5	0.3
	Commercial and Residential	14%	10%	0.3	0.1
	Total			2.9	0.4
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	13%	11%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

New Mexico

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	3.8	3.8
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

New York

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	5.9	5.1	16.0	16.3
	DOT	2.0	1.5	5.4	4.9
	Other Agency	1.8	1.3	4.8	4.1
	Commercial and Residential	2.2	2.3	5.8	7.3
	Companies/Branches Reporting	14	9		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.9	0.6	2.4	1.8
	Used in HMA/WMA	0.8	0.7	2.1	2.2
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	13.7%	16.9%		
	Average % for Other Agency Mixes	16.2%	17.9%		
	Average % for Commercial & Residential	17.6%	16.4%		
	State Average All Mixes Based on % Reported for Different Sectors	15.9%	17.0%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	13.4%	13.7%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	1.8	0.1	4.9	0.3
	Used in HMA/WMA	1.8	0.1	4.9	0.3
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.08%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.03%	0.00%		
	% Companies/Branches Reporting Using RAS	21%	11%		
WMA		% Total Production		Tons (Millions)	
	DOT	24%	21%	1.3	1.0
	Other Agency	20%	8%	1.0	0.3
	Commercial and Residential	12%	14%	0.7	1.0
	Total			3.0	2.4
	% of Market				
	Chemical Additive %	4%	10%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	96%	90%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	4%	9%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

North Carolina

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.8	4.2	12.0	12.0
	DOT	1.7	2.6	7.3	7.5
	Other Agency	0.3	0.3	1.1	1.0
	Commercial and Residential	0.8	1.2	3.6	3.5
	Companies/Branches Reporting	6	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.6	1.0	2.4	2.8
	Used in HMA/WMA	0.7	1.1	3.0	3.1
	Used in Aggregate	0.0	0.5	0.0	1.5
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.1	0.0	0.3
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	26.4%	26.3%		
	Average % for Other Agency Mixes	21.1%	17.5%		
	Average % for Commercial & Residential	26.8%	27.7%		
	State Average All Mixes Based on % Reported for Different Sectors	26.1%	26.0%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	25.2%	25.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	12.0	20.0	50.5	56.8
	Used in HMA/WMA	4.4	11.6	18.4	32.9
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.25%	0.34%		
	Average % for Other Agency Mixes	0.00%	0.28%		
	Average % for Commercial & Residential	0.00%	0.13%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.15%	0.27%		
	% Companies/Branches Reporting Using RAS	33%	57%		
WMA		% Total Production		Tons (Millions)	
	DOT	6%	6%	0.4	0.4
	Other Agency	8%	8%	0.1	0.1
	Commercial and Residential	14%	10%	0.5	0.4
	Total			1.0	0.9
	% of Market				
	Chemical Additive %	17%	16%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	83%	60%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	14%	10%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

North Dakota

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	5.0	5.0
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Ohio

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	10.5	13.5	14.6	14.8
	DOT	5.8	6.1	8.1	6.7
	Other Agency	3.6	3.8	5.1	4.1
	Commercial and Residential	1.0	3.7	1.4	4.0
	Companies/Branches Reporting	6	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	3.2	3.4	4.4	3.7
	Used in HMA/WMA	2.9	3.8	4.1	4.1
	Used in Aggregate	0.1	0.1	0.2	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.1	0.0	0.1	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	24.9%	27.5%		
	Average % for Other Agency Mixes	27.2%	25.0%		
	Average % for Commercial & Residential	30.5%	29.9%		
	State Average All Mixes Based on % Reported for Different Sectors	26.3%	27.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	27.9%	28.0%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	27.0	9.5	37.6	10.4
	Used in HMA/WMA	22.6	26.3	31.5	28.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.23%	0.00%		
	Average % for Other Agency Mixes	0.23%	0.28%		
	Average % for Commercial & Residential	0.09%	0.43%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.22%	0.19%		
	% Companies/Branches Reporting Using RAS	33%	43%		
WMA		% Total Production		Tons (Millions)	
	DOT	78%	70%	6.3	4.7
	Other Agency	74%	64%	3.7	2.6
	Commercial and Residential	81%	66%	1.2	2.7
	Total			11.2	9.9
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	17%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Oklahoma

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.7	2.2	5.5	4.6
	DOT	1.1	1.2	3.6	2.4
	Other Agency	0.3	0.6	0.9	1.3
	Commercial and Residential	0.3	0.4	1.0	0.9
	Companies/Branches Reporting	6	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	0.5	1.1	1.0
	Used in HMA/WMA	0.2	0.4	0.7	0.8
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	19.1%	19.2%		
	Average % for Other Agency Mixes	22.2%	14.8%		
	Average % for Commercial & Residential	23.9%	22.0%		
	State Average All Mixes Based on % Reported for Different Sectors	20.5%	18.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	12.8%	16.5%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	50.0	28.5	162.2	59.5
	Used in HMA/WMA	14.0	25.0	45.4	52.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	1.96%	2.19%		
	Average % for Commercial & Residential	2.67%	2.63%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.82%	1.13%		
	% Companies/Branches Reporting Using RAS	33%	33%		
WMA		% Total Production		Tons (Millions)	
	DOT	45%	47%	1.6	1.1
	Other Agency	44%	62%	0.4	0.8
	Commercial and Residential	76%	87%	0.8	0.8
	Total			2.8	2.7
	% of Market				
	Chemical Additive %	15%	1%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	85%	99%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	17%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Oregon

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	0.4	1.5	4.8	4.9
	DOT	0.1	0.5	1.7	1.6
	Other Agency	0.1	0.4	1.7	1.3
	Commercial and Residential	0.1	0.6	1.3	1.9
	Companies/Branches Reporting	3	5		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.0	0.3	0.6	1.1
	Used in HMA/WMA	0.1	0.4	1.2	1.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	24.2%	25.5%		
	Average % for Other Agency Mixes	23.4%	23.7%		
	Average % for Commercial & Residential	30.0%	28.2%		
	State Average All Mixes Based on % Reported for Different Sectors	25.6%	26.1%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	25.5%	28.0%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	15.0	0.0	50.4
	Used in HMA/WMA	1.5	18.8	19.4	63.3
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.48%	0.00%		
	Average % for Other Agency Mixes	0.29%	0.63%		
	Average % for Commercial & Residential	0.47%	2.84%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.41%	1.29%		
	% Companies/Branches Reporting Using RAS	33%	40%		
WMA		% Total Production		Tons (Millions)	
	DOT	1%	11%	0.0	0.2
	Other Agency	39%	33%	0.7	0.4
	Commercial and Residential	5%	4%	0.1	0.1
	Total			0.7	0.7
	% of Market				
	Chemical Additive %	0%	9%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	91%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	33%	16%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Pennsylvania

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	6.7	3.2	14.9	17.7
	DOT	3.5	1.7	7.8	9.5
	Other Agency	1.7	0.3	3.8	1.8
	Commercial and Residential	1.5	1.2	3.3	6.4
	Companies/Branches Reporting	14	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.3	0.6	2.8	3.1
	Used in HMA/WMA	1.0	0.5	2.3	2.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
		Average % Used in Mixes			
	Average % for DOT Mixes	16.5%	16.9%		
	Average % for Other Agency Mixes	12.5%	18.1%		
	Average % for Commercial & Residential	20.0%	16.8%		
	State Average All Mixes Based on % Reported for Different Sectors	16.3%	17.0%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	15.4%	15.9%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	73.0	38.0	163.2	208.4
	Used in HMA/WMA	56.9	59.0	127.2	323.6
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
		Average % Used in Mixes			
	Average % for DOT Mixes	0.94%	0.87%		
	Average % for Other Agency Mixes	0.86%	0.74%		
	Average % for Commercial & Residential	0.65%	3.55%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.85%	1.83%		
	% Companies/Branches Reporting Using RAS	21%	33%		
WMA		% Total Production		Tons (Millions)	
	DOT	30%	56%	2.3	5.3
	Other Agency	16%	15%	0.6	0.3
	Commercial and Residential	14%	13%	0.5	0.9
	Total			3.4	6.5
		% of Market			
	Chemical Additive %	14%	38%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	86%	62%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	7%	17%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Puerto Rico

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	NCR	1.6	1.6
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial and Residential	*	NCR	*	NCR
	Companies/Branches Reporting	*	NCR		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	NCR	*	NCR
	Used in HMA/WMA	*	NCR	*	NCR
	Used in Aggregate	*	NCR	*	NCR
	Used in Cold Mix	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
		Average % Used in Mixes			
	Average % for DOT Mixes	*	NCR		
	Average % for Other Agency Mixes	*	NCR		
	Average % for Commercial & Residential	*	NCR		
	State Average All Mixes Based on % Reported for Different Sectors	*	NCR		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	NCR		
	% Companies/Branches Reporting Using RAP	*	NCR		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	NCR	*	NCR
	Used in HMA/WMA	*	NCR	*	NCR
	Used in Aggregate	*	NCR	*	NCR
	Used in Cold Mix	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
		Average % Used in Mixes			
	Average % for DOT Mixes	*	NCR		
	Average % for Other Agency Mixes	*	NCR		
	Average % for Commercial & Residential	*	NCR		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	NCR		
	% Companies/Branches Reporting Using RAS	*	NCR		
WMA		% Total Production		Tons (Millions)	
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial and Residential	*	NCR	*	NCR
	Total			*	NCR
		% of Market			
	Chemical Additive %	*	NCR		
	Additive Foaming %	*	NCR		
	Plant Foaming %	*	NCR		
	Organic Additive %	*	NCR		
	% Companies/Branches Reporting Using WMA	*	NCR		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Rhode Island

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	2.5	2.4
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

South Carolina

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	0.7	2.0	5.4	4.9
	DOT	0.4	1.3	3.6	3.3
	Other Agency	0.1	0.2	1.2	0.5
	Commercial and Residential	0.1	0.4	0.6	1.1
	Companies/Branches Reporting	3	6		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.1	0.3	1.1	0.8
	Used in HMA/WMA	0.2	0.4	1.3	1.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	19.7%	22.6%		
	Average % for Other Agency Mixes	21.8%	21.5%		
	Average % for Commercial & Residential	29.0%	25.0%		
	State Average All Mixes Based on % Reported for Different Sectors	21.1%	23.0%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	23.4%	21.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	2.0	2.0	16.2	5.0
	Used in HMA/WMA	2.0	1.1	16.2	2.7
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.45%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.20%		
	Average % for Commercial & Residential	0.00%	0.16%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.30%	0.06%		
	% Companies/Branches Reporting Using RAS	33%	17%		
WMA		% Total Production		Tons (Millions)	
	DOT	2%	5%	0.1	0.2
	Other Agency	0%	0%	0.0	0.0
	Commercial and Residential	0%	0%	0.0	0.0
	Total			0.1	0.2
	% of Market				
	Chemical Additive %	100%	92%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	0%	8%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	11%	14%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

South Dakota

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	2.1	2.1
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Tennessee

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	3.8	4.4	7.7	7.4
	DOT	2.2	2.4	4.5	4.0
	Other Agency	0.7	0.8	1.4	1.4
	Commercial and Residential	0.9	1.2	1.8	2.0
	Companies/Branches Reporting	6	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.0	0.7	1.9	1.2
	Used in HMA/WMA	0.7	0.6	1.3	1.0
	Used in Aggregate	0.0	0.0	0.1	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	16.1%	17.9%		
	Average % for Other Agency Mixes	19.7%	16.9%		
	Average % for Commercial & Residential	20.4%	24.6%		
	State Average All Mixes Based on % Reported for Different Sectors	17.8%	19.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	17.4%	14.0%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	5.0	40.5	10.0	67.2
	Used in HMA/WMA	13.2	39.1	26.3	64.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.13%	1.03%		
	Average % for Other Agency Mixes	0.45%	0.57%		
	Average % for Commercial & Residential	0.79%	0.80%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.34%	0.88%		
	% Companies/Branches Reporting Using RAS	50%	43%		
WMA		% Total Production		Tons (Millions)	
	DOT	18%	17%	0.8	0.7
	Other Agency	11%	13%	0.1	0.2
	Commercial and Residential	1%	37%	0.0	0.7
	Total			1.0	1.6
	% of Market				
	Chemical Additive %	14%	10%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	86%	90%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	14%	10%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Texas

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	7.1	9.7	17.0	18.0
	DOT	4.1	5.9	9.7	10.9
	Other Agency	2.0	2.5	4.8	4.5
	Commercial and Residential	1.0	1.4	2.5	2.5
	Companies/Branches Reporting	8	11		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.8	1.3	1.9	2.4
	Used in HMA/WMA	1.0	1.5	2.4	2.8
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	26.6%	15.3%		
	Average % for Other Agency Mixes	13.9%	15.5%		
	Average % for Commercial & Residential	11.5%	17.0%		
	State Average All Mixes Based on % Reported for Different Sectors	20.7%	15.6%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	14.1%	15.3%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	129.0	153.2	307.8	283.1
	Used in HMA/WMA	142.9	167.2	341.1	309.0
	Used in Aggregate	0.0	0.0	0.0	2.2
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	2.0	0.0	4.8	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	1.85%	1.75%		
	Average % for Other Agency Mixes	2.05%	1.74%		
	Average % for Commercial & Residential	2.52%	1.54%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	2.01%	1.72%		
	% Companies/Branches Reporting Using RAS	75%	64%		
WMA		% Total Production		Tons (Millions)	
	DOT	40%	38%	3.9	4.1
	Other Agency	36%	13%	1.7	0.6
	Commercial and Residential	26%	12%	0.7	0.3
	Total			6.3	5.0
	% of Market				
	Chemical Additive %	57%	69%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	43%	31%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	11%	8%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Utah

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.6	2.9	3.4	3.4
	DOT	0.9	0.9	1.1	1.1
	Other Agency	0.9	0.5	1.1	0.6
	Commercial and Residential	0.9	1.5	1.1	1.7
	Companies/Branches Reporting	8	8		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.6	0.7	0.8	0.9
	Used in HMA/WMA	0.6	0.8	0.8	1.0
	Used in Aggregate	0.0	0.1	0.0	0.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	23.4%	22.3%		
	Average % for Other Agency Mixes	19.8%	20.3%		
	Average % for Commercial & Residential	25.8%	33.4%		
	State Average All Mixes Based on % Reported for Different Sectors	23.0%	27.5%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	24.4%	27.9%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.0	0.0	0.0	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	0%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	54%	71%	0.6	0.8
	Other Agency	72%	55%	0.8	0.3
	Commercial and Residential	48%	34%	0.5	0.6
	Total			2.0	1.7
	% of Market				
	Chemical Additive %	0%	5%		
	Additive Foaming %	17%	0%		
	Plant Foaming %	83%	95%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	13%	9%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Vermont

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	2.3	2.3
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Virginia

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	4.9	5.2	10.0	9.8
	DOT	2.1	2.3	4.3	4.4
	Other Agency	0.9	1.1	1.7	2.1
	Commercial and Residential	2.0	1.8	4.0	3.3
	Companies/Branches Reporting	8	7		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.8	1.2	3.7	2.3
	Used in HMA/WMA	1.3	1.4	2.7	2.6
	Used in Aggregate	0.0	0.6	0.1	1.1
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.1	0.0	0.2	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	25.4%	25.4%		
	Average % for Other Agency Mixes	27.5%	27.9%		
	Average % for Commercial & Residential	29.8%	29.2%		
	State Average All Mixes Based on % Reported for Different Sectors	27.6%	27.2%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	26.8%	26.8%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	11.1	0.8	22.5	1.4
	Used in HMA/WMA	31.1	10.9	63.2	20.3
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.47%	0.36%		
	Average % for Other Agency Mixes	1.57%	0.07%		
	Average % for Commercial & Residential	0.40%	0.09%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.63%	0.21%		
	% Companies/Branches Reporting Using RAS	50%	29%		
WMA		% Total Production		Tons (Millions)	
	DOT	64%	79%	2.7	3.5
	Other Agency	74%	87%	1.3	1.9
	Commercial and Residential	74%	80%	2.9	2.6
	Total			7.0	7.9
	% of Market				
	Chemical Additive %	11%	9%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	86%	91%		
	Organic Additive %	3%	0%		
	% Companies/Branches Reporting Using WMA	11%	12%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Washington

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	2.8	2.6	4.3	4.9
	DOT	0.5	0.7	0.8	1.4
	Other Agency	1.2	1.1	1.8	2.1
	Commercial and Residential	1.1	0.7	1.7	1.4
	Companies/Branches Reporting	4	4		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.5	0.6	0.8	1.1
	Used in HMA/WMA	0.5	0.7	0.8	1.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
		Average % Used in Mixes			
	Average % for DOT Mixes	19.9%	25.7%		
	Average % for Other Agency Mixes	19.9%	25.4%		
	Average % for Commercial & Residential	24.7%	27.2%		
	State Average All Mixes Based on % Reported for Different Sectors	21.8%	26.0%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	18.5%	25.5%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	4.5	7.1	7.0	13.4
	Used in HMA/WMA	9.6	7.5	14.9	14.2
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
		Average % Used in Mixes			
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.52%	0.04%		
	Average % for Commercial & Residential	0.31%	0.95%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.35%	0.29%		
	% Companies/Branches Reporting Using RAS	50%	50%		
WMA		% Total Production		Tons (Millions)	
	DOT	4%	12%	0.0	0.2
	Other Agency	4%	10%	0.1	0.2
	Commercial and Residential	9%	21%	0.2	0.3
	Total			0.3	0.7
		% of Market			
	Chemical Additive %	0%	13%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	87%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	25%	25%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

West Virginia

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	1.5	1.5	3.0	2.6
	DOT	1.1	1.1	2.2	1.8
	Other Agency	0.0	0.1	0.0	0.1
	Commercial and Residential	0.4	0.4	0.8	0.6
	Companies/Branches Reporting	3	3		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	0.3	0.4	0.5	0.7
	Used in HMA/WMA	0.2	0.2	0.4	0.4
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	15.0%	12.4%		
	Average % for Other Agency Mixes	15.0%	9.7%		
	Average % for Commercial & Residential	15.6%	14.5%		
	State Average All Mixes Based on % Reported for Different Sectors	15.1%	12.7%		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	12.1%	15.0%		
	% Companies/Branches Reporting Using RAP	100%	100%		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA	0.0	0.0	0.0	0.0
	Used in Aggregate	0.0	0.0	0.0	0.0
	Used in Cold Mix	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Average % Used in Mixes				
	Average % for DOT Mixes	0.00%	0.00%		
	Average % for Other Agency Mixes	0.00%	0.00%		
	Average % for Commercial & Residential	0.00%	0.00%		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.00%	0.00%		
	% Companies/Branches Reporting Using RAS	0%	0%		
WMA		% Total Production		Tons (Millions)	
	DOT	2%	1%	0.0	0.0
	Other Agency	0%	1%	0.0	0.0
	Commercial and Residential	1%	1%	0.0	0.0
	Total			0.0	0.0
	% of Market				
	Chemical Additive %	0%	0%		
	Additive Foaming %	0%	0%		
	Plant Foaming %	100%	100%		
	Organic Additive %	0%	0%		
	% Companies/Branches Reporting Using WMA	33%	22%		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	7.6	*	12.0	13.0
	DOT	3.7	*	5.9	*
	Other Agency	1.8	*	2.8	*
	Commercial and Residential	2.1	*	3.3	*
	Companies/Branches Reporting	3	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	1.2	*	1.9	*
	Used in HMA/WMA	1.1	*	1.8	*
	Used in Aggregate	0.0	*	0.0	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	17.0%	*		
	Average % for Other Agency Mixes	17.1%	*		
	Average % for Commercial & Residential	21.1%	*		
	State Average All Mixes Based on % Reported for Different Sectors	18.2%	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	15.0%	*		
	% Companies/Branches Reporting Using RAP	100%	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	63.4	*	100.2	*
	Used in HMA/WMA	52.6	*	83.2	*
	Used in Aggregate	0.0	*	0.0	*
	Used in Cold Mix	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
		Average % Used in Mixes			
	Average % for DOT Mixes	0.76%	*		
	Average % for Other Agency Mixes	0.60%	*		
	Average % for Commercial & Residential	0.67%	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	0.69%	*		
	% Companies/Branches Reporting Using RAS	100%	*		
WMA		% Total Production		Tons (Millions)	
	DOT	7%	*	0.4	*
	Other Agency	11%	*	0.3	*
	Commercial and Residential	10%	*	0.3	*
	Total			1.1	*
		% of Market			
	Chemical Additive %	87%	*		
	Additive Foaming %	0%	*		
	Plant Foaming %	13%	*		
	Organic Additive %	0%	*		
	% Companies/Branches Reporting Using WMA	33%	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting

Wyoming

		Reported Values		Total Estimated Value	
		2013	2014	2013	2014
Tons of HMA/WMA Produced		Tons (Millions)		Tons (Millions)	
	Total	*	*	2.8	2.8
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Companies/Branches Reporting	*	*		
RAP		Tons (Millions)		Tons (Millions)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on % Reported for Different Sectors	*	*		
	State Average All Mixes Based on RAP Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAP	*	*		
RAS		Tons (Thousands)		Tons (Thousands)	
	Accepted	*	*	*	*
	Used in HMA/WMA	*	*	*	*
	Used in Aggregate	*	*	*	*
	Used in Cold Mix	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
		Average % Used in Mixes			
	Average % for DOT Mixes	*	*		
	Average % for Other Agency Mixes	*	*		
	Average % for Commercial & Residential	*	*		
	State Average All Mixes Based on RAS Tons Used in HMA/WMA	*	*		
	% Companies/Branches Reporting Using RAS	*	*		
WMA		% Total Production		Tons (Millions)	
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial and Residential	*	*	*	*
	Total			*	*
		% of Market			
	Chemical Additive %	*	*		
	Additive Foaming %	*	*		
	Plant Foaming %	*	*		
	Organic Additive %	*	*		
	% Companies/Branches Reporting Using WMA	*	*		

NCR = No Companies Reporting

* = Fewer than 3 contractors reporting