

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2020

Information Series 138



11th Annual Survey

This document is disseminated under the sponsorship of the U.S. Department of Transportation, Federal Highway Administration, in the interest of information exchange. The United States Government assumes no liability for its contents or the use of the information contained in this document.

The contents of this report reflect the views of the contractor, who is responsible for the accuracy of the data presented herein. The contents do not necessarily reflect the official policy of the U.S. Department of Transportation.

This report does not constitute a standard, specification, or regulation.

The United States Government does not endorse products or manufacturers. Trade or manufacturer's names may appear only because they are considered essential to the object of this document.



NAPA Building • 6406 Ivy Lane, Suite 350 • Greenbelt, MD 20770-1441
Tel: 301-731-4748 • Fax: 301-731-4621
Toll free: 1-888-468-6499 • www.AsphaltPavement.org
Publication Sales: napa-orders@abdintl.com • Toll free: 888-600-4474
Tel: 412-741-6314 • Fax: 412-741-0609

11th Annual Asphalt Pavement Industry Survey
IS 138
Produced December 2021

Technical Report Documentation Page

1. Report No. Information Series 138 (11th edition)		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020				5. Report Date December 2021	
				6. Performing Organization Code	
7. Author(s) Brett A. Williams, J. Richard Willis, Ph.D., & Joseph Shacat				8. Performing Organization Report No. IS 138(11e)	
9. Performing Organization Name and Address National Asphalt Pavement Association 6406 Ivy Lane, Suite 350 Greenbelt, MD 20770-1441				10. Work Unit No. (TRAIS)	
				11. Contract or Grant No. HIF180121PR	
12. Sponsoring Organization Name and Address Federal Highway Administration Office of Preconstruction, Construction, and Pavements 1200 New Jersey Ave. SE Washington, DC 20590				13. Type of Report and Period Covered Final Report; January–December 2020	
				14. Sponsoring Agency Code FHWA-HICP-40	
15. Supplementary Notes FHWA Agreement Officer's Representative: Timothy B. Aschenbrener, P.E.					
16. Abstract <p>A shared goal of the Federal Highway Administration (FHWA) and the National Asphalt Pavement Association (NAPA) is to support and promote sustainable practices, such as the use of recycled materials and warm-mix asphalt (WMA). The use of recycled materials, primarily reclaimed asphalt pavement (RAP) and reclaimed asphalt shingles (RAS), in asphalt pavements conserves raw materials and reduces overall asphalt mixture costs, as well as reduces the stream of material going into landfills.</p> <p>WMA technologies have been introduced to reduce production and compaction temperatures for asphalt mixtures, which reduces the energy needed and emissions associated with mixture production. Additional benefits include improved low-temperature compaction of asphalt mixtures leading to improved pavement performance, as well as a longer paving season. WMA was chosen for accelerated deployment in federal-aid highway, state department of transportation, and local road projects as part of FHWA's 2010 Every Day Counts initiative.</p> <p>The objective of this survey, first conducted for the 2009 and 2010 construction seasons, is to quantify recycled materials used and WMA produced annually by the asphalt pavement industry to document the deployment of these technologies to understand where they are being used and where they are underutilized. Results show significant growth in the use of RAP, RAS, and WMA technologies since 2009, although the rate of year-over-year growth has generally slowed since 2013.</p> <p>The asphalt industry remains the country's most diligent recycler with more than 99 percent of reclaimed asphalt pavement being put back to use. The average percentage of RAP used in asphalt mixtures has increased from 15.6 percent in 2009 to 21.3 percent in 2020. In 2020, the estimated RAP tonnage used in asphalt mixtures was 87.0 million tons. This represents 4.4 million tons (24 million barrels) of asphalt binder conserved, along with the replacement of more than 82 million tons of virgin aggregate. The use of RAS in asphalt pavement mixtures has decreased from 701,000 tons in 2009 to an estimated 586,000 tons in 2020 with the use of RAS decreasing (36.4 percent) from 2019 to 2020.</p> <p>The combined savings of asphalt binder and aggregate from using RAP and RAS in asphalt mixtures is estimated at more than \$3.0 billion and nearly 59 million cubic yards of landfill space.</p> <p>More than 900,000 tons of other recycled materials were reported as being incorporated into nearly 9.1 million tons of asphalt pavement mixtures during the 2020 construction season, including recycled tire rubber, blast furnace slag, steel slag, and cellulose fibers.</p> <p>The estimated total production of asphalt with WMA technologies during the 2020 construction season was 186.4 million tons of which about 50 percent was produced at reduced temperatures. This was a 13 percent increase from the estimated 164.5 million tons of WMA in 2019, with increased utilization reported for all sectors tonnage for the year. Utilization of WMA technologies in 2020 was 1010 percent more than the estimated 16.8 million tons in the 2009 construction season.</p> <p>Asphalt produced with WMA technology made up 45.7 percent of the total estimated asphalt mixture market in 2020. Production plant foaming, representing 49 percent of the market, is the most commonly used warm-mix technology; chemical additive technologies accounted for a little more than 46 percent of the market. Differences were seen in which WMA technologies were used when production temperatures were or were not reduced.</p>					
17. Key Words reclaimed asphalt pavement, reclaimed asphalt shingles, warm-mix asphalt, recycled tire rubber, ground tire rubber, slag, fly ash, RAP, RAS, WMA, GTR, RTR, recycled materials, economics, engineering				18. Distribution Statement No restrictions.	
19. Security Classification (of this report) Unclassified.		20. Security Classification (of this page) Unclassified.		21. No. of Pages 51	22. Price NA

Table of Contents

Table of Contents.....	4
List of Abbreviations	6
Executive Summary.....	7
Reclaimed Asphalt Pavement	7
Reclaimed Asphalt Shingles.....	8
Other Findings.....	8
Warm-Mix Asphalt Technologies	8
Background	9
Objective and Scope.....	10
Survey Methodology.....	10
Producer Survey Results	10
Data Summary and National Estimates	14
Total Asphalt Mixture Production.....	16
Reclaimed Asphalt Pavement	17
RAP Use by Sector	18
RAP Use in Each State	19
RAP Stockpiles.....	21
RAP Fractionation.....	22
RAP Recycling Agent Use.....	23
Reclaimed Asphalt Shingles	24
RAS Use by Sector	25
RAS Use in Each State.....	29
RAS Stockpiles	29
RAS Recycling Agent Use.....	30
The Importance of Engineering Recycled Asphalt Mixtures for Quality.....	31
Cost Savings from RAP and RAS	31
Warm-Mix Asphalt Technology.....	32
WMA Technology Use by Sector.....	33
WMA Technology Use in Each State	34
WMA Technologies	35
Use of WMA Technologies at Different Temperatures.....	36
Energy and Greenhouse Gas Emission Benefits from WMA and RAP	37
Energy and GHG Emission Benefits from Production of WMA at Reduced Temperature	37
GHG Emission Benefits from Use of RAP	37
Other Recycled Materials.....	39
Recycled Tire Rubber	39
Steel & Blast Furnace Slag.....	40
Recycled Fibers.....	42
Coal Combustion Products.....	43
Other Recycled Materials.....	44
In-place Recycling.....	45
In-Place Recycling Use by User Producer Group Region.....	45

Historical Trends 46

Summary and Conclusions 47

 Reclaimed Asphalt Pavement 47

 Reclaimed Asphalt Shingles 48

 Material Cost Savings 49

 Other Recycled Materials..... 49

 Warm Mix Asphalt 49

 Conclusions 50

References 50

Methodology & Survey Forms..... Appendix A

State-by-State Use of Recycled Materials and Warm-Mix Asphalt in Asphalt Pavement Mixtures Appendix B

Methodology for Calculating Energy and Greenhouse Gas Emission Benefits From Production of WMA and Use of RAP
..... Appendix C

Suggested Citation:

Williams, B.A., J.R. Willis, & Shacat, J. (2021). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020, 11th Annual Survey* (IS 138). National Asphalt Pavement Association, Greenbelt, Maryland.
DOI:10.13140/RG.2.2.14846.46409

List of Abbreviations

AASHTO	American Association of State Highway and Transportation Officials
CCP	Coal Combustion Product
CCPR	Cold Central Plant Recycling
CIR	Cold In-Place Recycling
CRM	Crumb Rubber Modifier
DOT	Department of Transportation
FDR	Full-Depth Reclamation
FHWA	Federal Highway Administration
GHG	Greenhouse Gas
GTR	Ground Tire Rubber
HIR	Hot In-Place Recycling
HMA	Hot-Mix Asphalt
MWAS	Manufacturing Waste Asphalt Shingles
NAPA	National Asphalt Pavement Association
NCAT	National Center for Asphalt Technology
NCAUPG	North Central Asphalt User/Producer Group
NEAUPG	North East Asphalt User/Producer Group
NSA	National Slag Association
OGFC	Open-Graded Friction Course
PCAS	Post-Consumer Asphalt Shingles
PCCAS	Pacific Coast Conference on Asphalt Specifications
RAP	Reclaimed Asphalt Pavement
RAS	Reclaimed Asphalt Shingles
RBR	Recycled Binder Ratio
RMA	Rubber Manufacturers Association
RMAUPG	Rocky Mountain Asphalt User/Producer Group
RTR	Recycled Tire Rubber
SAPA	State Asphalt Pavement Association
SEAUPG	Southeastern Asphalt User/Producer Group
UPG	User/Producer Group
WMA	Warm-Mix Asphalt

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020

Executive Summary

The results of the asphalt pavement industry survey for the 2020 construction season show that asphalt mixture producers have a strong record of employing sustainable practices and continue to increase their use of recycled materials and warm-mix asphalt (WMA). The use of recycled materials, particularly reclaimed asphalt pavement (RAP) and reclaimed asphalt shingles (RAS), conserves raw materials and reduces overall asphalt mixture costs, allowing road owners to achieve more roadway maintenance and construction activities within limited budgets. WMA technologies can improve compaction at reduced temperatures, ensuring pavement performance and long life; conserve energy; reduce emissions from production and paving operations; and improve conditions for workers.

The objective of this survey, first conducted for the 2009 and 2010 construction seasons, was to quantify the use of recycled materials, primarily RAP and RAS, as well as the use of WMA technologies by the asphalt pavement industry. For the 2020 construction season, the National Asphalt Pavement Association (NAPA) conducted a voluntary survey of asphalt mixture producers across the United States on tons produced, along with a survey of state asphalt pavement associations (SAPAs) regarding total tons of asphalt pavement mixture produced in their state.

Asphalt mixture producers from 50 states, and the District of Columbia completed the 2020 construction season survey. A total of 274 companies and 1,406 production plants were represented in the survey.

A degree of fluctuation in year-to-year comparisons of data is influenced by which companies responded to the 2020 construction season survey versus prior year survey respondents. Respondents to the 2020 construction season survey increased by 62 companies compared to 2019. Of the companies responding to the 2020 survey, 93 did not respond to the 2019 construction season survey.

The following are highlights of the survey of usage during the 2020 construction season:

Reclaimed Asphalt Pavement

- Asphalt mixture producers remain the country's most diligent recyclers, with more than 93 percent of asphalt mixture reclaimed from old asphalt pavements being put back to use in new pavements and the remaining 7 percent being used in other civil engineering applications, such as unbound aggregate bases.
- The total estimated tons of RAP used in asphalt mixtures was 87.0 million tons in 2020. This represents a 55.4 percent increase from the total estimated tons of RAP used in 2009. Since 2009, total asphalt mixture tonnage has increased only 13.8 percent.
- The percentage of producers reporting use of RAP was at 98.9 percent of respondents, up 1.2 percent from 2019. Three producers reported landfilling a minor amount (77,000 tons, or 0.016 percent) of RAP during 2020.
- RAP usage during the 2020 construction season is estimated to have reduced the need for 4.4 million tons (24 million barrels) of asphalt binder and more than 82 million tons of aggregate with a total estimated value of more than \$2.9 billion.
- The total estimated amount of RAP stockpiled nationwide at the end of the 2020 construction season was about 135 million tons.
- Fractionated RAP represents about 26 percent of RAP use nationwide, and the tons of RAP mixtures produced using softer binders are estimated at 23 percent while tons produced using recycling agents is estimated at 6 percent.

- Reclaiming 96 million tons of RAP for future use saved about 58.4 million cubic yards of landfill space, and more than \$5.1 billion in gate fees for disposal in landfills.
- The use of RAP in new asphalt mixtures reduced greenhouse gas emissions in 2020 by 2.3 million metric tons of CO_{2e}, which is equivalent to the annual emissions of 510,000 passenger vehicles

Reclaimed Asphalt Shingles

- The total estimated tons of RAS used in asphalt mixtures decreased 36 percent to an estimated 586,000 tons in 2020. This continues the decrease in the use of RAS reported during the 2019 construction season, with utilization at about 70 percent below the 2014 peak level of reported usage.
- The total estimated amount of RAS stockpiled nationwide at the end of the 2020 construction season was about 1.27 million tons, a 11.3 percent increase from 2019.
- RAS usage during the 2020 construction season is estimated to have reduced the need for 117,200 tons (more than 644,000 barrels) of asphalt binder and about 293,000 tons of aggregate with a total estimated value of more than \$59 million.
- Reclaiming 514,000 tons of unprocessed RAS for future use saved about 310,000 cubic yards of landfill space, and more than \$27 million in gate fees for disposal in landfills.

Other Findings

- The use of softer binders and recycling agents with mixtures incorporating RAP and RAS was reported nationwide. There was little correlation between the level of RAP and RAS used and the use of softer binders and/or recycling agents.
- Other recycled materials commonly reported as being used in asphalt mixtures during the 2020 construction season were recycled tire rubber, blast furnace slag, steel slag, cellulose fibers, and fly ash.
- More than 900,000 tons of other recycled materials was reported as being used in nearly 9.1 million tons of asphalt mixtures by 70 companies in 28 states during the 2020 construction season.

Warm-Mix Asphalt Technologies

- The estimated total tonnage of asphalt pavement mixtures produced with WMA technologies for the 2020 construction season was 186.4 million tons. This was a 13 percent increase from the estimated 164.5 million tons of WMA in 2019, driven by increased WMA tonnage in all sectors.
- Mixtures produced with WMA technologies made up 45.7 percent of the total estimated asphalt mixture market in 2020. About 49.9 percent (93.1 million tons) of these mixtures were produced with a temperature reduction of at least 10°F.
- Production plant foaming, representing 49 percent of the market in 2020, remains the most commonly used warm-mix technology, despite decreasing about 46.2 percent since its peak in the 2011 construction season.
- Chemical additive technologies accounted for a little more than 46 percent of the market in 2020, a slight decrease from their use (48 percent) in the 2019 construction season.
- About 67 percent of survey respondents produce asphalt with WMA technologies; 184 producers in 47 states reported using WMA technologies.
- The use of WMA technologies to produce asphalt mixture at reduced temperatures reduced greenhouse gas emissions in 2020 by 0.06 – 0.25 million metric tons of CO_{2e}, which is equivalent to the annual emissions of 13,000 to 54,000 passenger vehicles.

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020

Background

A shared goal of the Federal Highway Administration (FHWA) and the National Asphalt Pavement Association (NAPA) is to support and promote sustainable practices, such as incorporation of recycled materials in pavement mixtures and the use of warm-mix asphalt (WMA) technologies. Reclaimed asphalt pavement (RAP) is recycled at a greater rate than any other material in the United States and helps lower overall material costs, allowing road owners to achieve more roadway maintenance and construction activities within limited budgets. Another recycled material used in asphalt mixtures is reclaimed asphalt shingles (RAS) from both manufacturing waste (MWAS) and post-consumer asphalt shingles (PCAS). The use of RAP and RAS in asphalt pavements can reduce the amount of new asphalt binder and aggregates required in mixtures, which can help stabilize the price of asphalt mixtures and save natural resources. Other recycled materials commonly incorporated into asphalt pavements include recycled tire rubber (RTR), steel and blast furnace slags, and cellulose fibers. By putting waste materials and byproducts to a practical use, the asphalt pavement industry helps reduce the amount of material going to landfills while improving the sustainability of asphalt mixtures.

WMA technologies reduce the mixing and compaction temperatures for asphalt mixtures. Environmental benefits include reductions in both fuel consumption and air emissions. Construction benefits include the ability to extend the paving season into the cooler months, haul material longer distances, improve compaction at lower temperatures, and use higher percentages of RAP (Prowell et al., 2012; West et al., 2014). As part of FHWA's original group of Every Day Counts initiatives, WMA was chosen in 2010 for accelerated deployment in federal-aid highway, state department of transportation (DOT), and local road projects (FHWA, 2013). In 2013, WMA was honored with the Construction Innovation Forum's NOVA Award for its engineering, economic, and environmental benefits (CIF, 2013).

FHWA works closely with the pavement industry through associations and other stakeholders to promote pavement recycling technologies and WMA. From 2007 to 2011, the American Association of State Highway and Transportation Officials (AASHTO) conducted a biennial survey of state DOT use of recycled materials (Copeland et al., 2010; Copeland, 2011; Pappas, 2011) and results were presented at FHWA Expert Task Group meetings. FHWA partners with NAPA to document industry use of RAP, RAS, other recycled materials, as well as WMA technologies used by asphalt mixture producers. These efforts have established a baseline for RAP, RAS, and WMA usage, and have tracked the growth in use of these sustainable practices by the road construction industry since 2009.

FHWA first partnered with NAPA to capture annual RAP, RAS, and WMA use for the 2009 construction season (Hansen & Newcomb, 2011; Hansen & Copeland, 2013a; 2013b; 2014; 2015; 2017; Hansen et al., 2017; Williams et al., 2018; 2019; 2020). Compared to the findings of the first survey (Hansen & Newcomb, 2011), asphalt mixture producers have shown significant growth in the use of these technologies, although the year-over-year rate of growth has slowed since the 2013 construction season. Since 2012, the survey has also asked about other recycled materials used in asphalt mixtures. Prior-year versions of this report are available at

<https://www.asphaltpavement.org/expertise/sustainability/sustainability-resources/recycling>.

This report documents the results of the industry survey for the 2020 construction season, including the results, trends, and changes from 2009 through 2020. The survey methodology and survey instrument are included in Appendix A, and state-level data are included in Appendix B.

Objective and Scope

The objective of this effort is to quantify the use of recycled materials and WMA technologies by the asphalt pavement industry. From January to July 2021, NAPA fielded a voluntary survey of asphalt mixture producers in the United States on tons produced, along with a survey of state asphalt pavement associations (SAPAs) regarding total tons of asphalt pavement mixture produced in their state during the 2020 construction season. While keeping specific producer data confidential, NAPA staff compiled the amount of asphalt mixtures produced; the amount of RAP, RAS, and other recycled material used; and the amount of WMA produced in the United States. A separate survey was conducted in parallel to measure the use of in-place asphalt pavement recycling techniques, which include full-depth reclamation (FDR), cold in-place recycling (CIR), hot in-place recycling (HIR), and cold central plant recycling (CCPR).

Survey Methodology

The survey methodology used to collect and analyze the data in this report is detailed in Appendix A. Note that when reporting data at the state level, to keep specific producer information confidential, no state-specific results are provided in the tables or appendixes if fewer than three producers from that state responded to the survey. Information from states with fewer than three responding companies is included in the estimated national values, however.

Producer Survey Results

Asphalt mixture producers from 50 states, and the District of Columbia completed the survey for the 2020 construction season. A total of 274 companies and a total of 1,406 production plants are represented in the 2020 survey. The reported total asphalt mixture tons for 2020 was 194.0 million tons, and the average tons produced per plant fell for the first time since 2016 to levels just above 2015 average.

A degree of fluctuation in year-to-year comparisons of data is influenced by which companies responded to the 2020 construction season survey versus prior-year survey respondents. For the 2020 construction season survey, there was a 29.2 percent increase in the total number of companies responding and a 27.7 percent increase in the number of plants; 34 percent of companies and more than 34 percent of the plants responding in 2020 did not participate in the 2019 survey. About 10.9 percent of responding companies, representing about 5.0 percent of the total reported tonnage, were not NAPA members.

Table 1 summarizes the number of asphalt mixture production companies and the number of production plants reporting for each state. Branches, subsidiaries, and operating units are counted as unique companies in Table 1 and throughout this report.

Table 1: Number of Companies Completing 2020 Construction Season Survey in Each State/Territory

State	Cos.	Prod. Plants	State	Cos.	Prod. Plants	State	Cos.	Prod. Plants
Alabama	4	24	Kentucky	5	25	Ohio	12	98
Alaska	*	*	Louisiana	3	8	Oklahoma	9	26
American Samoa	NCR	NCR	Maine	3	24	Oregon	5	15
Arizona	4	25	Maryland	8	18	Pennsylvania	10	53
Arkansas	6	25	Massachusetts	4	15	Puerto Rico	NCR	NCR
California	5	61	Michigan	9	50	Rhode Island	*	*
Colorado	7	28	Minnesota	5	36	South Carolina	6	23
Connecticut	*	*	Mississippi	7	26	South Dakota	*	*
Delaware	*	*	Missouri	5	16	Tennessee	7	39
District of Columbia	*	*	Montana	*	*	Texas	4	35
Florida	8	47	Nebraska	3	6	U.S. Virgin Islands	NCR	NCR
Georgia	6	58	Nevada	4	6	Utah	9	20
Guam	NCR	NCR	New Hampshire	3	16	Vermont	*	*
Hawaii	*	*	New Jersey	4	20	Virginia	9	46
Idaho	5	18	New Mexico	*	*	Washington	9	49
Illinois	21	64	New York	13	63	West Virginia	3	16
Indiana	7	43	North Carolina	9	83	Wisconsin	5	68
Iowa	4	19	North Dakota	*	*	Wyoming	*	*
Kansas	3	18	No. Mariana Islands	NCR	NCR	Total†	274	1406

NCR = No Companies Responding

* = Fewer than 3 Companies Reporting

† = Total includes companies/production plants from states with fewer than 3 companies reporting

Table 2 summarizes the total number of companies and production plants responding in previous years, as well as the average tons of asphalt pavement mixture produced by each plant.

Table 2: Summary of Jurisdictions (States or Territories), Companies, and Production Plants Responding, 2009–2020

Year	No. Jurisdictions Reporting	No. of Companies Reporting	No. of Production Plants Represented in Survey	Average Tons Produced per Plant
2009	48	196	1,027	121,000
2010	48	196	1,027	117,000
2011	49	203	1,091	121,000
2012	49	213	1,141	122,000
2013	52	249	1,281	115,000
2014	50	228	1,185	127,000
2015	49	214	1,119	137,000
2016	50	229	1,146	136,000
2017	52	237	1,146	141,000
2018	52	272	1,328	143,000
2019	50	212	1,101	147,000
2020	51	274	1,406	138,000

Table 3 includes state-by-state 2020 construction season total estimated asphalt mixture tonnage, as estimated by the SAPA or from Equation A1 (see Survey Methodology in Appendix A); tonnage reported by survey respondents; and the percentage of reported tons included in estimated tons. The closer a state's percentage is to 100 percent indicates the completeness of reported tonnage compared to estimated tonnage. At the national level, survey responses make up 48 percent of the estimated total tons for the 2020 construction season.

Table 3: Summary of 2020 Estimated and Reported Asphalt Mixture Tons in Each State

State	Tons, Millions		Reported % of Estimated	State	Tons, Millions		Reported % of Estimated
	Estimated	Reported			Estimated	Reported	
Alabama	7.0	2.5	36%	Montana	4.1	*	*
Alaska	5.1	*	*	Nebraska	3.0	0.4	13%
American Samoa	0.02	NCR	NCR	Nevada	3.5	1.2	34%
Arizona	7.4	4.2	57%	New Hampshire	1.6	1.1	69%
Arkansas	6.0	2.9	48%	New Jersey	9.8	4.8	49%
California	25.4	12.2	48%	New Mexico	3.8	*	*
Colorado	9.0	4.9	54%	New York	17.5	5.6	32%
Connecticut	4.9	*	*	North Carolina	12.0	9.9	83%
Delaware	1.3	*	*	North Dakota	2.5	*	*
District of Columbia	1.2	*	*	No. Mariana Isl.	0.02	NCR	NCR
Florida	16.8	11.2	67%	Ohio	18.0	11.8	66%
Georgia	13.6	7.4	54%	Oklahoma	5.1	3.8	75%
Guam	0.1	NCR	NCR	Oregon	5.2	2.1	40%
Hawaii	0.8	*	*	Pennsylvania	17.8	5.9	33%
Idaho	2.9	1.2	41%	Puerto Rico	1.4	NCR	NCR
Illinois	14.4	8.4	58%	Rhode Island	2.2	*	*
Indiana	13.0	7.5	58%	South Carolina	7.0	3.2	46%
Iowa	5.2	1.9	37%	South Dakota	2.9	*	*
Kansas	3.5	2.4	69%	Tennessee	8.9	3.8	43%
Kentucky	4.0	1.7	43%	Texas	35.0	5.2	15%
Louisiana	7.5	1.1	15%	U.S. Virgin Isl.	0.1	NCR	NCR
Maine	2.7	2.7	99%	Utah	4.3	3.8	88%
Maryland	6.3	4.6	73%	Vermont	2.0	*	*
Massachusetts	6.5	2.9	45%	Virginia	10.5	7.3	70%
Michigan	14.8	10.0	68%	Washington	5.3	5.0	94%
Minnesota	12.2	7.3	60%	West Virginia	3.8	0.3	8%
Mississippi	4.3	4.2	98%	Wisconsin	12.0	9.6	80%
Missouri	10.2	2.4	24%	Wyoming	2.3	*	*
Total					407.8	194.0 [†]	48%

NCR No Companies Responding

* Fewer than 3 Companies Reporting

[†] Total Reported Tons includes values from state with fewer than 3 Companies Reporting

SAPA Estimated Tons

Numbers do not add up exactly due to rounding

Figure 1 shows the number of production plants, as well as the average tons produced per production plant, separated by User/Producer Group (UPG) region. The number of production plants responding from each UPG region increased from 2019 to 2020 with the largest increase in the North Central Asphalt User/Producer Group (NCAUPG) region and the smallest increase in the North East Asphalt User/Producer Group (NEAUPG) region. All User Producer Group regions saw a decrease in tonnage produced per plant during the 2020 construction season.

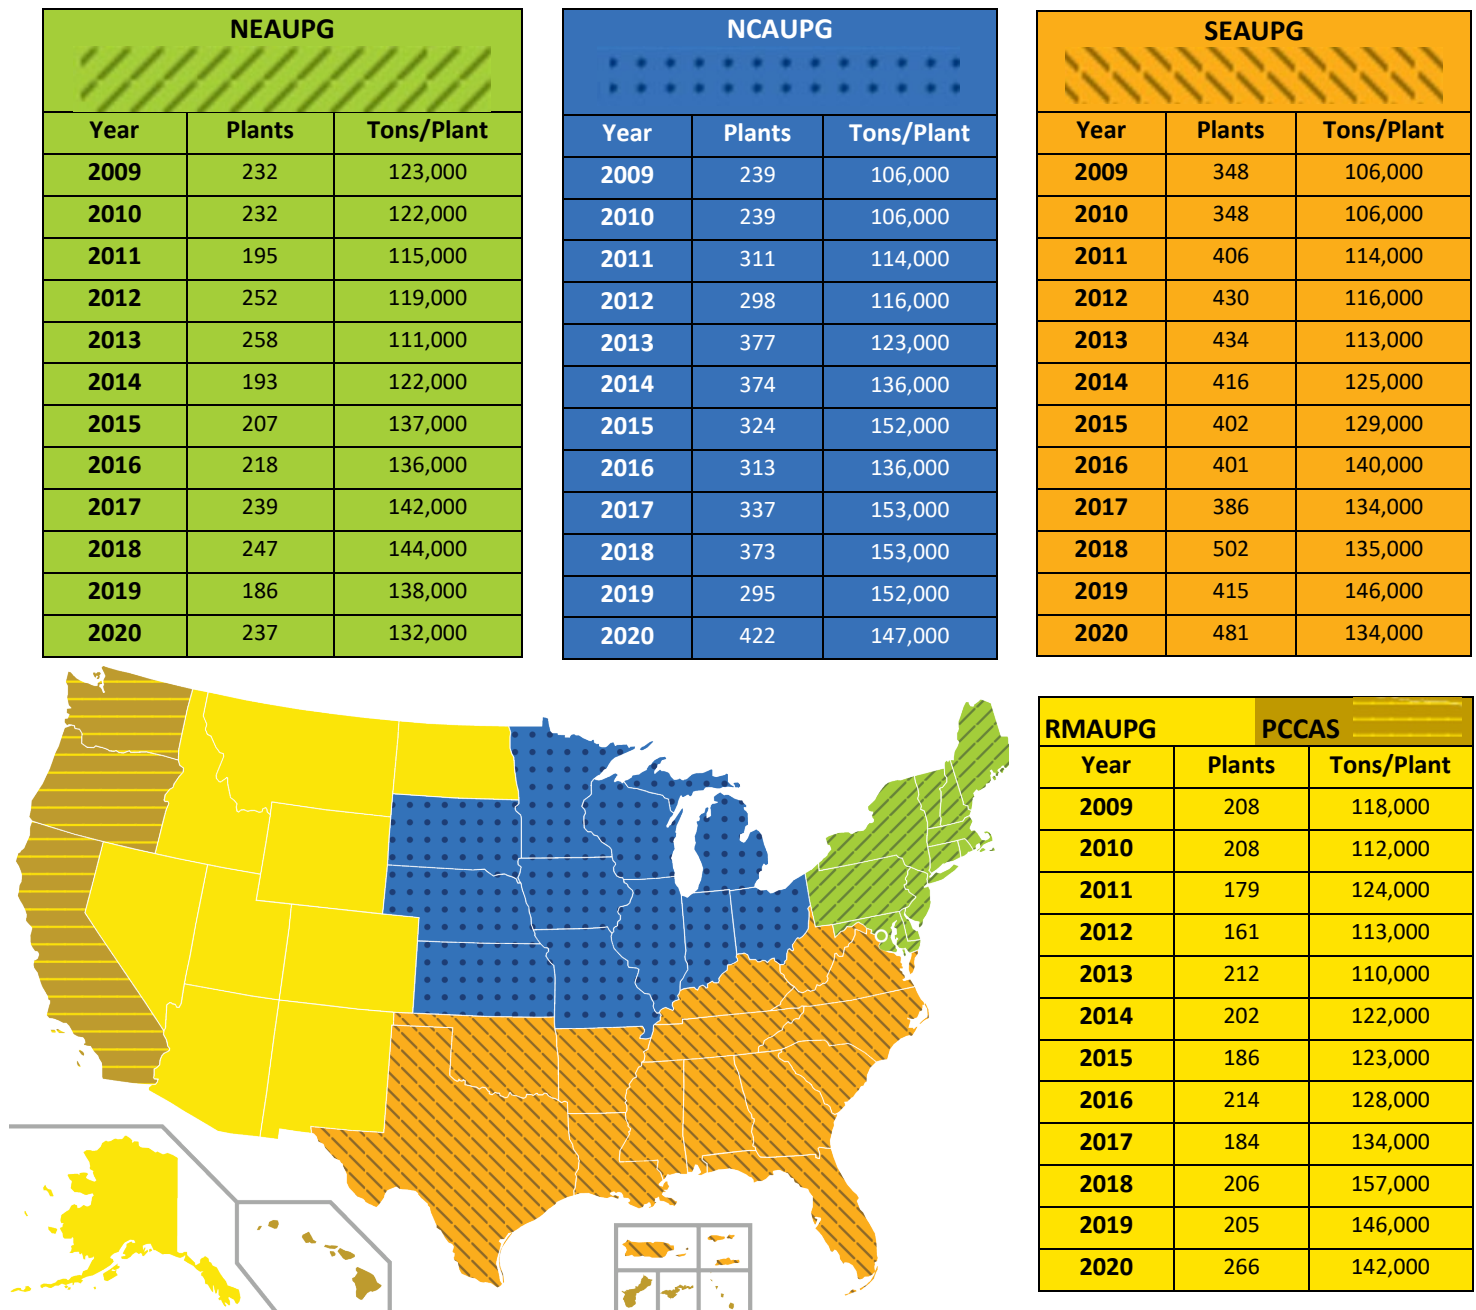


Figure 1: Number of Production Plants Responding to Survey by User/Producer Group Region and Estimated Tonnage Per Plant, 2009–2020

Data Summary and National Estimates

Table 4: Summary of RAP, RAS, WMA Data

NATIONAL SUMMARY					
Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	161.7	194.0	421.9	407.8
	DOT	63.2	77.5	164.8	162.8
	Other Agency	42.2	52.5	110.2	110.5
	Commercial & Residential	56.3	64.0	146.8	134.5
	No. of Companies Reporting	212	274		
RAP (Tons, Millions)	Accepted	40.2	48.7	97.0	96.3
	Used in HMA/WMA Mixtures	36.5	44.9	89.2	87.0
	Used as Aggregate	1.7	3.1	3.8	5.8
	Used in Cold-Mix Asphalt	0.1	0.2	0.3	0.4
	Used in Other	0.6	0.1	1.4	0.3
	Landfilled	0.1	0.1	0.1	0.2
	Total Tons of RAP Stockpiled at Year-End	58.8	71.5	138.0	135.3
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.1%	19.7%		
	Average % for Other Agency Mixtures ¹	19.3%	20.0%		
	Average % for Commercial & Residential Mixtures ¹	23.4%	24.0%		
	National Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			21.1%	21.3%
RAP	No. of Companies Reporting Using RAP	207	271		
RAS (Tons, Thousands)	Unprocessed PCAS Shingles Accepted	106	132	277	277
	Unprocessed MWAS Shingles Accepted	128	113	334	237
	Processed Shingles Accepted	162	132	423	278
	Used in HMA/WMA Mixtures	353	279	921	586
	Used as Aggregate	7	0	18	0
	Used in Cold-Mix Asphalt	0	0	0	0
	Used in Other	0	26	0	55
	Landfilled	0	0	0	0
	Total Tons of RAS Stockpiled at Year-End	438	605	1,143	1,272
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.226%	0.128%		
	Average % for Other Agency Mixtures ¹	0.195%	0.130%		
	Average % for Commercial & Residential Mixtures ¹	0.228%	0.156%		
	National Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.218%	0.144%
RAS	No. of Companies Reporting Using RAS	46	57		
WMA Technologies	Total Tons Produced With WMA Technology at Reduced Temperature			78.8	93.1
	Total Tons Produced With WMA Technology at HMA Temperatures			85.7	93.3
	DOT	43.5%	51.9%	71.7	84.5
	Other Agency	40.6%	45.2%	44.8	49.9
	Commercial & Residential	32.7%	38.6%	48.0	52.0
	No. of Companies Reporting Using WMA Technologies	130	184		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

Table 4 summarizes the RAP, RAS, and WMA data from the 2020 construction season survey alongside data from the 2019 construction season survey (Williams et al., 2020) for comparison. The information requested in the survey is summarized in Appendix A. In the column labeled "Reported Values" are national summaries of the values from asphalt mixture producers completing the survey. The column labeled "Estimated Values" for the category labeled "Tons of HMA/WMA Produced" was determined as outlined in the Survey Methodology section of Appendix A.

For the amount of RAP accepted, asphalt mixture producers were asked “How many tons of removed asphalt pavement and asphalt millings were accepted/delivered to your facilities in the state in 2020?” For the amount of RAS accepted, producers were asked “How many tons of shingles were accepted/delivered to your facilities in the state in 2020?” Producers were asked to report tons of unprocessed PCAS and unprocessed MWAS accepted/delivered, as well as tons of processed RAS acquired from shingle processors. These data are reported in Table 4 as the tonnage of material accepted. Producers were also asked for the tonnage of RAP and RAS used in the production of asphalt pavement mixtures, cold-mix asphalt, as aggregate, or for other purposes, such as in a chip seal. The tons of reclaimed material sent to landfills were also requested, along with the tons of material stockpiled at year-end.

For each state, the tons of RAS and RAP reported as accepted and used were multiplied by the ratio of total estimated production to total reported production, and these values were summed to arrive at the national estimated tons for these materials, which is reported in the “Estimated Values” column of Table 4.

To understand the average percentage of recycled material used in mixtures, producers were asked to report the percent of RAP or RAS averaged across all asphalt mixtures produced for each sector (DOT, Other Agency, Commercial & Residential). If precise data were not available, respondents were asked to provide their best estimate. These responses are reported in the “Average % Used in Mixtures” section of Table 4 for RAP and RAS. A “National Average All Mixtures Based on Tons Used in HMA/WMA” was calculated and reported in Table 4 for both RAP and RAS based on reported tonnage of each material used in HMA/WMA mixtures divided by the total reported tons produced. Producers were not asked about allowable RAP or RAS limits or binder replacement requirements, which can influence demand for mixtures that incorporate these materials.

Producers were asked to give their best estimate of the percentage of tons of asphalt paving mixture produced for each sector using WMA technologies with a temperature reduction of 10°F to 100°F. A separate question was asked about the percentage of tons of asphalt paving mixture produced for each sector with WMA technologies but without reducing production temperatures. These percentages were multiplied by the total mixture production for each sector to determine the total estimated tons of asphalt mixture produced using WMA technologies for each sector.

Total Asphalt Mixture Production

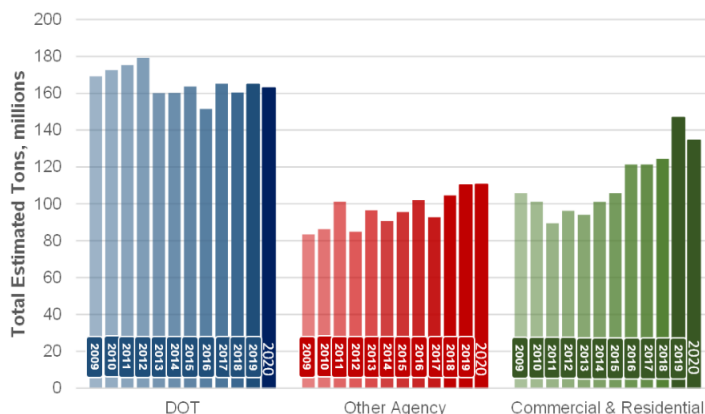


Figure 2a: Estimated Total Asphalt Mixture Production by Sector, 2009–2020

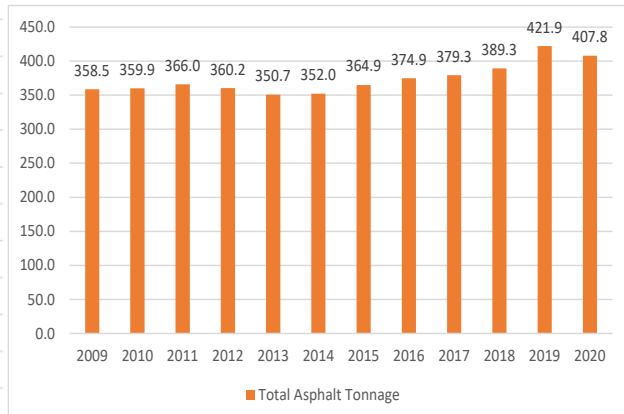


Figure 2b: Estimated Total Asphalt Mixture Production in Total, 2009–2020

Table 4 includes the national summary of asphalt mixture production data from the 2019 and 2020 construction season surveys. The information requested in the survey is detailed in Appendix A and summarized in Table A1, Section 2. State-level data are reported in Appendix B.

From 2019 to 2020, the estimated total amount of asphalt mixture produced in the United States decreased from 421.9 million tons to 407.8 million tons, a decrease of 3.3 percent.

Asphalt pavement mixture producers' customers can be divided into two broad sectors: the private sector (Commercial & Residential) and the public sector (DOT or Other Agency). The "Other Agency" sector includes asphalt pavement mixtures produced for public works agencies; toll authorities; and city, county, and tribal transportation agencies, as well as the U.S. military and federal agencies, such as the Federal Aviation Administration, National Park Service, and U.S. Forest Service.

As seen in Figure 2, increases and decreases in total tonnage production estimates by sector have varied from year to year. Compared to the 2019 construction season, 2020 asphalt mixture tonnage produced for the DOT sector decreased 1.2 percent, mixture production for the Other Agency sector increased by 0.3 percent, and the Commercial and Residential sector decreased significantly (8.4 percent) from 2019 to 2020.

Reclaimed Asphalt Pavement

Table 4 includes the national summary of RAP data from the 2019 and 2020 construction season surveys. The information requested in the survey is detailed in Appendix A and summarized in Table A1, Section 2. State-level data is reported in Appendix B. Figure 3 is a visual representation of the estimated total tons of RAP used in asphalt mixtures, aggregate, cold-mix asphalt, and other uses, as well as the amount landfilled, from the 2009 to 2020 construction season surveys. The overwhelming majority of RAP is used in hot-mix asphalt (HMA) or warm-mix asphalt (WMA) mixtures, which is the most optimal use of RAP.

From the 2019 to 2020 construction season, the amount of RAP used in HMA/WMA decreased from 89.2 million to 87.0 million tons. The average percent RAP used in asphalt mixtures increased to 21.3 percent in 2020 from 21.1 percent in 2019. For 2020, about 99 percent of companies responding to the survey reported using RAP. This was a slight increase from the 98 percent of companies reporting using RAP in 2019, and a slight decrease from the 100 percent of companies reporting using RAP in 2013 and 2014, and in line with the 99 percent of companies reporting RAP use in the 2015 survey.

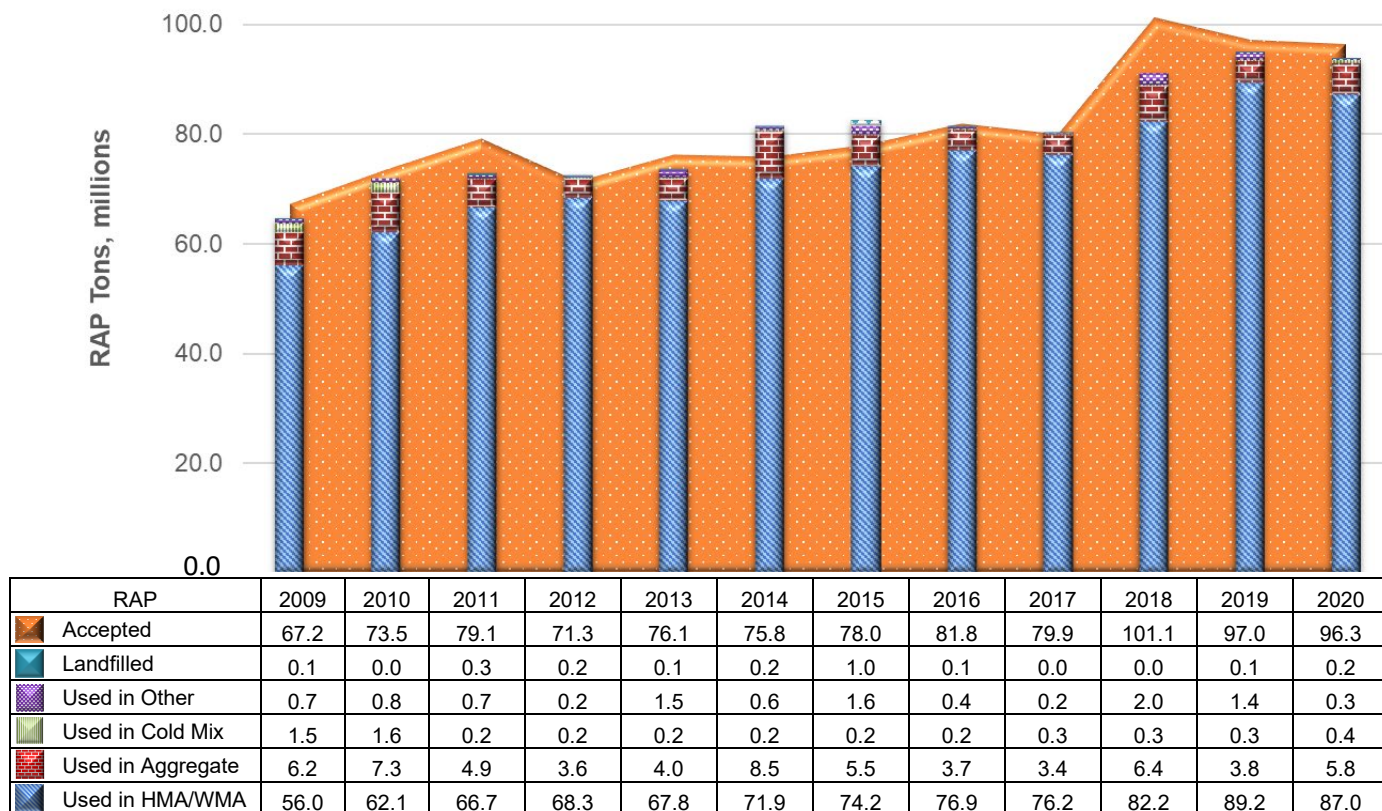


Figure 3: Comparison of Tons of RAP Accepted and Tons of RAP Used or Landfilled (Million Tons), 2009–2020

Placement of RAP in construction and demolition landfills is rare. Since the beginning of the survey in 2009, the average amount of RAP landfilled is less than 170,000 tons per year. In 2020, 150,044 tons, about 0.16 percent, of RAP was landfilled. The amount of RAP accepted during the 2020 construction season saved about 58.4 million cubic yards of landfill space.

RAP Use by Sector

Figure 4 shows the total estimated tons of RAP used in each sector. These values were calculated using the average percentages of RAP reported by producers for each sector and adjusted to account for differences between reported RAP tonnage and tons calculated from the percentage by sector.

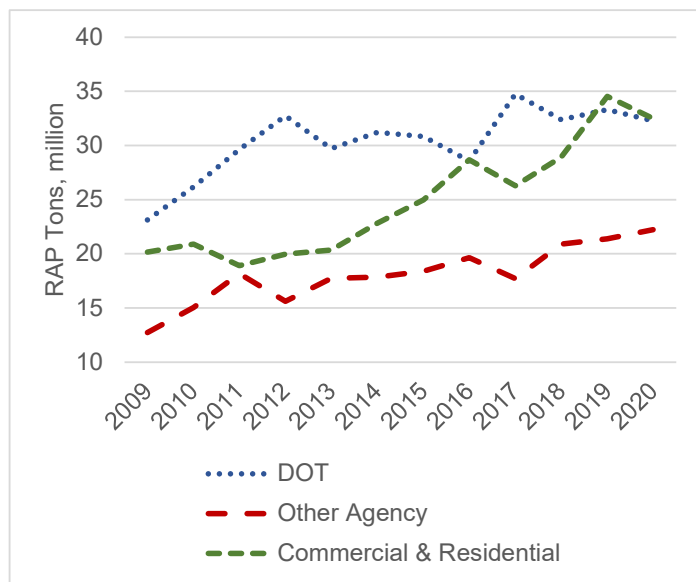


Figure 4: RAP Use by Sector (Million Tons)

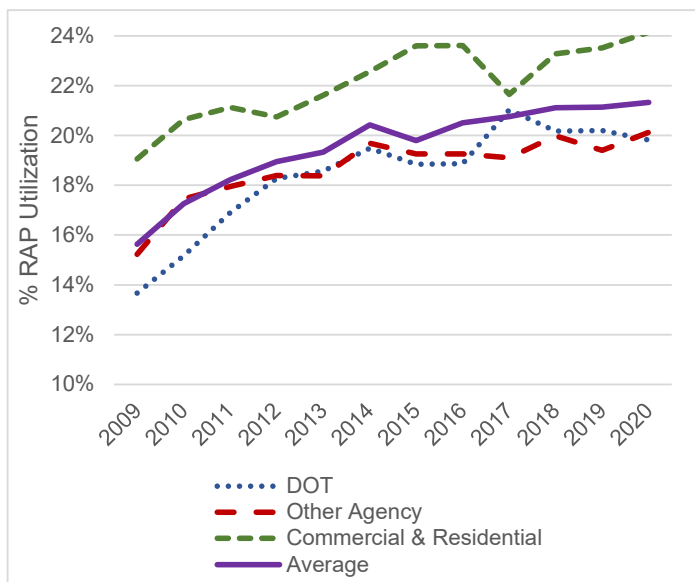


Figure 5: Average Percent RAP Used by Sector

Figure 5 shows the average percentage of RAP used by each sector and overall across all asphalt pavement mixtures. In 2020, the average percent RAP used by all sectors increased to a new high of 21.3 percent. Previously, the average percent RAP had seen steady growth from 2009 to 2014 before plateauing around 20 percent through 2017. The percent of RAP used in each sector during 2020 remained steady with the utilization percentages from 2019.

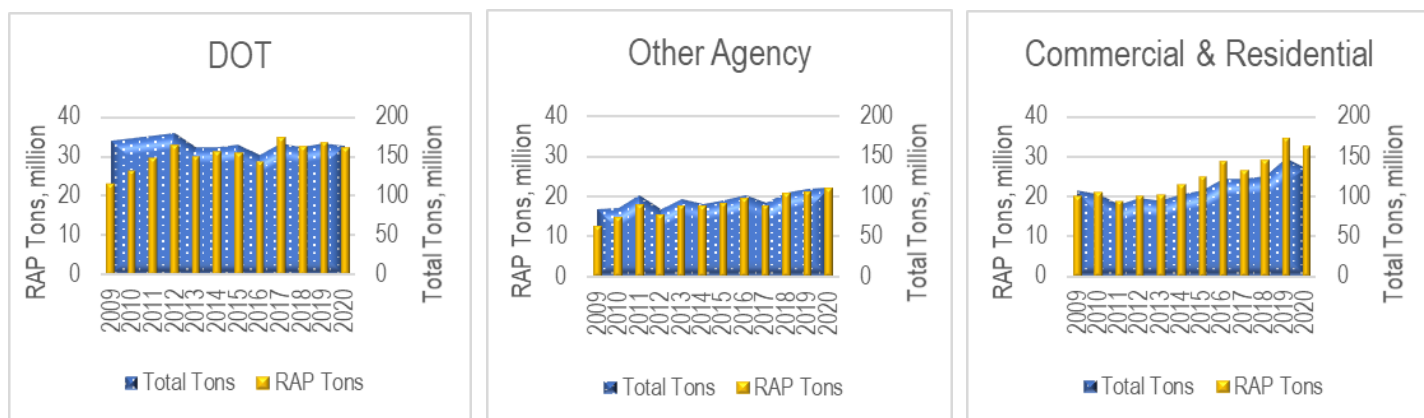


Figure 6: RAP Tons and Total Mixture Tons Comparison (Million Tons)

Since the 2012 construction season, the tonnage of RAP used by each sector has generally moved up or down with the total tonnage used by the sector, which is shown in Figure 6. For the 2020 construction season, the tons of RAP used increased slightly in the Other Agency sector, while it decreased for the DOT and Commercial & Residential sectors. The changes in RAP tonnage were a result of changes in mix tonnages for each sector, and the sectors remained relatively flat in their percent utilization, which resulted in the national average percentage of RAP used increasing slightly from 21.1 percent in 2019 to 21.3 percent 2020 season.

RAP Use in Each State

Table 5 and Figure 7 show the average percentage of RAP used in HMA/WMA mixtures in each state by construction season based on reported RAP tons used in HMA/WMA mixtures and total reported tonnage. It should be noted that the accuracy of data for individual states varies depending on the number of responses received from producers in each state and the total number of tons accounted for in the responses.

Figure 8 revisualizes the Table 5 data, showing the number of states with producers reporting average RAP percentages used at the various ranges by construction season from 2009 to 2020. The number of states with producers reporting average RAP percentages 20 percent or greater has increased significantly, rising from 10 states in 2009 to 27 states in 2014; 29 states in 2016, decreasing to 24 states in 2017, 30 states in 2018, and peaking at 31 states in 2019, and then falling back to 26 states in 2020. The number of states with producers reporting RAP percentages less than 15 percent has decreased from 23 states in 2009 to just two states in 2014 and then remained relatively steady at 10 or 11 states in 2015 through 2017, before dropping to six states in 2018, five states in 2019, and slightly increasing to seven states in 2020.

Table 5: Average Estimated Percentage of RAP Used in Each State, 2016–2020

State	Average RAP Percent					State	Average RAP Percent				
	2016	2017	2018	2019	2020		2016	2017	2018	2019	2020
Alabama	24%	24%	26%	25%	24%	Montana	*	*	*	*	*
Alaska	*	*	*	*	*	Nebraska	*	19%	26%	*	20%
American Samoa	NCR	*	*	*	NCR	Nevada	22%	12%	*	*	17%
Arizona	9%	10%	12%	9%	7%	New Hampshire	21%	22%	18%	*	17%
Arkansas	10%	11%	12%	13%	14%	New Jersey	19%	19%	18%	20%	17%
California	15%	18%	16%	16%	15%	New Mexico	22%	21%	19%	*	*
Colorado	24%	24%	20%	20%	19%	New York	16%	16%	17%	17%	18%
Connecticut	21%	18%	15%	21%	*	North Carolina	23%	18%	26%	24%	31%
Delaware	*	*	*	NCR	*	North Dakota	*	12%	*	*	*
Dist. of Columbia	NCR	*	*	*	*	No. Mariana Isl.	NCR	NCR	NCR	NCR	NCR
Florida	32%	35%	27%	31%	34%	Ohio	27%	28%	28%	32%	28%
Georgia	27%	23%	25%	*	28%	Oklahoma	17%	15%	17%	19%	19%
Guam	NCR	NCR	NCR	NCR	NCR	Oregon	22%	18%	27%	26%	27%
Hawaii	*	20%	23%	19%	*	Pennsylvania	15%	15%	16%	13%	20%
Idaho	21%	27%	27%	24%	26%	Puerto Rico	NCR	NCR	NCR	NCR	NCR
Illinois	23%	25%	28%	23%	26%	Rhode Island	*	*	*	*	*
Indiana	22%	22%	24%	21%	24%	South Carolina	23%	21%	22%	22%	21%
Iowa	14%	11%	18%	19%	17%	South Dakota	*	*	NCR	NCR	*
Kansas	20%	19%	21%	*	26%	Tennessee	21%	23%	18%	24%	19%
Kentucky	13%	24%	16%	16%	18%	Texas	13%	15%	17%	16%	19%
Louisiana	19%	21%	22%	22%	17%	U.S. Virgin Islands	NCR	NCR	*	NCR	NCR
Maine	16%	20%	*	*	17%	Utah	25%	22%	27%	28%	26%
Maryland	26%	23%	26%	30%	28%	Vermont	*	*	*	*	*
Massachusetts	18%	16%	16%	16%	15%	Virginia	28%	32%	28%	28%	31%
Michigan	32%	28%	28%	29%	26%	Washington	25%	20%	24%	23%	24%
Minnesota	21%	20%	25%	24%	24%	West Virginia	14%	18%	20%	18%	17%
Mississippi	19%	18%	20%	23%	20%	Wisconsin	22%	16%	17%	21%	21%
Missouri	23%	23%	21%	27%	23%	Wyoming	10%	12%	*	*	*
NCR No Company Responding	* ≤ 3 Companies Reporting		0-9%		10-14%		15-19%		20-29%		≥ 30%

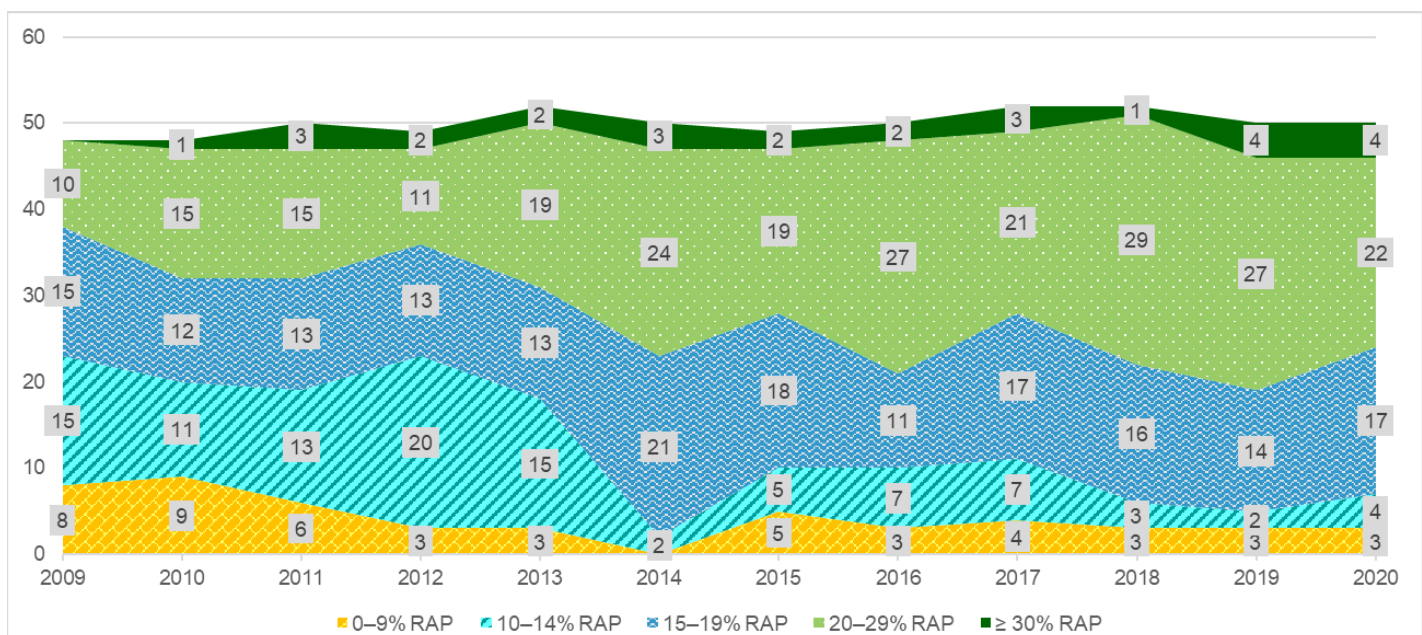
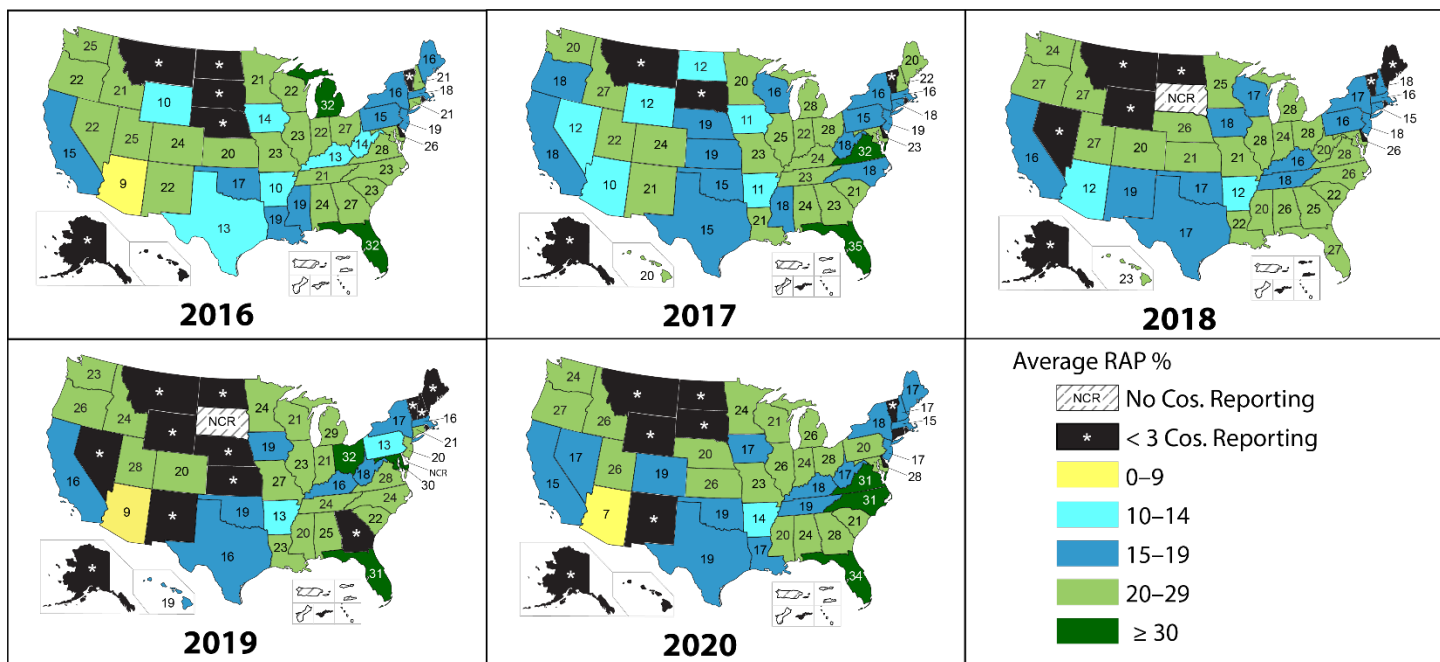


Figure 8: Number of States at Different Average Percentage of RAP Used in HMA/WMA Mixtures, 2009–2020

RAP Stockpiles

During the 2020 construction season, an estimated 96.3 million tons of RAP was accepted by asphalt mixture producers, and 93.5 million tons of RAP was used across all purposes during the year. In 2020, as in 2019, 2018, and 2016, more RAP was received than was utilized, indicating an increase in producer inventory. By comparison, in 2012, 2014, and 2015, more RAP was used than was received, indicating producers were drawing upon stockpiled RAP. In 2017, RAP acceptance and use were about equal. In 2020, the estimated amount of RAP stockpiled nationwide decreased to 135.30 million tons, a 2 percent decrease from the 138.04 million tons of RAP stockpiled at the end of the 2019 construction season. This decrease in stockpiled inventory is counter to the difference in the amount of RAP used and accepted, which can occur due to different asphalt producers responding to the survey each year. For 2020, 97.1 percent of producers reported having stockpiled RAP, up from 93.9 percent of producers in 2019. The reported RAP stockpiled represents about 1.4 years of inventory at 2020 utilization levels. Table 6 shows the reported and estimated amount of RAP stockpiled in each state at the end of the 2020 construction season. To calculate the estimated values, reported tons of RAP stockpiled were divided by the ratio of total reported tons of mixture produced to estimate tons of mixture produced. The total tonnage row in Table 6 includes stockpiled tonnages from states with fewer than three producers reporting.

Table 6: Reported Tons of RAP Stockpiled

State	Reported Tons Stockpiled (Million)		Estimated Tons Stockpiled (Million)		State	Reported Tons Stockpiled (Million)		Estimated Tons Stockpiled (Million)	
	2019	2020	2019	2020		2019	2020	2019	2020
Alabama	0.80	0.76	1.62	2.13	Montana	*	*	*	*
Alaska	*	*	*	*	Nebraska	*	0.12	*	0.90
American Samoa	*	NCR	*	NCR	Nevada	*	0.12	*	0.34
Arizona	0.46	0.58	0.99	1.02	New Hampshire	*	0.32	*	0.46
Arkansas	0.18	0.45	0.46	0.93	New Jersey	6.32	2.30	11.04	4.69
California	0.69	2.08	2.29	4.33	New Mexico	*	*	*	*
Colorado	0.66	0.86	1.32	1.57	New York	1.20	0.89	3.14	2.79
Connecticut	0.20	*	0.44	*	North Carolina	1.63	5.60	3.16	6.78
Delaware	NCR	*	NCR	*	North Dakota	*	*	*	*
District of Columbia	*	*	*	*	No. Mariana Isl.	NCR	NCR	NCR	NCR
Florida	2.24	3.62	3.69	5.43	Ohio	6.37	3.81	11.07	5.81
Georgia	*	3.31	*	6.07	Oklahoma	0.39	1.20	1.10	1.61
Guam	NCR	NCR	NCR	NCR	Oregon	0.82	0.94	2.25	2.34
Hawaii	0.15	*	0.19	*	Pennsylvania	0.40	0.85	3.18	2.57
Idaho	0.98	0.65	1.80	1.56	Puerto Rico	NCR	NCR	NCR	NCR
Illinois	0.70	2.00	6.33	3.43	Rhode Island	*	*	*	*
Indiana	1.16	2.35	3.30	4.07	South Carolina	0.71	1.42	1.91	3.11
Iowa	0.34	0.53	1.38	1.45	South Dakota	NCR	*	NCR	*
Kansas	*	0.79	*	1.15	Tennessee	4.02	1.85	4.94	4.32
Kentucky	0.33	0.58	0.80	1.36	Texas	0.77	0.99	5.27	6.69
Louisiana	0.19	0.05	1.08	0.35	U.S. Virgin Islands	NCR	NCR	NCR	NCR
Maine	*	0.37	*	0.37	Utah	1.17	0.46	1.66	0.52
Maryland	0.16	2.65	0.68	3.63	Vermont	*	*	*	*
Massachusetts	0.54	0.69	1.65	1.56	Virginia	1.73	2.56	3.60	3.68
Michigan	14.75	14.98	28.12	22.17	Washington	1.26	1.15	1.79	1.22
Minnesota	1.50	3.96	2.93	6.62	West Virginia	0.33	0.34	0.66	4.33
Mississippi	0.43	0.61	0.57	0.63	Wisconsin	2.00	2.14	2.77	2.67
Missouri	1.66	0.42	4.13	1.76	Wyoming	*	*	*	*
Total†						58.80	71.48	138.04	135.30

NCR No Companies Responding for the State to the Survey

* Fewer than 3 Companies Reporting

† Includes Values from States with Fewer than 3 Companies Reporting

RAP Fractionation

Table 7 shows the average percentage of RAP fractionated into two or more sizes in each state, as reported by survey participants. **These results are representative only of the survey participants and do not completely reflect practices in a given state.** This also helps explain the state-level variability from year to year. Producers and SAPAs were not questioned about state specifications regarding fractionation and recycled material content.

Previous reports have shown that fractionation of RAP does not correlate to increased RAP utilization percentages. This holds true for the 2020 data, with an example being Oklahoma, which reports 70 percent of RAP being fractionated and averaging under 19 percent RAP in mixtures, while Maryland reported only 5 percent of RAP being fractionated but averaged over 28 percent RAP in mixtures.

Table 7: Reported Percentage of RAP Fractionated, in Each State, 2019–2020

State	% Fractionated		State	% Fractionated		State	% Fractionated	
	2019	2020		2019	2020		2019	2020
Alabama	19%	35%	Kentucky	48%	50%	Ohio	13%	19%
Alaska	*	*	Louisiana	92%	25%	Oklahoma	32%	70%
American Samoa	*	NCR	Maine	*	17%	Oregon	1%	8%
Arizona	0%	13%	Maryland	0%	5%	Pennsylvania	0%	23%
Arkansas	15%	37%	Massachusetts	0%	7%	Puerto Rico	NCR	NCR
California	3%	41%	Michigan	21%	22%	Rhode Island	*	*
Colorado	43%	26%	Minnesota	15%	12%	South Carolina	46%	27%
Connecticut	20%	*	Mississippi	0%	17%	South Dakota	NCR	*
Delaware	NCR	*	Missouri	22%	16%	Tennessee	15%	34%
Dist. of Columbia	*	*	Montana	*	*	Texas	50%	45%
Florida	15%	14%	Nebraska	*	0%	U.S. Virgin Isl.	NCR	NCR
Georgia	*	8%	Nevada	*	0%	Utah	13%	8%
Guam	NCR	NCR	New Hampshire	*	0%	Vermont	*	*
Hawaii	50%	*	New Jersey	10%	25%	Virginia	27%	31%
Idaho	0%	1%	New Mexico	*	*	Washington	23%	18%
Illinois	25%	58%	New York	7%	17%	West Virginia	0%	0%
Indiana	57%	61%	North Carolina	7%	42%	Wisconsin	3%	24%
Iowa	0%	5%	North Dakota	*	*	Wyoming	*	*
Kansas	*	35%	No. Mariana Isl.	NCR	NCR			
Average, Where Used [†]						21%	26%	

NCR No Companies Responding for the State to the Survey

* Fewer than 3 Companies Reporting

[†] Includes Values from States with Fewer than 3 Companies Reporting

RAP Recycling Agent Use

Table 8 shows the percentage of reported tons of RAP-containing mixtures produced using softer binder or recycling agents in each state. **These results are representative *only* of the survey participants and do not completely reflect practices in a given state.** While there is no strong relationship between the amount of RAP mixtures using softer binder or recycling agents and percentage of RAP used by the state, it should be noted that of the 26 states using 20 percent or more RAP, 23 of them report using softer binders and or recycling agents in a percentage of their RAP mixtures and three of these states reported no use of softer binders or recycling agents in RAP mixtures.

Table 8: Percentage of RAP Mixes Using Softer Binder and/or Recycling Agents in Each State, 2020

State	Softer Binder	Recyc. Agent	State	Softer Binder	Recyc. Agent	State	Softer Binder	Recyc. Agent
Alabama	1%	8%	Kentucky	5%	4%	Ohio	46%	9%
Alaska	*	*	Louisiana	8%	0%	Oklahoma	21%	15%
American Samoa	NCR	NCR	Maine	0%	0%	Oregon	6%	10%
Arizona	15%	16%	Maryland	20%	6%	Pennsylvania	12%	9%
Arkansas	0%	0%	Massachusetts	4%	0%	Puerto Rico	NCR	NCR
California	3%	35%	Michigan	35%	0%	Rhode Island	*	*
Colorado	30%	0%	Minnesota	19%	11%	South Carolina	28%	0%
Connecticut	*	*	Mississippi	2%	0%	South Dakota	*	*
Delaware	*	*	Missouri	56%	0%	Tennessee	22%	12%
Dist. of Columbia	*	*	Montana	*	*	Texas	16%	19%
Florida	69%	0%	Nebraska	0%	0%	U.S. Virgin Isl.	NCR	NCR
Georgia	18%	0%	Nevada	13%	0%	Utah	50%	0%
Guam	NCR	NCR	New Hampshire	0%	0%	Vermont	*	*
Hawaii	*	*	New Jersey	3%	24%	Virginia	13%	7%
Idaho	86%	0%	New Mexico	*	*	Washington	40%	9%
Illinois	45%	1%	New York	2%	8%	West Virginia	0%	0%
Indiana	4%	0%	North Carolina	36%	10%	Wisconsin	11%	21%
Iowa	25%	0%	North Dakota	*	*	Wyoming	*	*
Kansas	75%	0%	No. Mariana Isl.	NCR	NCR			
Average, When Used [†]							23%	6%

NCR No Companies Responding for the State to the Survey

* Fewer than 3 Companies Reporting

[†] Includes Values from States with Fewer than 3 Companies Reporting

Although the data is highly dependent upon the companies responding to the survey each year, the average percentage of RAP mixtures incorporating softer binders was 23 percent during the 2020 construction season, which is up from 18 percent in the 2019 survey. The percentage of RAP mixtures incorporating recycling agents has fluctuated year to year with 6 percent in 2020, 4 percent in 2019, 4 percent in 2018, 4 percent in 2017, 7 percent in 2016, and 3 percent in 2015.

Reclaimed Asphalt Shingles

Table 4 includes the national summary of RAS data from the 2019 and 2020 construction season surveys. The information requested in the survey is detailed in Appendix A and summarized in Table A1, Section 3. State-level data is reported in Appendix B. Producers and SAPAs were not asked about allowable RAS limits or binder replacement requirements for their states. Figure 9 is a visual representation of the estimated total tons of RAS used in asphalt mixtures, aggregate, cold-mix asphalt, and other uses, as well as the amount landfilled, from the 2009 to 2020 construction season surveys.

During the 2020 construction season, the total estimated amount of unprocessed and processed shingles received by producers was 792,000 tons, which is more than combined amount of RAS used in asphalt mixtures (586,000 tons) and in other civil engineering applications (55,000 tons) for the year. This is a 23 percent decrease from the 1.03 million total tons of RAS from all sources accepted during the 2019 construction season. The use of 586,000 tons of RAS in asphalt pavement mixtures during 2020 is a 36 percent decrease from the 921,000 tons used in 2019.

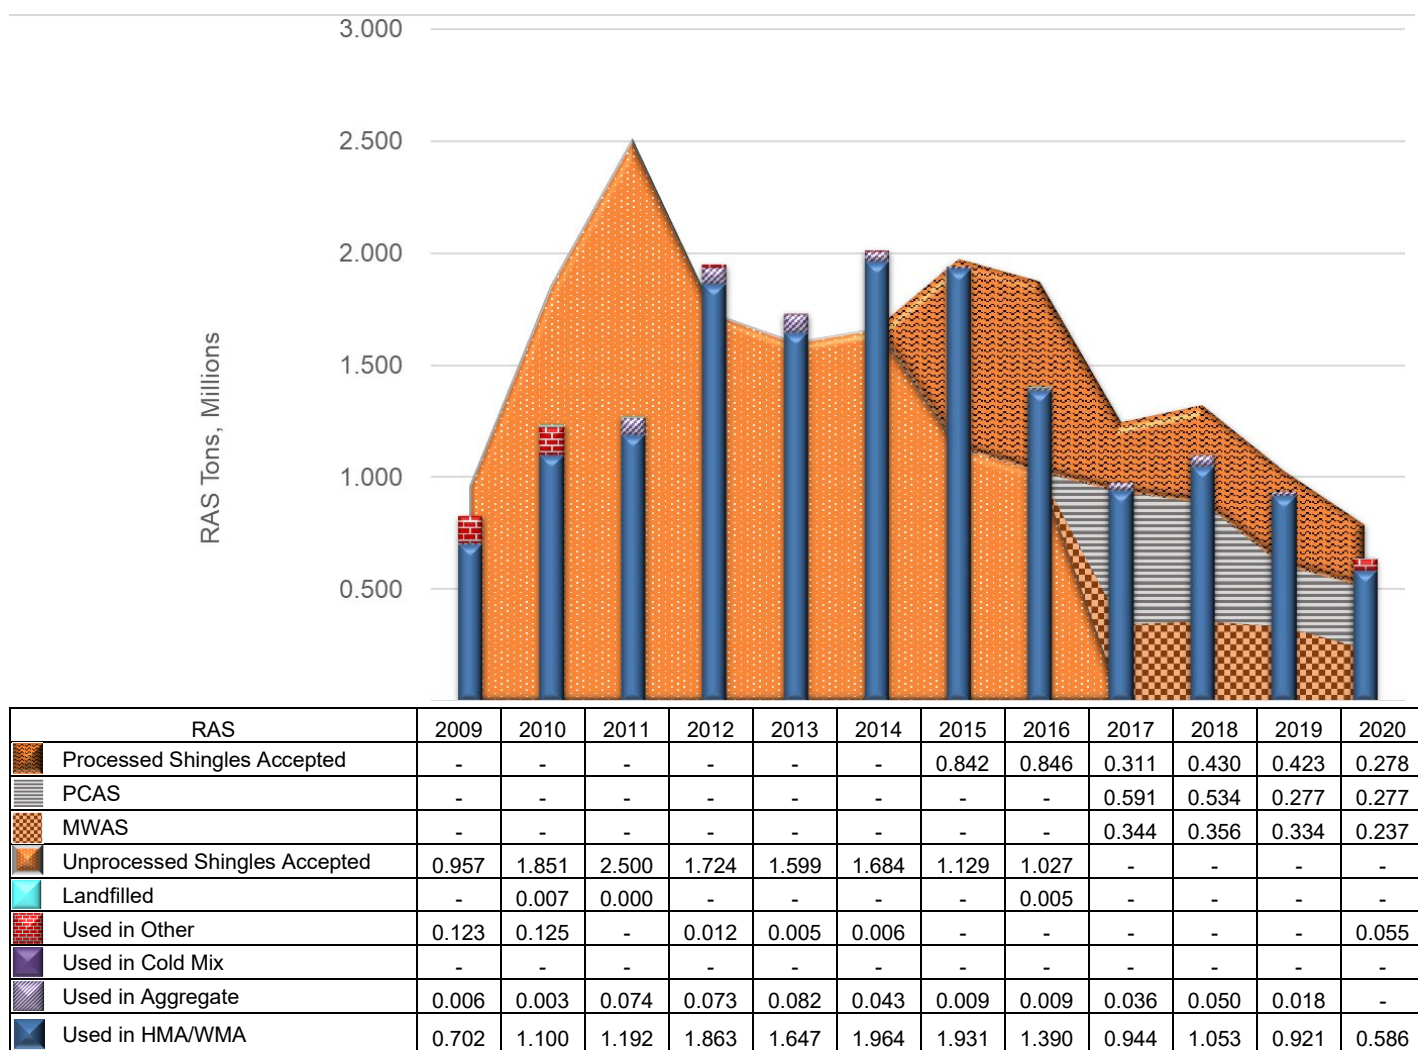


Figure 9: Comparison of Tons of RAS Accepted and Tons of RAS Used or Landfilled (Million Tons), 2009–2020. Processed RAS Acceptance First Tracked in 2015

As shown in Figure 9, from the 2012 to 2014 construction seasons, producers reported using RAS in greater quantities than they accepted. When this trend was first noticed, producers were contacted to confirm the reported values. All producers contacted indicated they either had RAS stockpiled or were purchasing RAS from shingle processors. To capture the volume of processed shingles accepted by producers, the 2015 survey began asking producers “How

many tons of processed shingles were accepted/delivered to your facilities in the state?” Beginning with the 2017 construction season survey producers were asked to report the tons of unprocessed PCAS, unprocessed MWAS, and processed RAS accepted separately.

As seen in Table 4, there was a significant (29 percent) decrease in the acceptance of MWAS in 2020 compared to 2019, leading to a 23 percent decrease in the total amount of RAS accepted during the 2020 construction season. The total estimated amount of unprocessed shingles accepted by producers declined 16 percent from 611,000 tons in 2019 to 514,000 tons in 2020. Acceptance of processed shingles decreased 34 percent during the same time period, from 423,000 tons in 2019 to 278,000 tons in 2020.

No RAS accepted by producers was reported as landfilled during the 2020 construction season. By accepting 514,00 tons of unprocessed RAS from both PCAS and MWAS sources, asphalt mixture producers saved about 310,000 cubic yards of landfill space.

According to the United States Environmental Protection Agency (U.S. EPA, 2020), about 15.1 million tons of waste shingles are generated annually. Therefore, asphalt mixture producers in 2020 diverted about 3.4 percent of the total available supply of waste shingles from landfills.

The number of companies using RAS increased from 46 in 2019 to 57 during the 2020 construction season. The percentage of producers reporting use of RAS decreased from 22 percent of respondents in 2019 to 21 percent in 2020.

RAS Use by Sector

Figure 10 shows the total estimated amount of RAS used in each of the three sectors of the paving market. These values were calculated using the average percentages of RAS reported by producers for the sectors and adjusted to account for differences between reported RAS tonnage and tons calculated from the percentage by sector. There was a decrease in the tons of RAS used by all sectors from the 2019 to 2020 construction season. All sectors also saw decreases in percentage of RAS use from 2019 to 2020.

Figure 11 shows the average percentage of RAS used by each sector and overall across all asphalt pavement mixtures. These values were calculated using the average percentages of RAS reported for the different sectors and adjusted to account for differences between reported RAS tonnage and tons calculated from the percentage by sector. Although previous years’ surveys saw relatively steady growth across all sectors from 2009 to 2014 with some year-to-year variation, there was a leveling of total RAS use from 2012 to 2015 until a notable decline began

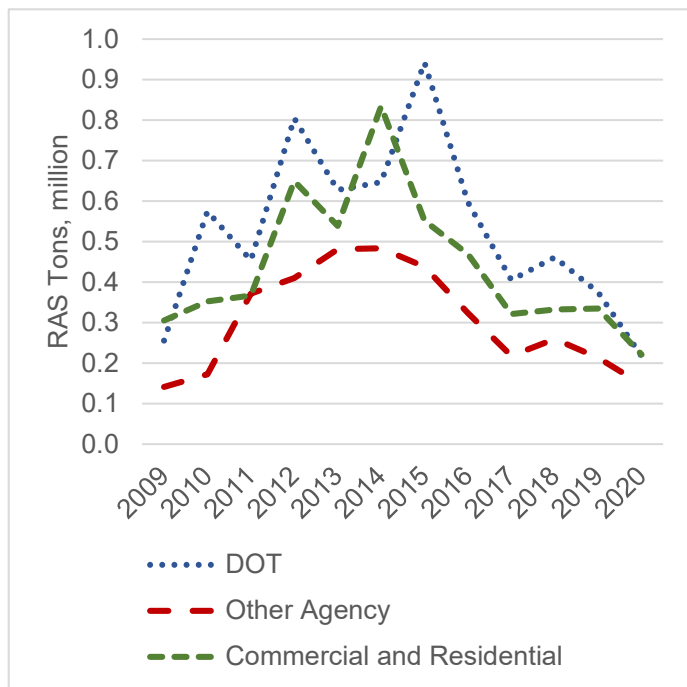


Figure 10: Estimated RAS Use by Sector (Million Tons)

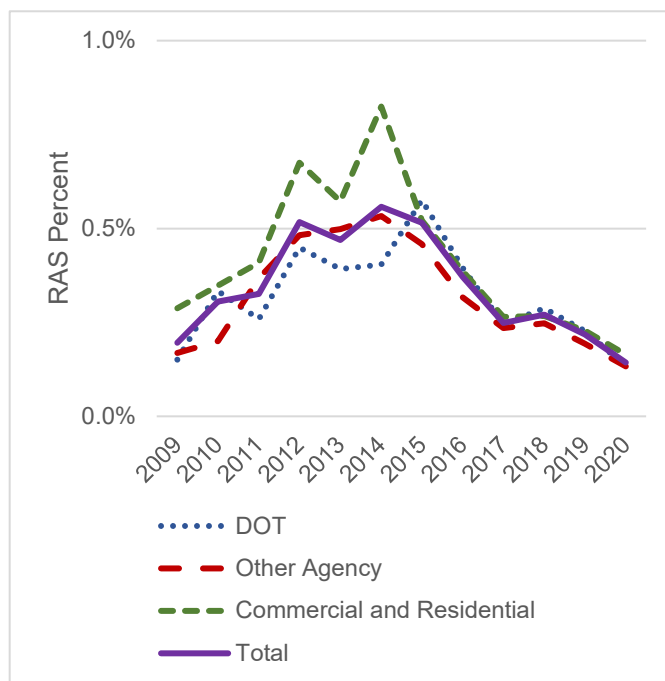


Figure 11: Average Percent RAS Used by Sector

in 2016 and continued into the 2020 season. The average percentage RAS peaked at 0.56 percent in 2012 and started declining from 0.54 percent in 2014 to 0.14 percent in the 2020 construction season.

In 2020, producers and SAPAs were asked which sectors allow RAS to be included in asphalt mixtures. Responses came from 48 states, and this information is summarized in Table 9. In cases where conflicting answers were provided, a middle ground was assumed with SAPA responses being given greater weight regarding the public sectors' RAS use and contractors' responses being given greater weight for the private sector. Most respondents reported that RAS is allowed in at least some mixtures and sectors. According to responses from producers and SAPAs, 30 DOTs reportedly allow RAS in some asphalt pavement mixtures, and four other DOTs allow it in all mixtures. These findings generally align the findings of a 2016 FHWA survey (Aschenbrener, 2017) examining DOT acceptance of the use of RAS. Aschenbrener (2017) also found that five state DOTs — District of Columbia, New Jersey, New York, Pennsylvania, and Massachusetts — allow only the use of MWAS in asphalt pavement mixtures. RAS use is allowed in some Other Agency sector mixtures in 33 states, with no additional states allowing RAS in all mixtures for that sector. Similarly, RAS is allowed in at least some Commercial & Residential sector mixtures in 38 states. There were no reports of states allowing RAS in all mixtures for all sectors, while ten states — Alaska, Arizona, Hawaii, Louisiana, Nevada, New Mexico, North Dakota, Rhode Island, West Virginia, and Wyoming — reportedly do not allow the use of RAS in mixtures for any sector.

Table 9: Sectors Allowing RAS, 2020

State	RAS Allowed In?			State	RAS Allowed In?		
	DOT Mixtures	Other Agency Mixtures	Commercial & Residential Mixtures		DOT Mixtures	Other Agency Mixtures	Commercial & Residential Mixtures
Alabama	Some	Some	Some	Montana	Some	None	None
Alaska	None	None	None	Nebraska	Some	Some	Some
American Samoa	NCR	NCR	NCR	Nevada	None	None	None
Arizona	None	None	None	New Hampshire	Some	Some	Some
Arkansas	Some	Some	Some	New Jersey	Some	None	Some
California	None	Some	Some	New Mexico	None	None	None
Colorado	None	None	Some	New York	All	Some	Some
Connecticut	Some	Some	Some	North Carolina	Some	Some	Some
Delaware	Some	Some	Some	North Dakota	None	None	None
District of Columbia	DNA	DNA	DNA	No. Mariana Isl.	NCR	NCR	NCR
Florida	None	Some	Some	Ohio	Some	Some	Some
Georgia	None	Some	Some	Oklahoma	Some	Some	Some
Guam	NCR	NCR	NCR	Oregon	Some	Some	Some
Hawaii	None	None	None	Pennsylvania	Some	Some	Some
Idaho	None	Some	Some	Puerto Rico	NCR	NCR	NCR
Illinois	All	Some	Some	Rhode Island	None	None	None
Indiana	All	Some	Some	South Carolina	Some	Some	Some
Iowa	Some	Some	Some	South Dakota	None	Some	Some
Kansas	Some	Some	Some	Tennessee	DNA	DNA	DNA
Kentucky	Some	Some	Some	Texas	Some	Some	Some
Louisiana	None	None	None	U.S. Virgin Islands	NCR	NCR	NCR
Maine	Some	None	Some	Utah	None	None	Some
Maryland	Some	Some	Some	Vermont	None	Some	Some
Massachusetts	Some	Some	Some	Virginia	Some	Some	Some
Michigan	Some	Some	Some	Washington	Some	Some	Some
Minnesota	All	Some	Some	West Virginia	None	None	None
Mississippi	None	None	Some	Wisconsin	Some	Some	Some
Missouri	Some	Some	Some	Wyoming	None	None	None

DNA Did Not Answer

NCR No Companies Responding

Table 10: States With Reported RAS Use, 2010–2020

State	RAS Used?											
	2010	2011	2012	2013	2014	2015	2016	2017	2018	2019	2020	
Alabama	Yes	Yes	Yes	Yes	Yes	Yes	Yes	No	Yes	Yes	No	
Alaska	No	No	No	No	No	No	No	No	No	No	No	
American Samoa	NCR	NCR	NCR	NCR	NCR	NCR	NCR	No	No	No	NCR	
Arizona	No	No	No	No	No	No	No	No	No	No	No	
Arkansas	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
California	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Colorado	Yes	Yes	Yes	No	Yes	Yes	Yes	Yes	No	No	No	
Connecticut	No	No	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Delaware	Yes	NCR	Yes	Yes	Yes	Yes	Yes	No	No	NCR	Yes	
District of Columbia	NCR	NCR	NCR	No	NCR	NCR	NCR	No	No	No	No	
Florida	Yes	No	No	Yes	Yes	Yes	No	No	Yes	No	No	
Georgia	No	Yes	Yes	Yes	No	No	Yes	No	No	No	No	
Guam	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	
Hawaii	No	No	No	No	No	No	No	No	No	No	No	
Idaho	No	No	No	No	No	No	No	No	No	No	No	
Illinois	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Indiana	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Iowa	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	No	
Kansas	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Kentucky	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Louisiana	No	No	No	Yes	No	No	Yes	No	No	No	No	
Maine	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Maryland	Yes	Yes	Yes	Yes	Yes	Yes	No	Yes	No	Yes	Yes	
Massachusetts	Yes	Yes	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Michigan	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Minnesota	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Mississippi	No	Yes	Yes	Yes	Yes	Yes	Yes	No	No	No	No	
Missouri	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Montana	No	No	No	No	No	No	No	No	No	No	No	
Nebraska	NCR	No	Yes	Yes	No	No	Yes	No	No	No	No	
Nevada	Yes	No	No	No	No	No	Yes	Yes	No	No	No	
New Hampshire	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
New Jersey	No	No	No	Yes	No	No	No	No	No	Yes	No	
New Mexico	NCR	No	NCR	No	No	NCR	Yes	Yes	No	No	No	
New York	Yes	Yes	Yes	Yes	Yes	Yes	No	Yes	No	No	No	
North Carolina	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
North Dakota	NCR	No	NCR	No	No	No	No	No	No	No	No	
N. Mariana Islands	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	
Ohio	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Oklahoma	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Oregon	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Pennsylvania	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Puerto Rico	No	No	No	No	NCR	No	NCR	NCR	NCR	NCR	NCR	
Rhode Island	No	No	No	No	No	No	No	No	No	No	No	
South Carolina	No	Yes	No	Yes	Yes	No	Yes	No	No	Yes	Yes	
South Dakota	No	Yes	Yes	Yes	Yes	NCR	Yes	No	NCR	NCR	No	
Tennessee	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	No	
Texas	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
U.S. Virgin Islands	NCR	NCR	NCR	NCR	NCR	NCR	NCR	NCR	No	NCR	NCR	
Utah	No	No	No	No	No	No	No	No	No	No	No	
Vermont	No	No	Yes	Yes	Yes	Yes	No	Yes	Yes	Yes	No	
Virginia	No	Yes	Yes	Yes	Yes	Yes	Yes	No	Yes	No	No	
Washington	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
West Virginia	Yes	No	No	No	No	No	No	No	No	No	No	
Wisconsin	No	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	Yes	
Wyoming	No	No	No	Yes	No	No	Yes	No	No	No	No	
NCR	= No Companies Responding											
Yes	= RAS Use Reported											
No	= No RAS Use Reported											

NCR = No Companies Responding
 Yes = RAS Use Reported
 No = No RAS Use Reported

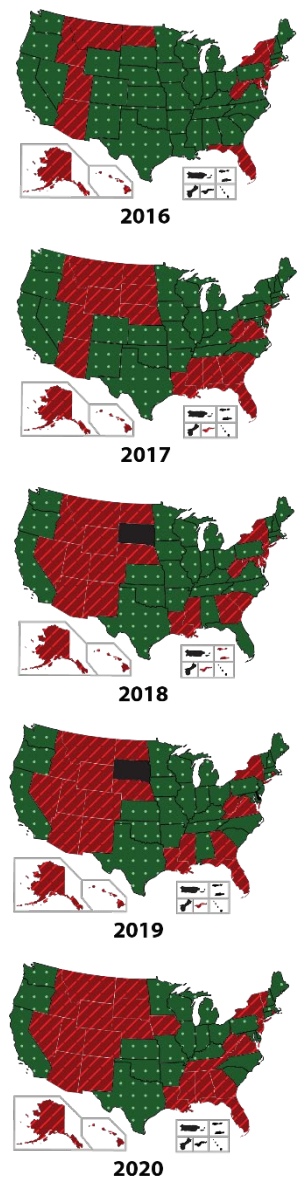


Figure 12: States with Companies Reporting RAS Use by Construction Season, 2016–2020

RAS Use in Each State

Table 10 shows states where asphalt pavement mixture producers reported using RAS in 2010 through 2020, and Figure 12 shows states where producers reported using RAS from 2016 through 2020. Red indicates a state where RAS use was not reported for that construction season. The number of states where producers reported using RAS increased annually from 22 in 2009 to 38 in 2013, but decreased to 34 in 2014, 32 in 2015, 29 in 2017, 27 in 2018 and 28 in 2019. During the 2020 construction season, asphalt mixture producers in 24 states report RAS use. Iowa producers for the first time since the beginning of the survey reported no RAS use, while still reporting that RAS is allowed in some mixtures for all sectors.

RAS Stockpiles

In 2020, 93 percent of the 57 producers using RAS reported having inventories of stockpiled RAS, compared to 87 percent of the 46 producers using RAS in 2019. Some 1.272 million tons of RAS was reported as stockpiled at year-end 2020, a (11.3 percent) increase from the 1.143 million tons of RAS in stockpiles at the end of 2019. The reported RAS stockpiled represents about 2.2 years of inventory at 2020 utilization levels.

Table 11: Reported Tons of RAS Stockpiled, 2019–2020

State	Reported Tons Stockpiled (Thousands)		Estimated Tons Stockpiled (Thousands)		State	Reported Tons Stockpiled (Thousands)		Estimated Tons Stockpiled (Thousands)	
	2019	2020	2019	2020		2019	2020	2019	2020
Alabama	15.0	0.0	30.5	0.0	Montana	*	*	*	*
Alaska	*	*	*	*	Nebraska	*	0.0	*	0.0
American Samoa	*	NCR	*	NCR	Nevada	*	0.0	*	0.0
Arizona	0.0	0.0	0.0	0.0	New Hampshire	*	0.0	*	0.0
Arkansas	10.8	4.7	28.1	9.6	New Jersey	0.0	0.0	0.0	0.0
California	3.3	0.0	10.9	0.0	New Mexico	*	*	*	*
Colorado	0.0	0.0	0.0	0.0	New York	0.0	0.0	0.0	0.0
Connecticut	0.2	*	0.4	*	North Carolina	115.5	179.0	224.4	217.0
Delaware	NCR	*	NCR	*	North Dakota	*	*	*	*
District of Columbia	*	*	*	*	No. Mariana Isl.	NCR	NCR	NCR	NCR
Florida	0.0	0.0	0.0	0.0	Ohio	24.4	29.0	42.4	44.2
Georgia	*	0.0	*	0.0	Oklahoma	5.0	75.2	14.1	100.9
Guam	NCR	NCR	NCR	NCR	Oregon	1.0	27.5	2.8	68.1
Hawaii	0.0	*	0.0	*	Pennsylvania	5.0	62.1	39.7	187.4
Idaho	0.0	0.0	0.0	0.0	Puerto Rico	NCR	NCR	NCR	NCR
Illinois	0.2	14.1	1.8	24.2	Rhode Island	*	*	*	*
Indiana	16.5	15.9	47.1	27.6	South Carolina	7.0	15.0	18.7	32.8
Iowa	6.2	0.0	25.1	0.0	South Dakota	NCR	*	NCR	*
Kansas	*	5.5	*	8.0	Tennessee	8.5	0.0	10.4	0.0
Kentucky	40.0	10.5	96.5	24.7	Texas	42.0	23.5	286.5	158.2
Louisiana	0.0	0.0	0.0	0.0	U.S. Virgin Isl.	NCR	NCR	NCR	NCR
Maine	*	0.1	*	0.1	Utah	0.0	0.0	0.0	0.0
Maryland	7.0	13.0	29.6	17.8	Vermont	*	*	*	*
Massachusetts	22.2	60.9	68.3	136.5	Virginia	0.0	0.0	0.0	0.0
Michigan	1.0	1.0	1.9	1.5	Washington	3.5	9.5	5.0	10.1
Minnesota	12.6	1.0	24.6	1.7	West Virginia	0.0	0.0	0.0	0.0
Mississippi	0.0	0.0	0.0	0.0	Wisconsin	46.2	50.7	63.9	63.4
Missouri	42.5	4.0	105.9	17.0	Wyoming	*	*	*	*
Total†						437.9	605.3	1143.0	1272.3

NCR No Companies Responding

* Fewer than 3 Companies Reporting

† Includes Values from States with Fewer than 3 Companies Reporting

Table 11 shows the reported and estimated amount of RAS stockpiled in each state at the end of the 2019 and 2020 construction seasons. To calculate the estimated values, reported tons of RAS stockpiled were divided by the ratio of total reported tons of mix produced to estimated tons of mix produced. The total tonnage row in Table 11 includes stockpiled tonnages from states with fewer than three producers reporting.

RAS Recycling Agent Use

Table 12 shows the percentage of reported tons of RAS-containing mixtures produced using softer binder or recycling agents in each state. **These results are representative *only* of the survey participants and do not completely reflect practices in a given state.** Similar to the RAP, there does not appear to be a relationship between the amount of RAS mixtures using softer binder and/or recycling agents and percentage of RAS used by the state.

Table 12: Percentage of RAS Mixtures Using Softer Binder and/or Recycling Agents in Each State, 2020

State	Softer Binder	Recyc. Agent	State	Softer Binder	Recyc. Agent	State	Softer Binder	Recyc. Agent
Alabama	0%	0%	Kentucky	50%	0%	Ohio	100%	0%
Alaska	*	*	Louisiana	0%	0%	Oklahoma	75%	28%
American Samoa	NCR	NCR	Maine	0%	0%	Oregon	0%	99%
Arizona	0%	0%	Maryland	100%	0%	Pennsylvania	33%	0%
Arkansas	0%	0%	Massachusetts	25%	0%	Puerto Rico	NCR	NCR
California	20%	20%	Michigan	50%	0%	Rhode Island	*	*
Colorado	0%	0%	Minnesota	10%	2%	South Carolina	0%	100%
Connecticut	*	*	Mississippi	0%	0%	South Dakota	*	*
Delaware	*	*	Missouri	100%	0%	Tennessee	0%	0%
Dist. of Columbia	*	*	Montana	*	*	Texas	0%	0%
Florida	0%	0%	Nebraska	0%	0%	U.S. Virgin Isl.	NCR	NCR
Georgia	0%	0%	Nevada	0%	0%	Utah	0%	0%
Guam	NCR	NCR	New Hampshire	0%	0%	Vermont	*	*
Hawaii	*	*	New Jersey	0%	0%	Virginia	0%	0%
Idaho	0%	0%	New Mexico	*	*	Washington	33%	40%
Illinois	35%	0%	New York	0%	0%	West Virginia	0%	0%
Indiana	25%	0%	North Carolina	100%	25%	Wisconsin	30%	21%
Iowa	0%	0%	North Dakota	*	*	Wyoming	*	*
Kansas	68%	0%	No. Mariana Isl.	NCR	NCR			
Average, When Used [†]							24%	8%

NCR No Companies Responding for the State to the Survey

* Fewer than 3 Companies Reporting

[†] Includes Values from States with Fewer than 3 Companies Reporting

Although the data is highly dependent upon the companies responding to the survey each year, in states where RAS is reportedly used, the average percentage of RAS mixtures incorporating softer binders was 24 percent during the 2020 construction season, while the percentage of RAS mixtures incorporating recycling agents was at 8 percent. In 2019, producers reported a lower average percentage (20 percent) of RAS mixtures incorporating softer binders and the same average percentage (8 percent) of RAS mixtures incorporating recycling agents, as compared to the 2020 construction season.

The Importance of Engineering Recycled Asphalt Mixtures for Quality

For more than three decades, two guiding principles of asphalt recycling have been: asphalt mixtures containing recycled materials should 1) meet the same requirements as asphalt mixtures with all virgin materials, and 2) perform equal to or better than asphalt mixtures with all virgin materials. This is at the heart of the “Three E’s of Recycling,” which state that recycled materials should provide Environmental, Economic, and Engineering benefits.

Quality recycled mixtures have been successfully designed and produced for many years. When successfully engineered, designed, produced, and constructed, the proof is in performance. A recent study comparing the performance of recycled versus virgin mixtures based on Long-Term Pavement Performance (LTPP) data from 16 U.S. states and two Canadian provinces shows that overlays containing at least 30 percent RAP performed equal to overlays using virgin mixtures (Carvalho et al., 2010; West et al., 2011). At the NCAT Test Track, test sections containing 50 percent RAP using Superpave mixture design procedures for each layer outperformed companion test sections with all virgin materials in all pavement performance measures.

However, as the amount of recycled materials in asphalt pavement mixtures increase, additional considerations for material handling, engineering, mixture design, quality, and performance testing become more important. In particular, RAP and RAS should be tested and classified to determine the amount, properties, and quality of available asphalt binder. These values have an impact on pavement performance and are important to assess when developing a high recycled content mixture design. In some cases, it may be necessary to make use of recycling agents or a softer asphalt binder to ensure the final mixture design delivers the desired level of product performance.

For more information about processing and using reclaimed asphalt pavement and recycled asphalt shingles, consult the NAPA publication *Best Practices for RAP and RAS Management* (Quality Improvement Series 129).

Cost Savings from RAP and RAS

The use of RAP and RAS both reduce the need for virgin materials, conserving valuable asphalt and aggregates. Beyond the environmental benefits of resource preservation, the use of RAP and RAS can help lower initial material costs for road construction, allowing road owners to achieve more roadway maintenance and construction activities within limited budgets. Table 13 summarizes the individual and cumulative savings from the use of RAP and RAS in asphalt mixtures realized during the 2020 construction season. In total, the use of RAP and RAS saved more than \$3.0 billion during the 2020 construction season compared to the use of all virgin materials. This is \$380 million less than in 2019 due to decreases in asphalt binder prices (Table 14) and reduced total asphalt mixture tonnages in 2020.

Table 13: Material Savings, 2019–2020

Material	Material Quantity, Million Tons		% Agg.	% AC	Aggregate Cost Savings, \$ Billion		Asphalt Binder Cost Savings, \$ Billion		Total Cost Savings, \$ Billion	
	2019	2020			2019	2020	2019	2020	2019	2020
RAP	89.2	87.0	95	5	\$0.916	\$0.894	\$2.375	\$2.061	\$3.291	\$2.955
RAS	0.921	0.586	50*	20	\$0.005	\$0.003	\$0.098	\$0.056	\$0.103	\$0.059
Total					\$0.921	\$0.898	\$2.473	\$2.116	\$3.394	\$3.014

* Includes granules and mineral filler

The estimated savings shown in Table 13 were based on the cost factors shown in Table 14. Asphalt binder prices were estimated based upon an average of publicly available 2020 asphalt price indexes for 37 states (see Figure 14). The average price of unmodified asphalts from these states for 2020 was about \$442.35 per ton, down from the 2019 average price of \$500.38. Five of the states (Alabama, Connecticut, Florida, Louisiana, and Virginia) also provide price indexes for

modified asphalts. The average modified asphalt prices from these states for 2020 was \$572.89 per ton, down from \$646.63 in 2019. Assuming 10 percent of asphalt mixtures use modified asphalt binders, the 2020 average price of asphalt binders used in asphalt mixtures was \$473.72 per ton, down 11.0 percent from 2019.

Most asphalt mixtures today use crushed stone as the primary aggregate, but they often include a small percentage of natural sand. The U.S. Geological Survey (USGS) reports the average price of Stone (Crushed) decreased to \$11.06 per ton and Sand and Gravel (Construction) increased to \$8.70 per ton for 2020 (USGS, 2021). Assuming the average asphalt pavement mixture contains 10 percent natural sand and 90 percent crushed stone, the average price of aggregate in an asphalt mixture was \$10.82 per ton for the 2020 construction season, up 0.1 percent from 2019.

Table 14: Material Cost Factors, 2017–2020

Material		% of Market	Cost/Ton			
			2017	2018	2019	2020
Asphalt	Unmodified	90	\$361.93	\$468.93	\$500.38	\$442.35
	Modified	10	\$480.04	\$595.98	\$646.63	\$572.89
	Weighted Average		\$390.44	\$481.90	\$532.46	\$473.72
Aggregate	Crushed Stone	90	\$10.39	\$10.76	\$11.12	\$11.06
	Sand and Gravel	10	\$7.84	\$8.29	\$8.01	\$8.70
	Weighted Average		\$10.13	\$10.51	\$10.81	\$10.82

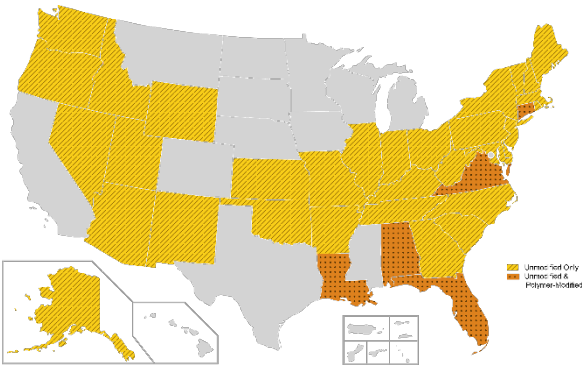


Figure 13: States With Publicly Available Asphalt Price Indexes, 2020

Minor additional cost savings, not calculated for this report, are associated with the use of RAS in stone-matrix asphalt and other specialty asphalt mixtures where shingle fibers may potentially replace mineral or cellulose fibers.

Additional cost savings are realized by diverting RAP and RAS from landfills. The national average gate fee for disposing of mixed construction and demolition (C&D) material in landfills is relatively close to the national average for municipal solid waste (MSW) landfill disposal (Tolaymat et al., 2017). Based upon a 2020 national average for MSW landfill gate fees of \$53.72 per ton, not sending more than 87 million tons of RAP and RAS to landfills (nearly 59 million cubic yards of material) saved more than \$4.7 billion dollars in gate fees, down from \$5.3 billion in 2019, due in part to a 3.0 percent decrease in MSW gate fees from 2019 to 2020 (Boxman & Staley, 2021).

Warm-Mix Asphalt Technology

Table 4 includes the national summary of WMA technology usage data from the 2019 and 2020 construction season surveys. The information requested in the survey is detailed in Appendix A and summarized in Table A1, Section 4. State-level data is reported in Appendix B. Producers were also asked about the different WMA technologies used.

Prior to the 2018 construction season, producers were asked to report primarily the use of WMA technologies to reduce production temperatures by at least 10°F from typical mixture production temperatures. However, because of potential compaction, antistripping, and workability benefits, the use of WMA technologies at HMA temperatures is common. To better understand the use of WMA technologies at different temperatures, the 2018, 2019, and 2020 construction season surveys asked additional questions to ensure disaggregation of WMA technology use at different temperatures. The results indicate that prior survey reports have better captured the use of WMA technologies than the use of WMA technologies at reduced temperature. Table 4 and this section report both aggregated data on the use of WMA technologies and disaggregated data on its use by mixture temperature where possible.

The percentage of companies reporting the use of WMA technologies saw rapid increases from the 2009 to 2011 construction seasons, but has gradually declined from 78 percent of respondents in 2015 to 62 percent of respondents in the 2019 and rebounding to 67 percent for the 2020 construction season, as shown in Figure 15. Increases in tonnage with WMA technologies as a percent of total tonnage have generally plateaued between 2013 and 2016, as seen in Figure 16. The 2020 construction season had a 13 percent increase in the production of asphalt with WMA technologies to 186.4 million tons, 45.7 percent of total asphalt pavement tonnage. A total of 184 companies, 67 percent of respondents, reported using WMA technologies during the 2020 construction season.

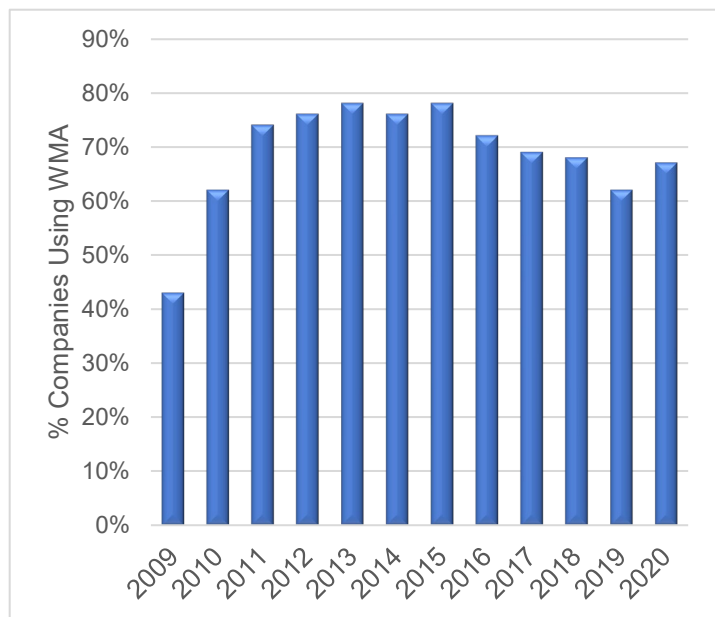


Figure 14: Percent of Companies Using WMA Technologies

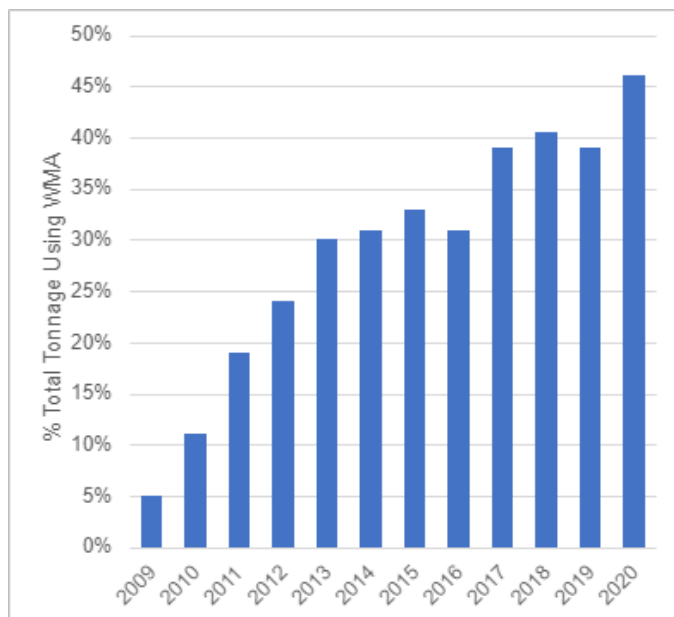


Figure 15: Percent Total Tonnage Produced Using WMA Technologies

WMA Technology Use by Sector

Figure 16 shows a steady increase in the number of tons of mixture produced using WMA technologies for each customer sector from 2011 to 2013, with use showing minor changes for the 2014 through 2016 construction seasons. In 2017, however, WMA technology use grew substantially due to notable increases in mixtures produced for the DOT and Commercial & Residential sectors. During 2018, growth in tonnage produced with WMA technologies was driven largely by a 58 percent increase in tons produced for the Other Agency sector. In 2019, tons produced with WMA technology in the Other Agency sector was down, while the DOT and the Commercial & Residential sectors were up from the 2018 construction season. Mix tonnages increased in all sectors during the 2020 construction season when compared to 2019. All in all, during the 2020 construction season, 51.9 percent of all DOT sector tonnage, 45.2 percent of Other Agency sector tonnage, and 38.6 percent of Commercial & Residential sector tonnage was produced using WMA technologies.

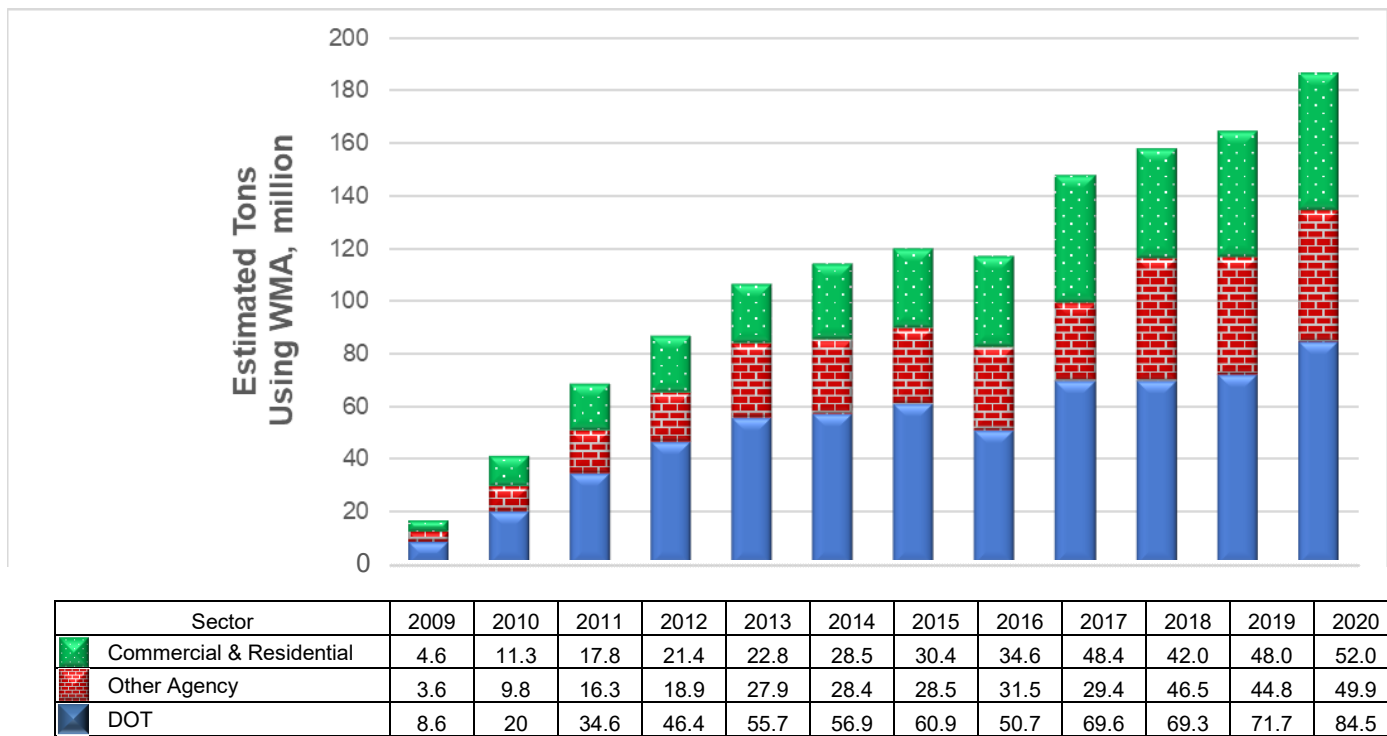


Figure 16: Estimated Tons (Millions) Produced With WMA Technologies by Sector, 2009–2020

WMA Technology Use in Each State

Figure 17 shows the estimated percentage of total tons produced as WMA in each state. The national trend from 2009 through 2020 shows increased tons of asphalt mixture produced with WMA technologies; however, a degree of fluctuation year-to-year is seen at the state level. The accuracy of data for individual states varies noticeably depending on the number of responses received from each state and the total number of tons represented by the respondents each year.

From 2019 to 2020, 22 states saw an increase of 10 percentage points or more in WMA production, while 13 states had a decrease of 10 percentage points or more. Nine states — Alaska, Arkansas, Colorado, Connecticut, Georgia, New Hampshire, North Carolina, Vermont, and West Virginia — had an increase of 30 percentage points or more in mixture production with WMA technologies. Eight states — California, Kansas, Maine, Missouri, Nebraska, Nevada, North Dakota, and Wyoming — had a decrease of 30 percentage points or more in mixture production with WMA technologies.

Mixture production with WMA technologies made up over half of the total asphalt mixture production in 23 states during 2020, ten of these states — Colorado, Connecticut, Kentucky Louisiana, Mississippi, New Hampshire, Pennsylvania, Utah, Vermont, and West Virginia — reported WMA as 75 percent or more of total production in 2020. Hawaii, Montana, and Rhode Island had no reported asphalt production with WMA technologies in 2020.

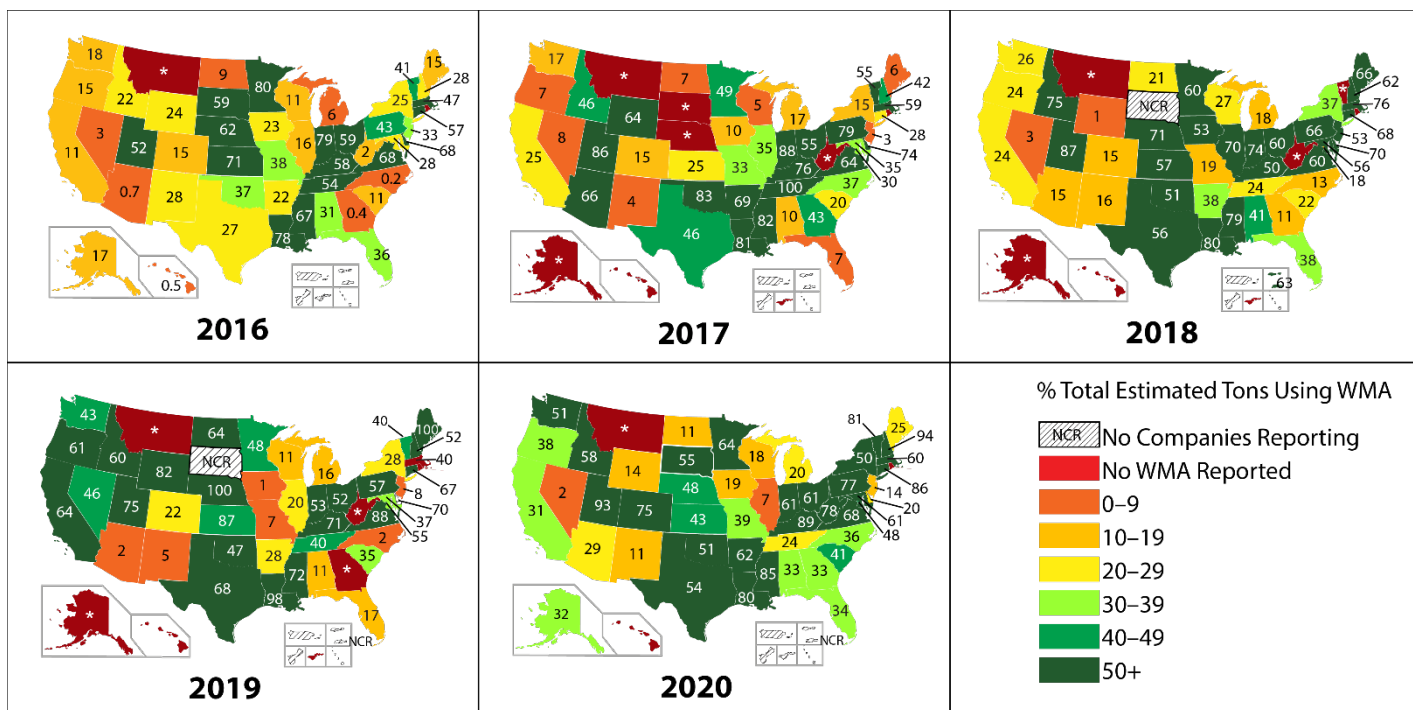


Figure 17: Estimated Percent of Total Production Using WMA Technologies in Each State, 2016–2020

WMA Technologies

As Table 15 and Figure 18 show, production plant foaming remains the most commonly used WMA production technology, being used for around 49 percent of the WMA produced in 2020. This is a decrease of about 1.8 percent from the 2019 season. The use of chemical additive technologies at 46.6 percent represents a 1.7 percent decrease for the 2020 construction season compared to 2019. Organic additives represented 1.6 percent of the market. Additive foaming was 2.6 percent of the market during 2020. The percentage of WMA produced with additive technologies has grown significantly since 2011 when they made up less than 5 percent of the WMA technologies used, and plant-based foaming has seen a general decrease over the same time period.

Table 15: Percent Production of WMA Technologies, 2009–2020

WMA Technology	% Production											
	2009	2010	2011	2012	2013	2014	2015	2016	2017	2018	2019	2020
Production Plant Foaming %	83.0%	92.0%	95.4%	88.3%	87.0%	84.5%	72.0%	76.9%	64.7%	63.2%	51.0%	49.2%
Additive Foaming %	2.0%	1.0%	0.2%	2.0%	0.3%	0.0%	2.1%	0.0%	0.0%	0.7%	0.0%	2.6%
Chemical Additive %	15.0%	6.0%	4.1%	9.4%	12.1%	15.0%	25.2%	21.1%	32.2%	34.3%	48.3%	46.6%
Organic Additive %	0.3%	1.0%	0.3%	0.2%	0.0%	0.5%	0.7%	1.9%	3.1%	1.8%	0.7%	1.6%

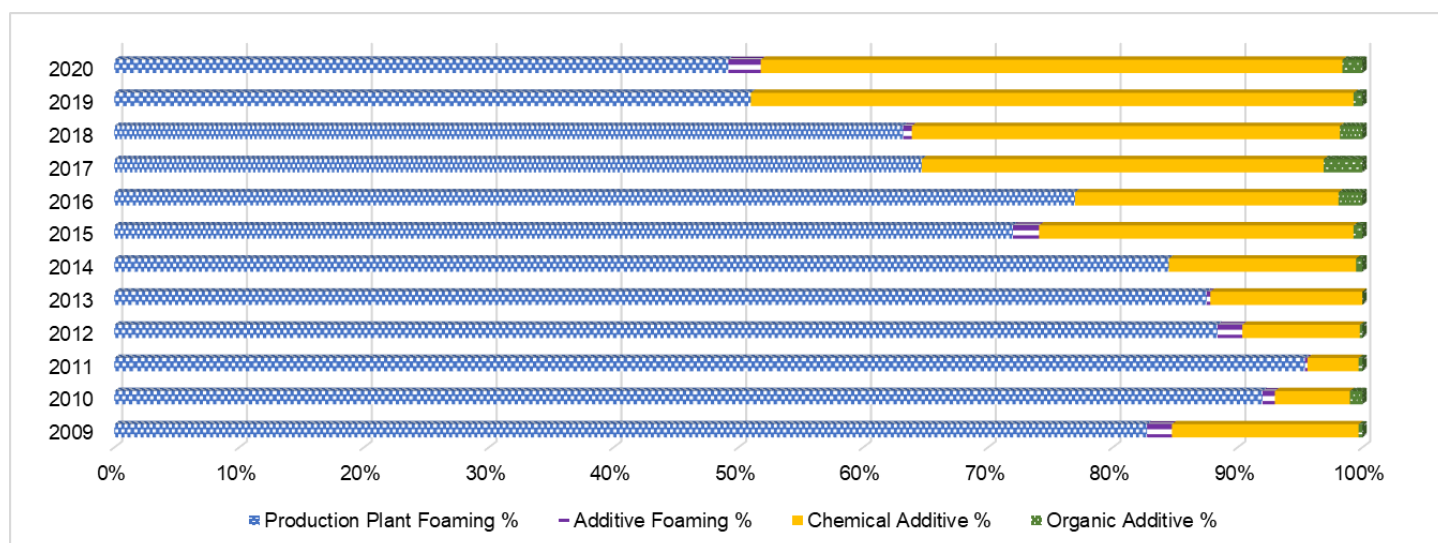


Figure 18: WMA Technologies Used as Percent of WMA Production, 2009–2020

Use of WMA Technologies at Different Temperatures

WMA additives can have compaction, workability, antistrip, and other benefits that encourage their use even when a reduction in production temperature is not sought or achieved by the producer. For this reason, producers were asked to report use of WMA technologies for asphalt production both at traditional HMA temperatures and at reduced temperatures. About 49.9 percent (93.1 million tons) of total tonnage produced using WMA technologies was produced with a temperature reduction of at least 10°F.

Of the respondents, 184 producers in 46 states, reported using WMA technologies. Of these, 89 producers reporting using WMA technologies at both reduced and HMA temperatures; 60 producers used WMA technologies only at reduced temperatures; and 35 producers reported using WMA technologies only at HMA temperatures.

Table 16 shows the percentage of reported tons produced using each WMA technologies at both reduced temperatures and at traditional HMA temperatures, along with the total tonnages produced with WMA technologies. While there is variation in the utilization of different WMA technologies at different production temperatures, producers reporting the use of WMA technologies at all temperatures typically did not report varying the technology by temperature. Therefore, much of the difference between the Reduced Temperatures and the HMA Temperatures columns in Table 16 is attributable to the technologies employed by producers that only utilize WMA technologies at either reduced temperatures or HMA temperatures.

The national average of the responses is shown in Table 16.

Table 16: WMA Technologies Utilization Detail, 2020

WMA Technology	% of Market		
	Reduced Temperatures	HMA Temperatures	At All Temperatures
Chemical Additive	44.0%	49.2%	46.6%
Plant Foaming	54.5%	44.0%	49.2%
Additive Foaming	0.3%	4.8%	2.6%
Organic Additive	1.2%	2.0%	1.6%
2020 Tons (Millions)	93.1	93.3	186.4

Energy and Greenhouse Gas Emission Benefits from WMA and RAP

Energy and greenhouse gas (GHG) emission benefits from use of WMA technologies to produce asphalt mixtures at reduced temperature and use of RAP in new asphalt mixtures are estimated to provide contextual information regarding the potential environmental impacts of these industry practices. These calculations are based on publicly available data and emission factors published by government agencies, industry, and non-governmental organizations. A detailed overview of the methodology and assumptions used to calculate energy and greenhouse gas (GHG) emission benefits is provided in Appendix C. GHG emissions are reported in million metric tonne (MMT) of CO₂-equivalent (CO₂e) emissions to be consistent with emission inventories published by the U.S. EPA and other government agencies.

Energy and GHG Emission Benefits from Production of WMA at Reduced Temperature

To estimate reductions in energy consumption and GHG emissions associated with the production of WMA at reduced temperature, we start by estimating the average temperature reduction achieved by plants that reduce mix production temperature when using WMA technologies. We then estimate the expected energy savings (Btu) from reduced temperature, convert that to fuel volume (natural gas), and use emission factors to estimate the combustion-related GHG emission reduction from producing WMA at reduced temperature. Two scenarios for mix production temperature were evaluated. The conservative and optimistic scenarios assume average reductions in mix production temperature of 10 °F and 40 °F, respectively.

The estimated reductions in energy consumption and GHG emissions for WMA produced at reduced temperature are provided in Table 17. The data in Table 17 are rounded to two significant digits to reflect the underlying uncertainties and approximate level of precision for these estimates. The calculated reduction of GHG emissions from production of WMA at reduced temperature is 0.06 or 0.25 MMT for the conservative and optimistic scenarios for mix production temperature, respectively. The assumptions for the energy consumption and GHG emission reductions are explained in Appendix C.

Table 17: Estimated GHG emission reduction for three scenarios of WMA produced at reduced temperature

Scenario	Mix Production Energy Reduction (thousand MMBtu)	GHG Emission Reduction (MMT CO ₂ e)	Equivalent Number of Passenger Vehicles ¹
Conservative (10° F temp Reduction)	930	0.06	13,000
Optimistic (40° F temp Reduction)	3,700	0.25	54,000

1. Assumes that each vehicle emits 4.6 tonne CO₂e/yr (U.S. EPA, 2018).

Upstream GHG emission burdens for producing WMA at reduced temperature are not included in Table 17 because either the quantity is insignificant (as is the case for foamed asphalt) or insufficient data are publicly available to confidently estimate these emission burdens (as is the case for chemical and organic additives). Considerations regarding the upstream GHG emission burdens for producing WMA at reduced temperature are provided in Appendix C.

GHG Emission Benefits from Use of RAP

A summary of GHG emission reductions and burdens from use of RAP is provided in Table 18. Net reduction of GHG emissions from use of RAP in new asphalt mixtures in 2019 is estimated to be 2.3 million tonne CO₂e, equivalent to the annual emissions from approximately 510,000 passenger vehicles. The data in Table 18 are rounded to two significant digits to reflect the underlying uncertainties and approximate level of precision for these estimates. The underlying assumptions for calculating the GHG emission reductions and burdens from use of RAP in new asphalt mixtures are explained in Appendix C.

Table 18: Summary of GHG Emission Reductions and Burdens from use of RAP in New Asphalt Mixtures in 2020 (MMT CO₂e)

Description	GHG Reduction (Burden)
Avoided Emissions	
Asphalt Binder Replacement	2.5
Aggregate Replacement	0.35
Transportation of Asphalt Binder and Aggregates	0.45
Subtotal Avoided Emissions	3.3
Emission Burdens	
RAP Processing	(0.11)
Transportation of RAP	(0.88)
Subtotal Emission Burdens	(0.99)
Net GHG Emissions Reduction	2.3
Equivalent Number of Passenger Vehicles¹	510,000

¹ Assumes that each vehicle emits 4.6 tonne CO₂e/yr (U.S. EPA, 2018).

Annual and cumulative GHG emission reductions from use of RAP in new asphalt mixtures from previous years of survey data are provided in Figure 19. The cumulative reduction of GHG emissions from use of RAP in new asphalt mixtures for the period 2009-2020 is estimated to be 23.5 million tonne CO₂e.

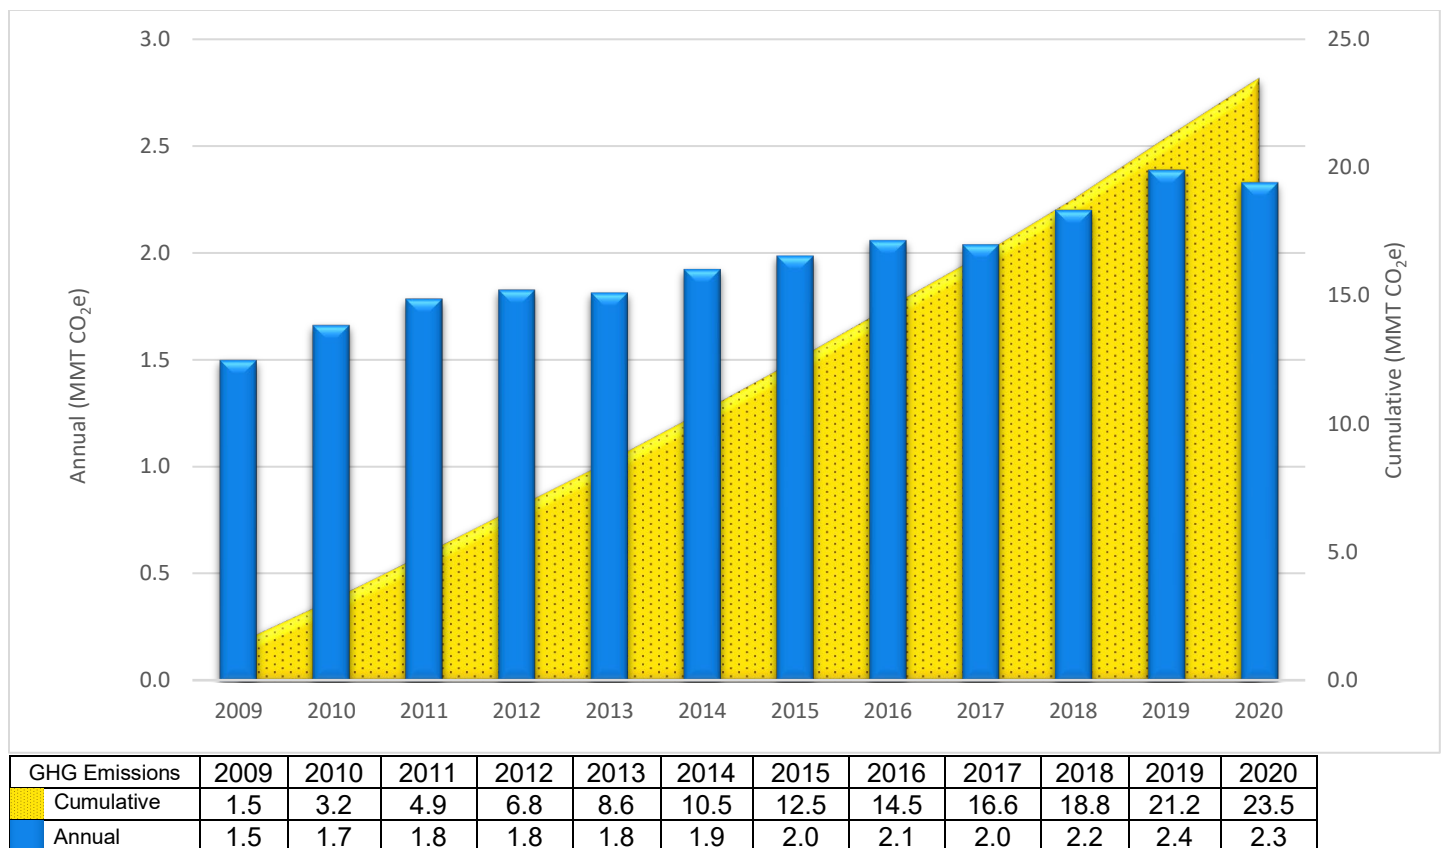


Figure 19: GHG Emissions Reduction from Use of RAP in New Asphalt Mixtures, 2009–2020

Other Recycled Materials

Starting with the 2012 construction season survey, a series of questions was asked about the use of other recycled materials in asphalt mixtures. The information requested in the survey is detailed in Appendix A and summarized in Table A1, Section 5.

Producers were asked how many tons of mixture were produced that incorporated other recycled materials, as well as how many tons of specific materials were used in mixture production during the 2020 construction season. In some cases, respondents provided only the tons of asphalt mixture produced using other recycled materials or only the tons of the other recycled materials used, not both. Four recycled materials — recycled tire rubber (RTR), steel slag, blast furnace slag, and cellulose fibers — were specifically listed in the survey. Respondents could specify up to two additional recycled materials used in mixtures.

Because the response rate to these questions about other recycled materials was expected to be low and because producers may not track the use of these materials, state and national estimates of total quantities used for these materials were not calculated. **All values in this section are reported values only and do not represent estimates of the total quantity of these materials used in each state or nationally.** Year-to-year variation in reported values is entirely dependent upon the makeup of the respondents to each year's survey. Where available, third-party data is referenced to provide an understanding of the estimated total usage of these materials.

A total of 70 companies from 28 states, 25.5 percent of survey respondents, reported using more than 900,000 tons of other recycled materials in about 9.1 million tons of asphalt mixtures during the 2020 construction season.

Recycled Tire Rubber

Table 19 summarizes reported information on the use of RTR, also referred to as ground tire rubber (GTR). Eighteen producers from 10 states reported using RTR in some asphalt mixtures. Information about the use of RTR in surface treatments, such as chip seals, was not within the scope of this survey. About 40 percent of the total reported asphalt mixture tonnage produced using RTR came from California, where legislative mandates require the wide-spread use of RTR in asphalt pavements (Caltrans, 2017). The total reported tons of asphalt mixture using RTR increased approximately 10 percent to 1,343,406 tons (about 0.33 percent of total reported tons for 2020) in the 2020 construction season survey, which was supported by the increase in producers responding to the 2020 survey.

While the tonnage produced that incorporates RTR is relatively straightforward to track and report, the tons of RTR used is harder to document due to different methods of producing mixtures that incorporate RTR and the likelihood that RTR is either preblended with binder at the terminal or blended onsite by a third party. Given these factors, producer reports of tons of RTR used versus tons of asphalt mixture produced using RTR were given a heightened level of scrutiny to determine if the reported data was within a reasonable range. When reported tons of RTR fell outside the expected range, producers were contacted to obtain correct values.

To give a picture of the total market size for RTR, the U.S. Tire Manufacturers Association (USTMA) reports that 24.4 percent of U.S. scrap tires were processed into an estimated 1 million tons of RTR in 2019. Of this, about 17 percent (180,000 tons) of RTR was used in asphalt pavement mixtures and surface treatments, such as seal coats, in 2019 (USTMA, 2020). USTMA conducts its scrap tire analysis biennially, so the 2019 data is the most current USTMA annual estimate, the RTR use reported by 2020 construction season survey respondents makes up nearly 11 percent of the total RTR estimated by USTMA as used in asphalt pavement mixtures and surface treatments.

Table 19: Reported Tons of Asphalt Mixtures Using Recycled Tire Rubber and Reported Tons of RTR Used, 2016–2020

State	Reported Tons of Asphalt Mixtures Using RTR					Reported Tons of RTR Used				
	2016	2017	2018	2019	2020	2016	2017	2018	2019	2020
Arizona	273,200	242,000	342,000	251,350	214,408	3,412	4,600	4,303	2,554	1,689
Arkansas	—	—	1,000	—	—	—	—	5	—	—
California	1,042,976	407,500	953,444	706,014	542,718	15,840	5,765	13,412	8,587	8,901
Delaware	8,000	—	2,500	—	—	40	—	10	—	—
Florida	32,288	22,392	9,895	—	—	135	145	136	—	—
Georgia	50,000	—	63,626	6,667	200,000	200	—	378	33	1200
Illinois	15,500	—	125,000	—	15,400	79	—	750	—	100
Indiana	—	—	—	—	—	—	—	—	—	—
Kentucky	—	3,000	—	1,000	—	—	20	—	5	—
Louisiana	—	5,000	—	—	—	—	35	—	—	—
Massachusetts	71,500	145,333	77,000	145,218	172,380	841	1,603	710	2,463	2,998
Michigan	1,350	12,500	4,500	3,500	80,000	0.7	125	55	5	3,000
Missouri	—	100,000	36,000	30,000	25,000	—	1,500	260	1,500	157
Nevada	—	23,000	—	—	—	—	275	—	—	—
New Hampshire	365	—	—	—	—	—	—	—	—	—
New Mexico	15,000	—	—	—	—	—	—	—	—	—
Ohio	—	6,300	—	—	—	—	65	—	—	—
Oklahoma	—	—	—	—	15,000	—	—	—	—	12
Oregon	6,000	—	—	—	—	—	—	—	—	—
Pennsylvania	5,260	—	—	40,000	69,000	25	—	—	160	890
South Carolina	10,000	—	—	—	—	18	—	—	—	—
Tennessee	10,000	—	—	—	—	50	—	—	—	—
Texas	—	11,000	6,280	5,500	9,500	—	40	98	52	78
Utah	—	—	—	—	—	—	—	—	—	—
Virginia	—	1,200	—	34,000	—	—	13	—	156	—
Washington	—	—	—	—	—	—	—	—	—	—
Wisconsin	—	—	—	—	—	—	—	—	—	—
Total	1,541,439	974,725	1,621,245	1,223,249	1,343,406	20,641	14,186	20,117	15,515	19,025
No. of Companies	26	19	21	14	18					

NCR = No Companies Responding

— = No Use Reported

Steel & Blast Furnace Slag

Table 20 summarizes the reported use of steel slag and blast furnace slag in asphalt mixtures. Producers in 10 states reported using steel slag, and in six states reported using blast furnace slag during the 2020 construction season; in five of these states — Alabama, Illinois, Indiana, Michigan, and Ohio — producers reported using both. Also reported in Table 18 is the use of foundry sand, another byproduct material generated by metal-casting processes at foundries. Not surprisingly, the reported use of slags in asphalt pavement mixtures is most common in regions with steel and iron production industries and thus a relatively available supply of slag aggregates (NSA, n.d.), as seen in Figure 20.

While the total tons of asphalt mixture and materials for each slag type vary from year to year, there was a downward trend in the reported combined use of both slags for 2014 through 2016, as illustrated in Figure 21, but rebounded significantly in 2017 and 2018. The reported slag utilization has since been on the decline, with use in 2019 decreasing 36 percent and then 2020 decreasing 31 percent in year over comparisons, but the fluctuating number of companies reporting slag use and the specific companies that did or did not participate in each survey impact these utilization trends. There was no reported use of foundry sand in 2020, which matched 2019.

The U.S. Geologic Survey estimates that about 16.0 million tons of iron and steel slag was sold in 2020, divided equally by weight between blast furnace slag and steel slag (USGS, 2021). About 14 percent of this (2.24 million tons) was estimated as used in asphalt pavement mixtures in 2017 (van Oss, 2020). With 858,000 tons of slag materials reported as being used in asphalt mixtures during the 2020 construction season, this survey captures nearly 38 percent of total slag estimated to be used in asphalt pavement mixtures. For the states reporting slag use, slightly more than 7 percent of their total reported asphalt pavement mixture tonnage includes steel and/or blast furnace slag. According to the American Foundry Society, between 4 million and 7 million tons of foundry sand are available for recycling annually (AFS, n.d.), identifying there remains a significant potential for use in asphalt pavement mixtures in the future.

Table 20: Reported Tons for Steel Slag, Blast Furnace Slag, & Foundry Sand and Tons of Asphalt Mixture Using Each Material, 2016–2020

State & Material	Reported Tons of Mixture Using Material					Reported Tons of Material Used				
	2016	2017	2018	2019	2020	2016	2017	2018	2019	2020
Steel Slag										
Alabama	475,000	755,764	985,000	985,015	741,000	55,000	164,229	195,500	190,252	163,500
Arkansas	60,210	49,005	148,533	63,901	131,500	9,109	10,238	26,658	5,195	24,500
Illinois	5,271	10,000	4,002	1,466	81,000	2,600	8,100	869	450	19,000
Indiana	140,000	132,500	328,214	84,997	194,546	64,000	45,929	110,777	72,937	54,301
Iowa	—	25,000	75,000	2,500	30,000	—	4,500	13,000	900	7,500
Kentucky	—	45,853	—	25,000	—	—	4,603	—	2,500	—
Michigan	—	367,652	1,847,249	1,400,000	1,964,335	—	259,252	225,818	215,000	285,000
Minnesota	134,000	140,000	115,000	102,000	25,000	17,800	28,500	20,000	15,000	5,000
Mississippi	35,000	—	5,000	36,187	120,075	500	—	250	1,394	4,683
Missouri	—	—	38,599	22,430	—	—	—	6,431	3,645	—
Ohio	85,000	145,868	145,000	155,000	225,000	18,000	30,556	30,000	32,000	45,000
Tennessee	—	—	30,000	—	—	—	—	3,000	—	—
Washington	—	413,000	395,000	367,000	338,000	—	53,300	48,000	36,000	35,000
Total	934,481	2,064,642	4,116,597	3,245,496	3,850,456	167,009	609,207	680,303	575,273	643,484
No. of Companies	12	18	23	14	18					

Blast Furnace Slag										
Alabama	210,000	177,933	375,000	252,653	122,000	30,000	39,379	85,500	54,530	13,500
Illinois	—	—	—	505	8,000	—	—	—	100	4,000
Indiana	1,007,000	1,001,700	1,660,356	972,970	256,356	179,900	336,413	548,431	319,465	29,000
Iowa	—	—	—	1,000	—	—	—	—	350	—
Kentucky	500,000	600,000	150,000	80,000	—	80,000	100,000	30,000	20,000	—
Michigan	—	393,239	470,015	319,449	138,889	—	156,741	110,220	116,670	14,000
Mississippi	—	11,534	—	—	—	—	1,150	—	—	—
Missouri	—	—	1,630	—	—	—	—	489	—	—
Ohio	696,219	660,395	595,263	623,238	590,996	176,333	164,861	149,580	155,758	151,770
Pennsylvania	—	—	—	—	5,000	—	—	—	—	2,500
Tennessee	—	—	60,000	—	—	—	—	6,000	—	—
West Virginia	695,572	150,000	1,052,500	—	—	100,987	22,500	137,958	—	—
Wisconsin	—	—	—	—	—	—	—	—	—	—
Total	3,108,791	2,994,801	4,364,764	2,249,815	1,121,241	567,220	821,044	1,068,178	666,873	214,770
No. of Companies	13	13	18	14	13					

Foundry Sand										
Missouri	15,960	10,000	—	—	—	1,596	1,000	—	—	—
Texas	—	—	50,000	—	—	—	—	4,800	—	—

— = No Use Reported

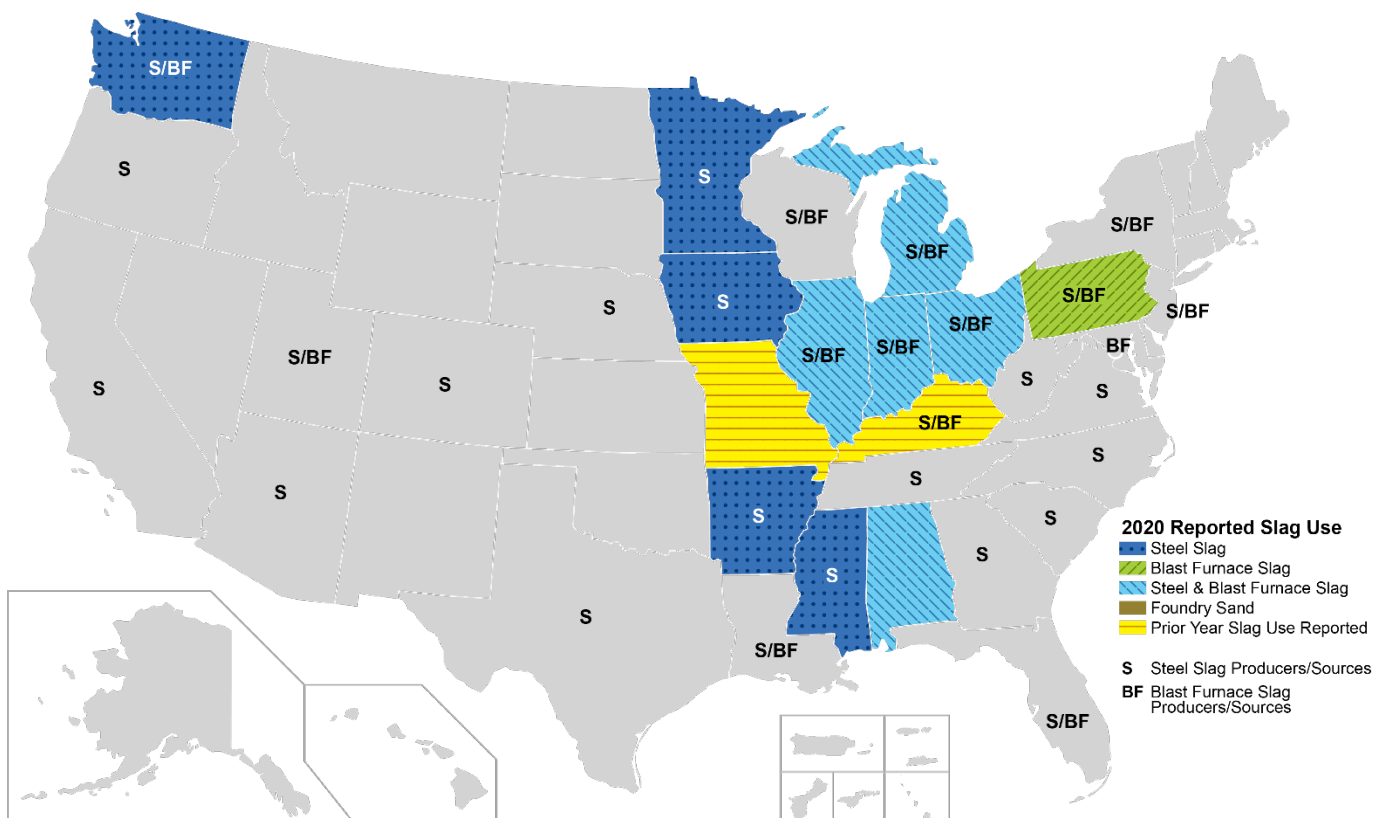


Figure 20: States Reporting Steel and/or Blast Furnace Slag Use and Slag Producers/Sources, 2020

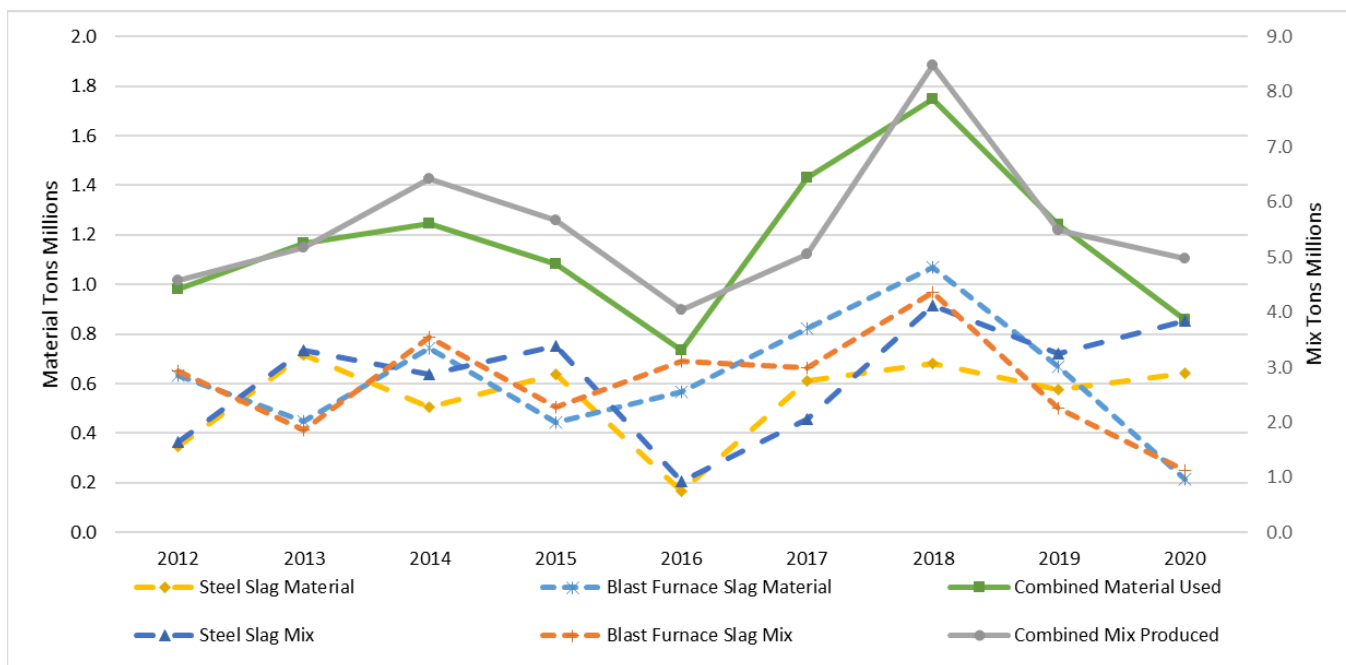


Figure 21: Steel and Blast Furnace Slag Use, 2012–2020

Recycled Fibers

Table 21 summarizes the use of various types of recycled fibers used in asphalt mixtures. For the 2020 construction season, producers only reported using recycled cellulose fibers. In 2016 a small amount of recycled poly fibers were reported. The reported use of cellulose fiber increased significantly beginning in 2015, due to the specific request for

data about cellulose fiber starting with the 2015 construction season survey. As explained in Appendix A, in previous years, reporting data about cellulose fiber use was at the discretion of the respondent. During the 2020 construction season, producers from 22 states reported using more than 8,700 tons of recycled fibers in nearly 2.25 million tons of asphalt pavement mixture.

Table 21: Recycled Fibers, 2016–2020

State & Material	Reported Tons of Mixture Produced Using Recycled Fibers*					Reported Tons of Other Recycled Fibers*				
	2016	2017	2018	2019	2020	2016	2017	2018	2019	2020
Cellulose Fibers										
Alabama	—	193,268	196,000	4,232	132,817	—	720	655	18	773
Arkansas	—	—	250	—	600	—	—	1	—	2
California	—	—	36,865	33,621	57,148	—	—	55	109	86
Connecticut	—	—	500	—	2200	—	—	2	—	7
Delaware	20,000	—	12,000	—	15,000	60	—	36	—	500
Dist. of Columbia	—	—	1,006	28,000	1,065	—	—	5	100	4
Florida	94,903	165,863	193,450	35,500	—	71	663	362	124	—
Georgia	—	—	370,934	304,877	425,000	—	—	1,170	1,045	1,300
Idaho	—	—	1,500	—	—	—	—	5	—	—
Illinois	—	—	—	—	442,900	—	—	—	—	1,320
Kentucky	—	—	35,000	—	—	—	—	105	—	—
Maryland	100,000	125,000	138,000	—	115,000	300	373	414	—	2090
Massachusetts	2,000	—	—	—	350	3	—	—	—	1
Michigan	—	145,200	151,728	152,865	60,000	—	84	231	174	80
Minnesota	—	—	14,000	12,000	152,200	—	—	22	100	506
Mississippi	53,998	40,173	60,000	133,236	218,794	153	121	400	513	534
Missouri	—	60,000	136,000	36,458	153,000	—	180	3,108	166	325
New York	1,640	—	500	1,160	9,000	9	—	1	5	5
North Dakota	65,000	—	—	—	60,000	195	—	—	—	180
Ohio	3,000	6	16,750	1,350	—	—	0	50	3	—
Oklahoma	—	—	—	—	47,000	—	—	—	—	26
Oregon	—	—	—	50,000	—	—	—	—	165	—
Pennsylvania	45,000	21,000	84,300	17,717	63,880	90	88	211	52	540
Tennessee	127,845	113,000	27,000	—	—	201	300	180	—	—
Texas	—	20,000	79,700	215,000	63,000	—	60	554	235	13
Utah	122,317	120,696	149,135	277,000	128,400	570	336	746	530	302
Virginia	30,000	—	116,000	90,000	50,000	90	—	348	271	50
Washington	—	—	5,000	—	—	—	—	100	—	—
Wisconsin	—	—	—	—	52,000	—	—	—	—	104
Carbon Fibers										
Washington	—	—	2,000	—	—	—	—	50	—	—
Poly Fibers										
Maine	—	—	—	—	—	2	—	—	—	—
New Hampshire	—	—	—	—	—	5	—	—	—	—
Vermont	—	—	—	—	—	3	—	—	—	—
Total	665,703	1,004,206	1,825,618	1,393,016	2,249,354	1,754	2,925	8,761	3,610	8,748
No. of Companies	28	20	43	28	42					

*Not all producers reporting tonnages of mixtures using other recycled materials provided quantities of recycled materials used and vice versa.

NCR = No Companies Responding; — = No Use Reported

Coal Combustion Products

Several waste and by-products associated with the burning of coal to produce electricity, including fly ash, bottom ash, boiler slag and flue-gas desulfurization (FGD) materials, are used in asphalt pavement mixtures as a cost-effective mineral filler that can help increase mixture stiffness and reduce asphalt drain down. In the 2020 construction season survey, fly ash was the only of these coal combustion products (CCP) reported as being used, as shown in Table 22. In previous survey years, limited use of bottom ash was reported in 2012 in South Dakota and in 2015 in Texas.

To give a picture of the total use of CCP in asphalt pavement mixtures, the American Coal Ash Association found that some 16,195 tons of fly ash, no bottom ash, no boiler slag, and 2,226 tons of FGD material from dry scrubbers and others were used as mineral filler in asphalt in 2020 (ACAA, 2021). Fly ash usage reported for the 2020 construction season survey is about 86 percent of total fly ash used as a mineral filler in asphalt pavements; however, only a very small amount (0.005 percent) of the 40.7 million tons of coal combustion products produced in 2020 were used in asphalt mixtures, according to ACAA (2021). Unlike with slags, there is no apparent correlation between the location of coal-fired power plants and the use of CCP in asphalt pavement mixtures.

Table 22: Reported Tons of Asphalt Mixtures Using Coal Combustion Products and Reported Tons of CCP Used, 2016–2020

State & Material	Reported Tons of Asphalt Mixtures Using CCP*					Reported Tons of CCP Used*				
	2016	2017	2018	2019	2020	2016	2017	2018	2019	2020
Fly Ash										
Alabama	—	58,253	160,000	—	51,417	—	2,625	5,100	—	2,007
Georgia	—	—	3,068	—	50,000	—	—	53	—	2,000
Illinois	—	95,750	—	—	12,000	—	1,500	—	—	300
Michigan	—	—	—	30,000	—	—	—	—	700	—
Mississippi	19,000	141,767	—	39,687	120,075	750	4,253	—	1,076	3,242
Missouri	—	60,000	—	—	110,000	—	4,000	—	—	2,334
North Dakota	—	—	—	—	60,000	—	—	—	—	2,400
Texas	30,000	20,000	110,000	175,000	—	—	600	3,300	8,750	—
Wisconsin	160,000	40,000	60,000	—	32,000	9,500	4,000	3,600	—	1,600
Total (All CCP)	209,000	415,770	333,068	244,687	435,492	10,250	16,978	12,053	10,526	13,883
No. of Companies	3	10	5	4	8					

*Not all producers reporting tonnages of mixtures using other recycled materials provided quantities of recycled materials used and vice versa.

NCR = No Companies Responding

— = No Use Reported

Other Recycled Materials

Table 23 summarizes other recycled materials reported as used in asphalt mixtures, for the 2020 construction season producers reported using blasting sand, marble production dust, plant start-up waste, and recycled polyethylene. In previous years, producers have also reported the use of crushed concrete aggregate, recycled glass, and petroleum-contaminated soil in asphalt pavement mixtures.

Table 23: Other Recycled Materials, 2016–2020

State & Material	Reported Tons of Mixture Produced Using Other Recycled Material*					Reported Tons of Other Recycled Material Used*				
	2016	2017	2018	2019	2020	2016	2017	2018	2019	2020
Blasting Sand										
South Carolina	—	—	—	—	25,000	—	—	—	—	5,000
Crushed Concrete Aggregates										
Florida	—	—	10,000	—	—	—	—	1,000	—	—
Marble Production Dust										
Georgia	—	—	—	—	50,000	—	—	—	—	500
Plant Start-Up Waste										
Missouri	—	—	15,000	—	5,000	—	—	4,000	—	500
Recycled Polyethylene (rPE)										
Wisconsin	—	—	—	—	1,000	—	—	—	—	5
Total	—	—	25,000	—	81,000	—	—	5,000	—	6,005

* Not all producers reporting tonnages of mixtures using other recycled materials provided quantities of recycled materials used and vice versa.

NCR = No Companies Responding; — = No Use Reported

In-place Recycling

Starting with the 2019 construction season survey, a supplemental survey was conducted to gather information about the use of in-place recycling techniques. The specific in-place recycling techniques the survey asked about included cold in-place recycling, hot in-place recycling, cold central plant recycling, and full-depth reclamation techniques. The information requested in the survey is detailed in Appendix A and summarized in Table A3, Sections 1 and 2.

Contractors were asked the quantity of recycled asphalt pavement processed as part of each in-place recycling technology during the 2020 construction season. Because different units of measurement may be used for each in-place recycling technology, respondents were asked to provide both a quantity and the unit of measure, for example tons, metric tonnes, cubic yards, square yards at inches of thickness, and so forth. All values provided within this report will be in tons; respondent quantities that were provided in a unit of volume were converted to tons with a compacted unit weight of 149.3 lbs. per cubic foot.

Because the response rate to the supplemental survey on in-place recycling was low, state and national estimates of total quantities used for these materials were not calculated. **All values in this section are reported values only and do not represent estimates of the total quantity of these materials used in each state or nationally.**

A total of 21 companies, from three of the four User Producer Group regions, reported using more than 3.7 million tons of recycled asphalt pavement while completing the in-place recycling process during the 2020 construction season.

In-Place Recycling Use by User Producer Group Region

Figure 22 shows the total reported tons for cold in-place recycling, hot in-place recycling, cold central plant recycling, and full-depth reclamation techniques separated by User/Producer Group (UPG) region during the 2020 construction season. The North Central Asphalt User/Producer Group (NCAUPG) region had the most respondents (13 companies); the region also accounted for more than 68 percent of the in-place recycling tonnage reported for 2020. The NCAUPG region had tonnage reported for all four techniques with FDR being, 48 percent and the highest tonnage for the region. The North East Asphalt User/Producer Group (NEAUPG) had no respondents to the in-place recycling survey. The Southeastern Asphalt User/Producer Group (SEAUPG) and the combined Rocky Mountains Asphalt User/Producer Group (RMAUPG) and Pacific Coast Conference on Asphalt Specification (PCCAS) regions, had 5 and 3 companies respond respectively. The SEAUPG region had no tonnage reported for CCPR and CIR, while the combined RMAUPG and PCCAS regions had no reported tonnage for HIR. The total reported tonnage was down (13 percent) from 4.2 million tons in 2019, to 3.7 million in 2020, with responses falling (25 percent) from 28 companies in 2019 to 21 companies in 2020.

Region	Companies	(tons)			
		HIR	CCPR	CIR	FDR
NCAUPG	13	139,482	480,000	773,596	1,296,890
SEAUPG	5	291,200	0	0	123,942
RMAUPG / PCCAS	3	0	14,500	544,059	40,975
NEAUPG	NCR	NCR	NCR	NCR	NCR
2020 Totals	21	430,682	494,500	1,317,655	1,461,807
2019 Totals	28	319,600	8,400	2,100,952	1,830,416

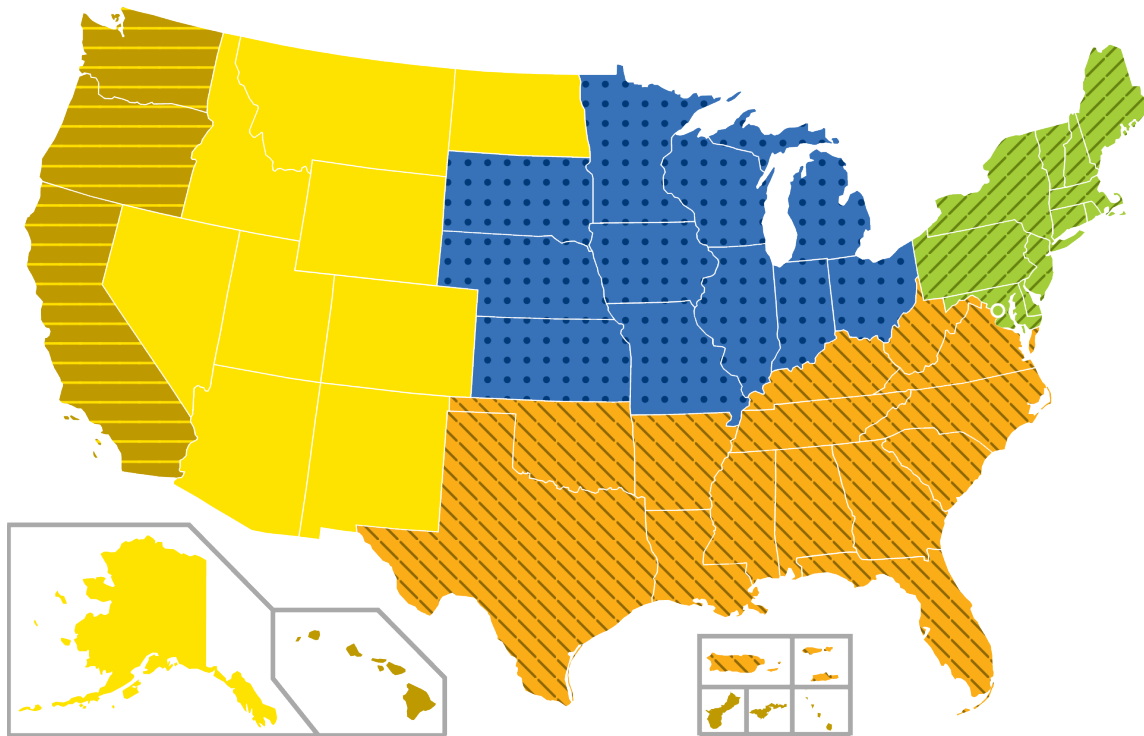


Figure 22: In-place Recycling Tonnages, 2020

Historical Trends

Since 2009 this annual survey has quantified and documented the use of recycled materials and WMA produced by the asphalt pavement mixture production industry. Throughout the report there are figures and tables provided which show production changes and trends that have occurred over this time period.

Historical trends from the 2009 to 2020 construction season surveys:

- Industry participation in this voluntary survey has increased in terms of both number of companies and number of plant production facilities, which is a critical factor in ensuring the survey is providing accurate estimates for the industry's annual asphalt production as well as the utilization of recycled materials and WMA. Table 2 provides the annual breakdown of participation, showing that participation has increased by 40 percent in terms of company responses and 37 percent in terms of plant production facilities for the 2009 to 2020 time frame.
- The year over year change in total asphalt mixture production has been relatively stable over the history of the survey, with 2019 (8% increase in tonnage compared to 2018) being the only year with over a 5 percent

change. Figure 2 provides the annual asphalt mixture production estimates and illustrates that 2012, 2013, and 2020 are the three construction seasons that saw a downturn in production, with - 2 percent, - 3 percent, and - 3 percent respectively.

- The national average percent RAP utilized in asphalt mixtures has gradually increased since 2009, with a 37 percent overall increase in average percent RAP, starting at 15.6 percent RAP in 2009 and reaching 21.3 percent in 2020. Figure 3 provides a graphical illustration of the tonnage of RAP that has been utilized as a result of the increased percent utilization on the asphalt production tonnages over the history of the survey.
- RAS tons utilized in asphalt mixtures peaked in 2014 and have steadily decreased in utilization for all sectors through the 2020 construction season. Figure 9 and Figure 10 show the annual tonnages of RAS utilization and provide visuals on the decreasing use by all sectors since reaching the peak utilization level.
- WMA has seen steady growth in all sectors since 2009, with the accumulated growth over the history of the survey in 2020 of more than 1010 percent from the estimated 16.8 million tons of WMA production in the 2009 construction season. The estimated annual WMA production for each sector is provided in Table 16.
- The majority of the WMA market is made up of two WMA technologies, plant-based foaming and chemical additives. Plant-based foaming peaked in 2011 at over 95 percent of the market while that was the low for the chemical additive technology at just 4 percent of the market in 2011. As seen in Table 15 and Figure 18, plant-based foaming has steadily decreased since 2011 and chemical additives have steadily increased market share, with plant-based foaming at 49 percent and chemical additives at 46 percent in 2020.
- Additionally, the survey has collected new information and provided further details over its history. Recent additions include the collection of in-place recycling techniques which started for the 2019 construction season, as well as the addition of the Energy and Greenhouse Gas Emissions analysis section of the report which was debuted in the 2019 construction season report.

Summary and Conclusions

The objective of this survey was to quantify the use of recycled materials and WMA produced by the asphalt pavement mixture production industry during the 2020 construction season. Asphalt mixture producers from 50 states and the District of Columbia completed the 2020 survey. Responses came from 274 companies with data from 1,406 production plants. Data collected was compared to annual data from previous surveys since the 2009 construction season.

The survey findings for 2020 regarding the use of RAP, RAS, and WMA are summarized in Table 4.

Comparing the 2020 results to 2019 construction season, estimated total asphalt mixture production saw an decrease from 407.8 million tons to 421.9 million tons, a 3.3 percent decrease. DOT tonnage decreased 1.2 percent, mixture production for the Other Agency sector increased by 0.3 percent, and the Commercial and Residential sector fell significantly (8.3 percent) from 2019 to 2020.

The use of RAP has risen dramatically since the 2009 construction season survey; 2020 saw a decrease in RAP tonnage used in asphalt mixtures of 2.5 percent below 2019, which was driven by the reduced asphalt mixture tonnage in 2020.

The 2020 construction season survey shows:

Reclaimed Asphalt Pavement

- The total estimated tons of RAP used in asphalt mixtures was 87.0 million tons in 2020. This represents a 55.4 percent increase in the total estimated tons of RAP used in 2009. During the same time frame, total asphalt mixture tonnage increased only 13.8 percent.

- The percentage of producers reporting use of RAP was 98.9 percent of respondents which is up 1.2 percent from 2019.
- The average percent RAP used by all sectors has seen variable growth from 2009 to 2019. The average estimated percentage of RAP used in asphalt mixtures has increased from 15.6 percent in 2009 to 21.3 percent in 2020.
- Companies reporting having stockpiled RAP on hand at year-end increased from 93.9 percent in 2019 to 97.1 percent in 2020. In total, producers accepted an estimated 96.3million tons and used an estimated 93.7 million tons in 2020.
- Reclaiming 96 million tons of RAP for future use saved about 58.4 million cubic yards of landfill space.
- The total estimated amount of RAP stockpiled nationwide at the end of the 2020 construction season was 135 million tons.
- Producers from 40 states reported fractionating RAP. Nationally, a reported 26 percent of RAP is fractionated.
- Producers from 38 states reported using softer binders and 22 states reported using recycling agents in RAP mixtures. There was little correlation between the percentage of RAP used in asphalt pavement mixtures and the use of softer binders and/or recycling agents in a given state.

Reclaimed Asphalt Shingles

- Use of both recycled MWAS and PCAS in asphalt mixtures decreased (36 percent) from an estimated 921,000 tons in 2019 to 586,000 tons in 2020.
- The amount of unprocessed RAS accepted by asphalt mixture producers decreased from 611,000 tons in 2019 to 514,000 tons in 2020. An estimated 278,000 tons of processed RAS was also accepted by producers, which was about 145,000 tons less processed RAS than was accepted in 2019. The combined amount of unprocessed and processed RAS accepted in 2020 was 792,000 tons, which was 151,000 tons more RAS than was used for all purposes during the 2020 construction season.
- Of the unprocessed RAS accepted by producers in 2020, 277,000 tons was PCAS and 237,000 tons was MWAS.
- Of the RAS used in 2020, more than 91 percent was used in asphalt mixtures. The remainder was in other civil engineering applications. No producers reported landfilling of RAS during the 2020 construction season.
- The percent of producers reporting use of RAS decreased from 21.7 percent of respondents in 2019 to 20.8 percent in 2020.
- The total estimated amount of RAS stockpiled nationwide at the end of the 2020 construction season was nearly 1.27 million tons.
- Accepting 514,00 tons of unprocessed RAS from both PCAS and MWAS sources diverted about 310,000 cubic yards of material from landfills.
- The number of states with producers reporting RAS use was 24 in 2020. Iowa producers for the first time since the beginning of the survey reported no RAS use, while still reporting that RAS is allowed in some mixtures for all sectors.
- Commercial & Residential sectors allow the use of RAS in most states, with more limited use in DOT and Other Agency public sector mixtures, according to producer and SAPA reports. No states reportedly allow the use of RAS in all mixes for all sectors, and ten states reportedly do not approve the use of RAS in asphalt pavement mixtures for any sector.
- Producers from 18 states reported using softer binders and eight states reported using recycling agents in RAS mixtures.

Material Cost Savings

- The use of RAP and RAS saved more than \$3.0 billion during the 2020 construction season compared to the use of all virgin materials. These savings help reduce material costs for asphalt pavement mixtures, allowing road owners to achieve more roadway maintenance and construction activities within limited budgets.
- The diversion of RAP and RAS from landfills during the 2020 construction season save nearly 59 million cubic yards of space in construction and demolition landfills, as well as nearly \$4.7 billion in gate fees associated with the disposal of RAP and RAS.

Other Recycled Materials

- A reported total of more than 900,000 tons of other recycled materials was used in about 9.1 million tons of asphalt mixtures by 70 companies in 28 states during the 2020 construction season.
- Eighteen producers from 10 states reported use of recycled tire rubber (RTR) in asphalt mixtures during the 2020 construction season. The total reported tons of asphalt mixture using RTR increased 10 percent from 2019 to 1,343,000 tons in the 2020 construction season.
- Producers in 11 states reported use of steel or blast furnace slags, and no states reported the use of foundry sand in 2020. Compared to reported use in 2019, the reported tons of mixtures including steel slag and mixtures including blast furnace slag decreased 10 percent during the 2020 construction season. Reported use of these materials was concentrated along the Mississippi and Ohio River Valleys, where much of U.S. steel and iron production is concentrated.
- Producers in seven states reported using fly ash in asphalt mixtures in 2020. Fly ash was the only coal combustion product (CCP) reported as being used in asphalt pavement mixtures during the 2020 construction season.
- Producers in 22 states reported use of more than 8,700 tons of recycled cellulose fiber in more than 2.2 million tons of asphalt pavement mixtures during 2020.

Warm Mix Asphalt

The use of WMA technologies continues to increase since 2009. The 2020 construction season survey shows:

- The estimated total tonnage of asphalt pavement mixtures produced with WMA technologies for the 2020 construction season was about 186.4 million tons. This was a 13 percent increase from the estimated 164.5 million tons of mixture produced with WMA technologies in 2019 and a more than 1010 percent increase from the estimated 16.8 million tons in the 2009 construction season.
- Mixtures produced with WMA technologies made up 45.7 percent of the total estimated asphalt mixture market in 2020. About 49.9 percent (93.1 million tons) of these mixtures were produced with a temperature reduction of at least 10°F.
- In addition, producers using WMA technologies in ten states — Colorado, Connecticut, Kentucky Louisiana, Mississippi, New Hampshire, Pennsylvania, Utah, Vermont, and West Virginia — reported producing more than 75 percent of their total tonnage with WMA technologies.
- Production plant foaming, representing 49 percent of the market in 2020, remains the most commonly used warm-mix technology, despite decreasing about 46.2 percent since its peak in the 2011 construction season.
- Chemical additive technologies accounted for a little more than 46 percent of the market in 2020, a slight decrease from their use in the 2019 construction season.
- The decrease in plant-based foaming technologies been seen in the survey since 2011.
- There appears to be some variation in the use of WMA technology based upon production temperature.
- About 67 percent of survey respondents reported producing asphalt mixture with WMA technologies; 184 producers in 47 states reported using WMA technologies.

Conclusions

The 2020 survey results show that the asphalt pavement mixture production industry has a strong record of sustainable practices and continues to innovate through the use of recycled materials and WMA. Since the initial industry survey of the 2009 construction season, producers have significantly increased their use of recycled materials and WMA; however, since the 2013 survey, indicators are that the rate of increase of adoption has slowed.

The amount of RAP received was 2.6 million tons more than what producers utilized during the 2020 construction season, with 97.1 percent of producers indicated they have stockpiled RAP on hand. With an estimated 135.3 million tons of RAP stockpiled nationwide at year-end 2020, opportunities remain to increase the amount of RAP used in asphalt mixtures through engineering, performance-based specifications, education, improved RAP processing, production equipment, and procedures.

RAS use saw a 36 percent decrease in 2020 in asphalt pavement mixtures; by accepting 514,000 tons of waste shingles during 2020, producers diverted about 3.4 percent of the nation's available waste shingles for use in asphalt mixtures. An estimated 1.27 million tons of RAS was stockpiled nationwide at year-end 2020. As with RAP, performance-based specifications, education, improved processing, production equipment, and procedures will help increase the amount and percentages of RAS used in asphalt mixtures.

The asphalt pavement mixture production industry repurposes many products from other industries. The survey shows that, for the 2020 construction season, slag use was reported in 11 states, RTR use was reported in 10 states, recycled cellulose use was reported in 22 states, and fly ash use in seven states.

The tonnage of asphalt pavement mixtures produced with WMA technologies saw a 13 percent increase during the 2020 construction season with a total production of 186.4 million tons, which represents 45.7 percent of total estimated asphalt mixture production for the year. Producers in Hawaii, Montana, and Rhode Island reported not producing mixtures with WMA technologies in 2020.

References

- ACAA (2021). 2020 Coal Combustion Product (CCP) Production & Use Survey Report. American Coal Ash Association, Farmington Hills, Michigan. <https://www.acaa-usa.org/publications/production-use-reports> [Accessed December 2021]
- AFS (n.d.). Introduction to Foundry Sand [web page]. American Foundry Society, Schaumburg, Illinois. <https://www.afsinc.org/introduction-foundry-sand> [Accessed 24 May 2019]
- Aschenbrener, T. (2017). *FHWA Division Office Survey on State Highway Agency Usage of Reclaimed Asphalt Shingles: Quantities, Trends, Requirements, and Direction — Results from May 2017* (Report No. FHWA-HIF-18-009). Federal Highway Administration, Washington, D.C.
- Boxman, S., & Staley, B.F. (2021). Analysis of MSW Landfill Tipping Fees - 2020. Environmental Research & Education Foundation, Raleigh, N.C.
- Caltrans (2017). *2015 Crumb Rubber Report: Cost Differential Analysis Between Asphalt Containing Crumb Rubber and Conventional Asphalt*. California Department of Transportation, California State Transportation Agency, Sacramento, California.
- Carvalho, R.L., H. Shirazi, M. Ayres Jr., & O. Selezneva (2010). Performance of Recycled Hot-Mix Asphalt Overlays in Rehabilitation of Flexible Pavements. In *Transportation Research Record: Journal of the Transportation Research Board*, No. 2155, pp. 55–62. Transportation Research Board of the National Academies, Washington, D.C. doi:10.3141/2155-06
- CIF (2013). 2013 NOVA Award Winner — Warm Mix Asphalt. Construction Innovation Forum, Walbridge, Ohio. <http://youtu.be/q47p1SAy4g4> [Accessed 14 August 2014]
- Copeland, A. (2011). *Reclaimed Asphalt Pavement in Asphalt Mixtures: State of the Practice*. Report FHWA-HRT-11-021. Federal Highway Administration, McLean, Virginia.
- Copeland, A., C.L. Jones, & J. Bukowski (2010). Reclaiming Roads. *Public Roads*, Vol. 73, No. 5 (March/April). Publication FHWA-HRT-10-001. <http://www.fhwa.dot.gov/publications/publicroads/10mar/06.cfm> [Accessed 14 August 2014]
- FHWA (2013). Every Day Counts: Warm Mix Asphalt [website]. Federal Highway Administration, Washington, D.C. <http://www.fhwa.dot.gov/publications/publicroads/10mar/06.cfm> [Accessed 14 August 2014]

- Hansen, K.R., & A. Copeland (2013a). *2nd Annual Asphalt Pavement Industry Survey on Reclaimed Asphalt Pavement, Reclaimed Asphalt Shingles, and Warm-Mix Asphalt Usage: 2009–2011* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2013b). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2009–2012, 3rd Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2014). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2009–2013, 4th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2015). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2014, 5th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & A. Copeland (2017). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2015, 6th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., A. Copeland, & T.C. Ross (2017). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2016, 7th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- Hansen, K.R., & D.E. Newcomb (2011). *Asphalt Pavement Mix Production Survey: Reclaimed Asphalt Pavement, Reclaimed Asphalt Shingles, Warm-Mix Asphalt Usage: 2009–2010* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- NAHB (1998). *From Roofs to Roads... Recycling Asphalt Roofing Shingles into Paving Materials*. NAHB Research Center, National Association of Home Builders, Upper Marlboro, Maryland.
- NSA (n.d.). Slag Availability [web page]. National Slag Association, Pleasant Grove, Utah. <http://nationalslag.org/slag-availability> [Accessed December 2021]
- Pappas, J. (2011). Recycling Materials Survey. Presented at the RAP Expert Task Group May Meeting, May 2011, Irvine, California. <http://www.morerap.us/files/meetings/05-11/pappas-recycling-materials-survey.pdf> [Accessed 14 August 2014]
- Prowell, B.D., G.C. Hurley, & B. Frank. (2012). *Warm-Mix Asphalt: Best Practices, 3rd Edition* (QIP 125). National Asphalt Pavement Association, Lanham, Maryland.
- Prowell, B.D., R.J. Schreck, & S. Sasaki (2011). Evaluation of Compaction Benefits of Foamed Asphalt Mixtures at Varying Production Temperatures. Presented at 2nd International Warm-Mix Conference, 11–13 October 2011, St. Louis, Missouri.
- Tolaymat, T., M. Krause, J. Smith, & T. Townsend (2017). The State of the Practice of Construction and Demolition Material Recovery (EPA/600/R-17/231). U.S. Environmental Protection Agency, Washington, D.C.
- U.S. EPA (2018). *Questions and Answers: Greenhouse Gas Emissions from a Typical Passenger Vehicle*. Office of Transportation and Air Quality, EPA-420-F-18-008.
- U.S. EPA (2020). *Advancing Sustainable Materials Management: 2018 Fact Sheet*. Office of Land and Emergency Management, EPA 530-F-20-009
- USGS (2020). Mineral Commodities Summaries 2020. U.S. Geological Survey, Reston, Virginia. doi:10.3133/mcs2020.
- USTMA (2020). *2019 U.S. Scrap Tire Management Summary*. U.S. Tire Manufacturers Association, Washington, D.C.
- van Oss, H.G. (2020). Slag—Iron and Steel. In *2017 Minerals Yearbook*, pp. 69.1–69.8. U.S. Geological Survey, Reston, Virginia.
- West, R.C. (2016). *Best Practices for RAP and RAS Management* (QIP 129). National Asphalt Pavement Association, Lanham, Maryland.
- West, R.C., J. Michael, R. Turochy, & S. Maghsoodloo (2011). Use of Data from Specific Pavement Studies Experiment 5 in the Long-Term Pavement Performance Program to Compare Virgin and Recycled Asphalt Pavements. In *Transportation Research Record: Journal of the Transportation Research Board*, No. 2208, pp. 82–89. Transportation Research Board of the National Academies, Washington, D.C. doi:10.3141/2208-11
- West, R.C., M.C. Rodezno, G. Julian, B.D. Prowell, B. Frank, L.V. Osborn, & A.J. Kriech (2014). *NCHRP Report 779: Field Performance of Warm-Mix Asphalt Technologies*. Transportation Research Board of the National Academies, Washington, D.C. doi:10.17226/22272
- Williams, B.A., A. Copeland, & T.C. Ross (2018). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2017, 8th Annual Survey* (IS 138). National Asphalt Pavement Association, Lanham, Maryland. doi:10.13140/RG.2.2.30240.69129
- Williams, B.A., J.R. Willis, & Shacat, J. (2019). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2019, 10th Annual Survey* (IS 138). National Asphalt Pavement Association, Greenbelt, Maryland. DOI: 10.13140/RG.2.2.21946.82888



National Asphalt Pavement Association

6406 Ivy Lane, Suite 350

Greenbelt, Maryland 20770-1441

www.AsphaltPavement.org

napa@AsphaltPavement.org

Toll Free: 888-468-6499

Tel: 301-731-4748

Fax: 301-731-4621

Publication Sales

Login at <https://member.asphaltpavement.org/Shop/Product-Catalog>

Toll Free: 888-600-4474

Tel: 412-741-6314

Fax: 412-741-0609

11th Annual Asphalt Pavement Industry Survey IS 138



Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2020

IS-138 Appendix A:
Methodology & Survey Forms



11th Annual Survey

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020

Appendix A

Appendix A to the eleventh edition of *Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage* (Williams et al., 2021) provides details on the methodology used to collect and analyze the 2020 construction season survey data and reproduces the primary survey instruments used to collect data from asphalt pavement mixture producers and State Asphalt Pavement Associations (SAPA). Producers were asked primarily to provide company-/plant-level data, while SAPAs were asked to provide industry-level data for their state. In 2020, the supplemental survey was again fielded to gather information about the use of in-place recycling techniques.

Survey Methodology

To collect and analyze the data summarized in the main *Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage* report for the 2020 construction season survey, the following tasks were conducted:

1. Develop a survey instrument that enables an analysis of the quantities of recycled materials being used in asphalt mixtures, as well as the total amount of WMA produced nationally.
2. Conduct a voluntary survey of asphalt mix producers throughout the United States and follow up via telephone, email, and in-person requests for information in locations where responses were low.
3. Estimate the total asphalt mixture market in each state or territory by using data provided by SAPAs through the survey instrument and the U.S. Department of Transportation federal-aid highway apportionment to determine a weighting factor for each state and reconciling the total U.S. asphalt mix tonnage with national estimates.
4. Analyze and summarize the information nationally and in each state and to prepare a final report.

The survey was conducted using an online survey platform, SurveyMonkey®. Table A1 summarizes the questions asked in each section of the survey instrument. Sections 1 through 4 of the survey instrument remained consistent from the 2009 to 2014 construction seasons. Questions were added to or modified in Sections 2 through 4 for the 2015 to 2020 construction seasons to gather additional information about RAP and RAS stockpiling, fractionation, the use of softer binders and recycling agents, the acceptance of processed RAS, and the use of WMA technologies at HMA temperatures. In 2017, the Section 3 question about tons of unprocessed shingles accepted was modified to ask about the type of unprocessed shingles accepted. In 2018, the Section 4 questions about the use of WMA additives at HMA temperatures were modified to gather additional information. Section 5 was added in the 2012 construction season survey to collect information on the use of other recycled material in asphalt mixtures. Starting in 2015, the Section 5 question asking about specific recycled materials was modified to replace one user-provided response with cellulose fiber. A copy of the survey used to gather information for the 2020 construction season is provided in the Survey Instrument section of Appendix A.

Producers were notified of the survey through several forums and electronic media. Notice were placed in NAPA's e-newsletter, *ActionNews*, informing members of the survey and asking for their participation. SAPAs solicited participation by placing notices on their websites and in their newsletters. Announcements were made at NAPA meetings, as well as at several State Asphalt Pavement Association conferences. A press release was sent to construction industry trade media and was published in print and online. Notices of the survey and links were also shared through social media channels, primarily Twitter, Facebook, and LinkedIn. Follow up with producers and SAPAs was conducted via email, social media, and telephone.

Table A1: Survey Instrument Summary: Producer Questions, 2020

Section 1: General Information	Section 2: RAP	Section 3: RAS	Section 4: WMA	Section 5: Other Recycled Materials
Type of Survey Respondent	Tons RAP Accepted	Tons Unprocessed Tear-Off Shingles Accepted	Average % Produced for DOT Tons With $\geq 10^{\circ}\text{F}$ Reduction	Other Recycled Materials Used (Y/N)
Contact Information	Tons Used in HMA/WMA Mixes	Tons Unprocessed Manufacturers' Waste Shingles Accepted	Average % Produced for Other Agency Tons With $\geq 10^{\circ}\text{F}$ Reduction	Type of Other Recycled Materials Used (GTR, Steel Slag, Blast Furnace Slag, Cellulose Fiber, Up to Two User-Provided Responses)
State Information Is Provided for	Tons Used in Aggregate Base	Tons Processed Shingles Accepted	Average % Produced for Commercial & Residential Tons With $\geq 10^{\circ}\text{F}$ reduction	Tons of HMA/WMA Produced Using Each Other Recycled Material
Number of Production Plants	Tons Used in Cold-Mix Asphalt	Tons Used in HMA/WMA Mixes	Chemical Admixture % With $\geq 10^{\circ}\text{F}$ Reduction	Tons of Each Other Recycled Product Used
DOT Tons	Tons Used in Other	Tons Used in Aggregate Base	Additive Foaming % With $\geq 10^{\circ}\text{F}$ Reduction	
Other Agency Tons	Tons Landfilled	Tons Used in Cold-Mix Asphalt	Production Plant Foaming % With $\geq 10^{\circ}\text{F}$ Reduction	
Commercial & Residential Tons	Average % for DOT Mixtures	Tons Used in Other	Organic Additive % With $\geq 10^{\circ}\text{F}$ Reduction	
	Average % for Other Agency Mixtures	Tons Landfilled	Average % Produced for DOT Tons at HMA Temperatures	
	Average % for Commercial & Residential Mixtures	Average % for DOT Mixtures	Average % Produced for Other Agency Tons at HMA Temperatures	
	Excess RAP (Y/N)	Average % for Other Agency Mixtures	Average % Produced for Commercial & Residential Tons at HMA Temperatures	
	Tons of RAP Stockpiled	Average % for Commercial & Residential Mixtures	Chemical Admixture % at HMA temperatures	
	Percentage of RAP Fractionated	Excess RAS (Y/N)	Additive Foaming % at HMA temperatures	
	Percentage of RAP Mixtures Using Softer Asphalt Binder	Tons of RAS Stockpiled	Plant Foaming % at HMA temperatures	
	Percentage of RAP Mixtures Using Recycling Agents	What Sectors Allow What Level of RAS	Organic Additive % at HMA temperatures	
		Percentage of RAP Mixtures Using Softer Asphalt Binder		
		Percentage of RAP Mixtures Using Recycling Agents		

Asphalt mixture producers then went to the SurveyMonkey website to complete the survey form. Because data was collected on a state-by-state basis, producers could complete the survey multiple times, providing information for operations in different states on each visit. Some producers submitted data through PDF versions of the survey instrument or through a Microsoft Excel spreadsheet developed by NAPA. After the initial data was gathered and analyzed, anomalies in individual producer records were identified and reconciled.

To collect industry-wide data from the SAPAs, the survey instrument included 7 questions focused on state-level information, as opposed to specific producer information. Table A2 summarizes these questions. In a handful of states without SAPAs, industry-wide data was provided by an Associated General Contractors (AGC) chapter or a similar knowledgeable source. Prior to 2018, this data was collected via a separate survey; starting in 2018, a single survey instrument was used with the first question (“Are you an Asphalt Producer, State Asphalt Pavement Association, or Other”) determining whether the respondent should answer the producer or SAPA survey questions. Respondents indicating “Other” were not surveyed.

Table A2: Survey Instrument Summary: SAPA Questions, 2020

Section 1: General Information	Section 2: Tonnage	Section 3: RAP	Section 4: RAS	Section 5: Other Requirements
Type of Survey Respondent	Estimate of Total Tons Produced in State (All Sectors)	Do Producers in State Fractionate RAP (Y/N)	What Sectors Allow What Level of RAS (DOT, Other Agency, Commercial & Residential)	Require, Allow, or Prohibit Use of Recycling Agents With RAP, RAS, RAP+RAS
Contact Information				
State Information Is Provided for				

Appendix B and certain tables in this report provide survey responses and estimated values at the state/territory level. To keep specific producer data confidential, no state-specific information is provided in the tables or appendixes if fewer than three producers from the state/territory responded to the survey. Information from states/territories with fewer than three responding companies is included in the estimated national values, however.

To gather information about the use of cold in-place recycling, hot in-place recycling, cold central plant recycling, and full-depth reclamation techniques, a supplemental survey was developed in 2019. All respondents to the main survey were asked to complete the supplemental survey if their company provided any in-place recycling or cold central plant recycling services. In addition to promoting the supplemental survey using the same channels as the main survey, NAPA worked with the Asphalt Recycling & Reclaiming Association (ARRA) to promote participation among its membership.

The supplemental survey was conducted using an online survey platform, SurveyMonkey®. Table A3 summarizes the six questions asked in the two sections of the survey instrument. A copy of the supplemental survey is also provided in the Survey Instrument section of Appendix A. Respondents were asked to complete separate copies of the survey for each state in which they operated. Because different units of measurement may be used for each in-place recycling technology, respondents were asked to provide both a quantity and the unit of measure, for example tons, metric tonnes, cubic yards, square yards at inches of thickness, and so forth.

Table A3: Survey Instrument Summary: Supplemental Survey on In-Place Recycling Questions, 2020

Section 1: General Information	Section 2: Total Quantities
Contact Information	Hot In-Place Recycling (HIR)
State Information Is Provided for	Cold Central Plant Recycling (CCPR)
	Cold In-Place Recycling (CIR)
	Full-Depth Reclamation (FDR)

Data Estimation Method

To determine the estimated total amount of RAP and RAS used and WMA produced nationwide and in each state/territory, the total amount of asphalt mix produced in each state/territory needed to be determined. Total tonnage of asphalt mix produced represents both commercial (i.e., private sector) and governmental (i.e., DOT and Other Agency) tonnages. Estimated tonnages were provided by SAPAs for 27 states, totaling more than 290 million tons.

To estimate the total tons in states where a SAPA estimate of total tonnage was not available, a power curve relationship based on an examination of the relationship between SAPA-estimated tons and FY2020 federal-aid highway apportionment (FHWA, 2021) for those states was determined, resulting in Equation A1. This is the same methodology used to estimate tonnage in previous versions of this survey, as detailed in Hansen & Newcomb (2011), with the formula updated annually as SAPA-reported estimates and federal apportionments for the states change.

$$\text{Total Estimated Tons} = 0.0059 \times (\text{State Federal Apportionment})^{1.029} \quad [\text{A1}]$$

As shown in Figure A1, 40 states and territories, along with multiple counties and municipalities across the nation, have acted to raise and/or otherwise dedicate additional local funds to transportation since 2012 (T4America, n.d.; Davis, 2019; NCSL, 2021). These additional and/or dedicated funds are not accounted for in Equation A1, which can lead to underestimation of total tonnage in some states. Similarly, because federal funding for the U.S. territories is through the Territorial and Puerto Rico Highway Program instead of state apportionment, estimates for these jurisdictions were calculated using Equation A1 and Territorial and Puerto Rico Highway Program FY2020 funding levels (FHWA, 2017).

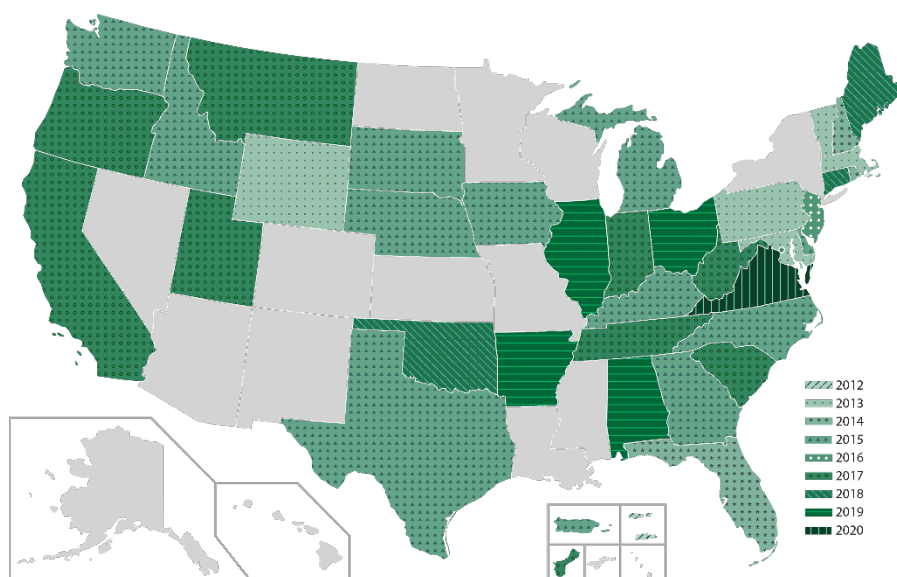


Figure A1: States Approving Measures to Increase and/or Dedicate Transportation Funding, 2012–2020

In addition, in some markets, asphalt pavement mixture may be produced in one state and placed in a neighboring state. Although producers are asked to report tonnage based upon the location where it is placed, it is possible that data about mixtures reported for one state may include data from mixtures placed in two or more states. This can lead to overreporting in one state and underreporting in another. For example, a producer in Washington, D.C., may have produced mixtures used in Virginia and Maryland too, but may report all tons produced as Washington, D.C., tonnage.

These caveats apply to the data reported in Appendix B and other state-level data included in this report; however, they have only minimal impact on the national values in the main report.

Survey Instrument

As outlined earlier, this appendix includes a copy of the survey instruments used to collect responses from participants. The majority of asphalt mixture producers participating in the survey used the online survey platform SurveyMonkey® to provide their responses. Some producers submitted their data through PDF forms or a Microsoft Excel spreadsheet developed by NAPA to collect the same information. The producer section of the survey instrument begins on page 7; the SAPA section begins on page 24. The supplemental survey begins on page 28.

References

- Davis, C. (2019). Most States Have Raised Gas Taxes in Recent Years. *JustTaxes Blog*. Institute on Taxation and Economic Policy, Washington, D.C. <https://itep.org/most-states-have-raised-gas-taxes-in-recent-years-0419/> [Retrieved July 19, 2019]
- FHWA (2017). FAST Act Fact Sheet: Territorial and Puerto Rico Program [web page]. Federal Highway Administration, Washington, D.C. <https://www.fhwa.dot.gov/fastact/factsheets/territorialprhighwaysfs.cfm> [Accessed 31 December 2019]
- FHWA (2021). FAST ACT Funding Tables: Chapter 11, Table FA-4: Summary of Apportionments Authorized for Fiscal Year (FY) 2020 [web page]. Federal Highway Administration, Washington, D.C. <https://www.fhwa.dot.gov/policyinformation/statistics/2020/pdf/fa4.pdf> [Accessed 16 November 2021]
- Hansen, K.R., & D.E. Newcomb (2011). *Asphalt Pavement Mix Production Survey: Reclaimed Asphalt Pavement, Reclaimed Asphalt Shingles, Warm-Mix Asphalt Usage: 2009–2010* (IS 138). National Asphalt Pavement Association, Lanham, Maryland.
- NCSL (2021). Recent Legislative Actions Likely to Change Gas Taxes [web page]. National Conference of State Legislatures, Washington, D.C. <http://www.ncsl.org/research/transportation/2013-and-2014-legislative-actions-likely-to-change-gas-taxes.aspx> [Accessed 1 November 2021]
- T4America (n.d.). State Transportation Funding [web page]. Transportation for America, Washington, D.C. <http://t4america.org/maps-tools/state-transportation-funding/> [Accessed 31 May 2019]
- Williams, B.A., J.R. Willis, & Shacat, J. (2021). *Annual Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020, 11th Annual Survey* (IS 138). National Asphalt Pavement Association, Greenbelt, Maryland.

2020 Construction Season Survey Instrument – Producer Section



Purpose

It is important for the industry that you complete this survey so that we have accurate information regarding the use of recycled materials and WMA and to identify areas needing assistance in implementation.

DATA FROM THIS SURVEY WILL BE CONFIDENTIAL AND WILL BE USED ONLY FOR THE PURPOSES OF DETERMINING THESE QUANTITIES. IT WILL NOT BE USED FOR ANY OTHER PURPOSE. DATA WILL BE REPORTED BY STATE ONLY, AND NO STATE-SPECIFIC DATA WILL BE REPORTED WHEN FEWER THAN THREE COMPANIES/BRANCHES RESPOND WITHIN A STATE, **NO COMPANY-SPECIFIC INFORMATION WILL BE DISCLOSED IN ANY WAY.**

Survey results will be shared with industry, government agencies, and officials to help in the implementation of recycling and warm-mix technologies. The data collected from this survey provides insight into trends, current practice, and is utilized to highlight the sustainability of asphalt mixtures. These results are also used by FHWA, Energy Information Administration, Environmental Protection Agency, and other federal, state, and local agencies to determine the impact of recycled materials and WMA.

By completing this survey you will be eligible to receive a complimentary copy of the full report.

Your participation is greatly appreciated.

* 1. Are you a...

- ☐ Asphalt Producer
- ☐ State Asphalt Pavement Association (or similar)
- ☐ Other



Industry Contact Information

It is recommended that you print a copy of the full survey — download a PDF — to make sure you have the necessary data at hand before beginning the online survey.

The following information will be used only to confirm that we do not get duplicate information from a company and to contact you if we have any questions regarding your answers. Contact Brett Williams at bwilliams@asphaltpavement.org or NAPA by phone at 888-468-6499 if you have any questions.

*** 2. Company/Branch Name:**

*** 3. Contact Person's Name & Address**

*** 4. Contact Person's Email**

*** 5. Contact Person's Phone Number**

State

Please select the state for which you are providing the information.

*** Which state is the information provided for?**

- | | | |
|--|--|---|
| <input type="radio"/> Alabama | <input type="radio"/> Kentucky | <input type="radio"/> Ohio |
| <input type="radio"/> Alaska | <input type="radio"/> Louisiana | <input type="radio"/> Oklahoma |
| <input type="radio"/> American Samoa | <input type="radio"/> Maine | <input type="radio"/> Oregon |
| <input type="radio"/> Arizona | <input type="radio"/> Maryland | <input type="radio"/> Pennsylvania |
| <input type="radio"/> Arkansas | <input type="radio"/> Massachusetts | <input type="radio"/> Puerto Rico |
| <input type="radio"/> California | <input type="radio"/> Michigan | <input type="radio"/> Rhode Island |
| <input type="radio"/> Colorado | <input type="radio"/> Minnesota | <input type="radio"/> South Carolina |
| <input type="radio"/> Connecticut | <input type="radio"/> Mississippi | <input type="radio"/> South Dakota |
| <input type="radio"/> Delaware | <input type="radio"/> Missouri | <input type="radio"/> Tennessee |
| <input type="radio"/> District of Columbia | <input type="radio"/> Montana | <input type="radio"/> Texas |
| <input type="radio"/> Florida | <input type="radio"/> Nebraska | <input type="radio"/> US Virgin Islands |
| <input type="radio"/> Georgia | <input type="radio"/> Nevada | <input type="radio"/> Utah |
| <input type="radio"/> Guam | <input type="radio"/> New Hampshire | <input type="radio"/> Vermont |
| <input type="radio"/> Hawaii | <input type="radio"/> New Jersey | <input type="radio"/> Virginia |
| <input type="radio"/> Idaho | <input type="radio"/> New Mexico | <input type="radio"/> Washington |
| <input type="radio"/> Illinois | <input type="radio"/> New York | <input type="radio"/> West Virginia |
| <input type="radio"/> Indiana | <input type="radio"/> North Carolina | <input type="radio"/> Wisconsin |
| <input type="radio"/> Iowa | <input type="radio"/> North Dakota | <input type="radio"/> Wyoming |
| <input type="radio"/> Kansas | <input type="radio"/> Northern Mariana Islands | |

*** 7. How many plants does this survey response cover?**

Number of plants



Total Asphalt Tonnage for 2020

Please complete the following information for the total tonnage of all asphalt production in 2020.

*** 8. What was your total tonnage of asphalt mixes in 2020 for the following sectors? (Use best estimate if data is not available.)**

State DOT

Other Agency (City, County, FAA, Military, Toll Authorities)

Commercial & Residential



RAP Supply and Use 2020

Please complete the following information on the amount of RAP received and used for 2020.

*** Did you accept, process, or use RAP in the state during 2020?**

- ☐ Yes
☐ No

Please complete the following information regarding the amount of RAP received and used for 2020.

*** 10. How many tons of reclaimed asphalt pavement and asphalt millings were accepted/delivered to your facilities in the state in 2020?**

Tons:

*** 11. How many tons of RAP were used in 2020 for the following purposes? (Use best estimate if data not available.)**

Recycled Back into HMA/WMA Mixes:

Aggregate Base:

Cold Mix:

Other:

Landfilled:

*** 12. What was the average RAP percentage used in asphalt mixes during 2020 for the following sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military, Toll Authorities)

Commercial & Residential



RAP Supply and Use 2020

* 13. At the end of the year 2020 did you have excess RAP (processed or unprocessed) in inventory?

☐ Yes ☐ No

* 14. Please estimate how many tons of RAP you had stockpiled at the end of 2020. (Use best estimate if data not available.)

15. What percentage of the RAP processed is fractionated into two or more sizes? (Use best estimate if data not available.)

16. What percent of mixes using RAP were produced using a softer grade of asphalt binder? (Use best estimate if data not available.)

17. What percent of mixes using RAP were produced using recycling agents? (Use best estimate if data not available.)

Please complete the following information on the amount of waste shingles received (processed and unprocessed) and used for 2020.

* 18. Did you accept waste shingles and/or process or use reclaimed asphalt shingles (RAS) in 2020?

☐ Yes
☐ No



Reclaimed Asphalt Shingles (RAS) Supply and Use for 2020

Please complete the following information regarding the amount of waste shingles received (processed and unprocessed) and used during 2020.

*** 19. How many tons of shingles were accepted/delivered to your facilities in the state in 2020?**

Unprocessed

Tear-off Shingles:

Unprocessed

Manufacturers'

Waste Shingles:

Processed

Shingles:

*** 20. How many tons of reclaimed asphalt shingles (RAS) were used for the following purposes in 2020? (Use best estimate if data not available.)**

Recycled into HMA/WMA Mixes:

Aggregate Base:

Cold Mix:

Other:

Landfilled:

Reclaimed Asphalt Shingles (RAS) Supply and Use for 2020

*** 21. What was average RAS percentage used in asphalt mixes in 2020 for the following sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military, Toll Authorities)

Commercial & Residential

*** 22. At the end of the year 2020 did you have any surplus RAS stockpiled? (Include processed and unprocessed shingles.)**

☐ Yes ☐ No

*** 23. Please estimate how many tons of RAS you had stockpiled at the end of 2020. (Use best estimate if data not available.)**

24. Is RAS allowed in

	ALL	SOME	NONE
DOT mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>
Other Agency mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>
Commercial and Residential mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>

25. What percent of mixes using RAS were produced using a softer grade of asphalt binder? (Use best estimate if data not available.)

26. What percent of mixes using RAS were produced using recycling agents? (Use best estimate if data not available.)

Warm-Mix Asphalt Production for 2020

Warm-mix asphalt is the generic term for a variety of technologies that allow the producers of asphalt pavement material to lower the temperatures at which the material is mixed and placed on the road by at least 10°F. The survey will collect data for warm-mix technologies used at reduced temperature and at hot mix temperatures separately.

*** 27. Did any of your plants in this state use warm-mix asphalt technologies in 2020?**

- ☐ Yes
☐ No

Warm-mix asphalt is the generic term for a variety of technologies that allow the producers of asphalt pavement material to lower the temperatures at which the material is mixed and placed on the road by at least 10°F.

*** 28. What was average percent of mix tons produced using warm-mix asphalt technologies in 2020 for the different sectors? (Use best estimate if data not available.)**

State DOT

Other Agency (City, County, FAA, Military, Toll Authorities)

Commercial & Residential

29. What percentage of the total warm-mix asphalt (WMA) for 2020 was produced using the following technologies? (Use best estimate if data not available, entries should total 100%)

Chemical Admixture

Additive (Zeolite) Foaming

Plant Foaming

Organic (Wax) Additive

Blend

*Please specify the Blend:



Warm-Mix Asphalt Production for 2020

30. What was average percent of mix tons using warm-mix technologies for mixes produced at hot-mix temperatures (i.e., without lowering temperatures by at least 10°F.)

State DOT

Other Agency (City, County, FAA, Military,
Toll Authorities)

Commercial & Residential

***31. What percentage of the total warm-mix asphalt (WMA) produced at hot mix temperatures (i.e., without lowering temperatures by at least 10°F.) for 2020 was produced using the following technologies? (Use best estimate if data not available, entries should total 100%)**

Chemical Admixture

Additive (Zeolite) Foaming

Plant Foaming

Organic (Wax) Additive

Blend

*Please specify the Blend:

Other Recycled Material for 2020

Please let us know if you used any other recycled materials in HMA/WMA mixes in 2020.

*** 32. Did you use other recycled materials (excluding RAP and RAS) in your mixes in 2020?**

*(This includes materials added to the mix such as: ground tire rubber, blast furnace slag, steel slag, boiler slag, fly ash, bottom ash, foundry sand, other coal combustion products, glass, cellulose fibers, etc.)

☐ Yes

☐ No

*** 33. What other recycled material (excluding RAP and RAS) did you use in your mixes in 2020?**

	Yes	No
Ground Tire Rubber	<input type="radio"/>	<input type="radio"/>
Steel Slag	<input type="radio"/>	<input type="radio"/>
Blast Furnace Slag	<input type="radio"/>	<input type="radio"/>
Recycled Cellulose Fibers	<input type="radio"/>	<input type="radio"/>
Other 1*	<input type="radio"/>	<input type="radio"/>
Other 2*	<input type="radio"/>	<input type="radio"/>

* Please describe the other recycled materials used.

*** 34. How many tons of HMA/WMA was produced using this product. (Use best estimate if data not available.)**

Ground Tire Rubber	<div></div>
Steel Slag	<div></div>
Blast Furnace Slag	<div></div>
Recycled Cellulose Fibers	<div></div>
Other 1	<div></div>
Other 2	<div></div>



Other Recycled Material for 2020

35. How many tons of the recycled product was used in 2020? (Enter 0 if you do not have a reasonable estimate of this quantity)

Ground Tire Rubber

Steel Slag

Blast Furnace Slag

Recycled Cellulose Fibers

Other 1

Other 2



Purpose

35. Would you like a complimentary copy of the final report?

☐ Yes ☐ No

If your company provides any of the following services: CIR, HIR, CCPR, or FDR, we ask that you to fill out a very short survey providing quantities of these activities in 2020. The link to the survey is here: https://www.surveymonkey.com/r/2020_IPR_Survey. Thank you for your time in helping document some of the asphalt industries efforts in sustainability and recycling.



SAPA Contact Information

This survey is intended to collect information from State Asphalt Pavement Associations or similar associations. Please answer the following questions by April 1, 2021, to assist NAPA in preparing the 2020 Recycled Materials and WMA Survey. The additional information you provide us on RAP and RAS will enhance the information we provide in the survey report. Contact Brett Williams at bwilliams@asphaltpavement.org or NAPA by phone at 888-468-6499 if you have any questions.

*** 37. Association Name:**

Contact

*** 38. Name**

SAPA Information

* 39. Which state is the information provided for?

- | | | |
|--|--|---|
| <input type="radio"/> Alabama | <input type="radio"/> Kentucky | <input type="radio"/> Ohio |
| <input type="radio"/> Alaska | <input type="radio"/> Louisiana | <input type="radio"/> Oklahoma |
| <input type="radio"/> American Samoa | <input type="radio"/> Maine | <input type="radio"/> Oregon |
| <input type="radio"/> Arizona | <input type="radio"/> Maryland | <input type="radio"/> Pennsylvania |
| <input type="radio"/> Arkansas | <input type="radio"/> Massachusetts | <input type="radio"/> Puerto Rico |
| <input type="radio"/> California | <input type="radio"/> Michigan | <input type="radio"/> Rhode Island |
| <input type="radio"/> Colorado | <input type="radio"/> Minnesota | <input type="radio"/> South Carolina |
| <input type="radio"/> Connecticut | <input type="radio"/> Mississippi | <input type="radio"/> South Dakota |
| <input type="radio"/> Delaware | <input type="radio"/> Missouri | <input type="radio"/> Tennessee |
| <input type="radio"/> District of Columbia | <input type="radio"/> Montana | <input type="radio"/> Texas |
| <input type="radio"/> Florida | <input type="radio"/> Nebraska | <input type="radio"/> US Virgin Islands |
| <input type="radio"/> Georgia | <input type="radio"/> Nevada | <input type="radio"/> Utah |
| <input type="radio"/> Guam | <input type="radio"/> New Hampshire | <input type="radio"/> Vermont |
| <input type="radio"/> Hawaii | <input type="radio"/> New Jersey | <input type="radio"/> Virginia |
| <input type="radio"/> Idaho | <input type="radio"/> New Mexico | <input type="radio"/> Washington |
| <input type="radio"/> Illinois | <input type="radio"/> New York | <input type="radio"/> West Virginia |
| <input type="radio"/> Indiana | <input type="radio"/> North Carolina | <input type="radio"/> Wisconsin |
| <input type="radio"/> Iowa | <input type="radio"/> North Dakota | <input type="radio"/> Wyoming |
| <input type="radio"/> Kansas | <input type="radio"/> Northern Mariana Islands | |

* 40. What is your best estimate of the total tons of asphalt mixture placed in your state in 2020? (This includes asphalt mixture tonnage for all sectors, ex. DOT, Other Agencies, Commercial & Residential) [2019 Estimates are provided below for your reference.]

SAPA Information

Table 3: Summary of 2019 Estimated and Reported Asphalt Mixture Tons in Each State

State	Tons, Millions		Reported % of Estimated	State	Tons, Millions		Reported % of Estimated
	Estimated	Reported			Estimated	Reported	
Alabama	6.5	3.2	49%	Montana	4.2	*	*
Alaska	5.1	*	*	Nebraska	2.8	*	*
American Samoa	0.03	*	*	Nevada	3.4	*	*
Arizona	8.4	3.9	46%	New Hampshire	1.3	*	*
Arkansas	6.0	2.3	38%	New Jersey	11.8	6.8	58%
California	25.9	7.9	31%	New Mexico	3.7	*	*
Colorado	8.7	4.4	51%	New York	17.5	6.7	38%
Connecticut	5.0	2.3	46%	North Carolina	15.0	7.7	51%
Delaware	1.3	NCR	NCR	North Dakota	2.3	*	*
District of Columbia	1.3	*	*	No. Mariana Isl.	0.03	NCR	NCR
Florida	16.0	9.7	61%	Ohio	19.4	11.2	58%
Georgia	17.4	*	*	Oklahoma	5.5	2.0	36%
Guam	0.12	NCR	NCR	Oregon	5.3	1.9	36%
Hawaii	0.9	0.7	78%	Pennsylvania	20.5	2.6	13%
Idaho	2.7	1.5	56%	Puerto Rico	1.4	NCR	NCR
Illinois	13.6	1.5	11%	Rhode Island	1.9	*	*
Indiana	13.0	4.6	35%	South Carolina	8.9	3.3	37%
Iowa	3.7	0.9	24%	South Dakota	2.6	NCR	NCR
Kansas	2.8	*	*	Tennessee	10.1	8.2	81%
Kentucky	6.0	2.5	42%	Texas	40.0	5.9	15%
Louisiana	6.8	1.2	18%	U.S. Virgin Isl.	0.09	NCR	NCR
Maine	1.1	*	*	Utah	4.2	2.9	69%
Maryland	7.0	1.7	24%	Vermont	1.7	*	*
Massachusetts	6.5	2.1	32%	Virginia	12.0	5.8	48%
Michigan	15.1	7.9	52%	Washington	6.3	4.4	70%
Minnesota	11.0	5.6	51%	West Virginia	4.2	2.3	55%
Mississippi	2.9	2.2	76%	Wisconsin	12.0	8.7	73%
Missouri	6.8	2.7	40%	Wyoming	2.3	*	*
Total					421.9	161.7 ⁺	38%

No Companies Responding

Fewer than 3 Companies Reporting

Total Reported Tons includes values from state with fewer than 3 Companies Reporting



SAPA Estimated Tons

Numbers do not add up exactly due to rounding

SAPA Information

41. Tonnage Estimate Comments

* 42. Do producers in your state fractionate RAP?

☐ Yes

☐ No

* 43. Is RAS allowed in

	ALL	SOME	NONE
DOT mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>
Other Agency mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>
Commercial and Residential mixes	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>

Comments:

* 44. Does your state require, allow, or prohibit the use of recycling agents or softer binders in high Asphalt Binder Replacement mixtures? (RAP, RAS, RAP & RAS)

	Require	Allow	Prohibit
Recycling Agent	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>
Softer Binders	<input type="radio"/>	<input type="radio"/>	<input type="radio"/>

Comments:



Purpose

The National Asphalt Pavement Association is working with the Federal Highway Administration to determine the amount of recycled materials being utilized for in-place recycling (Cold-In-Place, Hot In-Place, Cold Central Plant Recycling, and Full-Depth Reclamation). This survey will be used to collect this data.

It is important for the industry that you complete this survey so that we have accurate information regarding the use of recycled materials and to identify areas needing assistance in implementation.

DATA FROM THIS SURVEY WILL BE CONFIDENTIAL AND WILL BE USED ONLY FOR THE PURPOSES OF DETERMINING THESE QUANTITIES. IT WILL NOT BE USED FOR ANY OTHER PURPOSE. DATA WILL BE REPORTED REGIONALLY, AND NO REGIONAL DATA WILL BE REPORTED WHEN FEWER THAN THREE COMPANIES/BRANCHES RESPOND, NO COMPANY-SPECIFIC INFORMATION WILL BE DISCLOSED IN ANY WAY.

Survey results will help the industry, government agencies, and officials with the continued implementation of recycling. The data collected from this survey provides insight into trends, current practice, and is utilized to highlight the sustainability of asphalt mixtures. These results are also used by FHWA, Energy Information Administration, Environmental Protection Agency, and other federal, state, and local agencies to determine the impact of recycled materials.

By completing this survey you will be eligible to receive a complimentary copy of the full report.

Your participation is greatly appreciated.



Industry Contact Information

Companies with multi-state operations will need to fill in the survey for each state.

The following information will be used only to confirm that we do not get duplicate information from a company and to contact you if we have any questions regarding your answers. Contact Brett Williams at bwilliams@asphaltpavement.org or NAPA by phone at 888-468-6499 if you have any questions.

*** 1. Company/Branch Name:**

*** 2. Contact Person's Name & Address**

*** 3. Contact Person's Email**

*** 4. Contact Person's Phone Number**



State

* 5. Which state is the information provided for?

- | | | |
|--|--|---|
| <input type="radio"/> Alabama | <input type="radio"/> Kentucky | <input type="radio"/> Ohio |
| <input type="radio"/> Alaska | <input type="radio"/> Louisiana | <input type="radio"/> Oklahoma |
| <input type="radio"/> American Samoa | <input type="radio"/> Maine | <input type="radio"/> Oregon |
| <input type="radio"/> Arizona | <input type="radio"/> Maryland | <input type="radio"/> Pennsylvania |
| <input type="radio"/> Arkansas | <input type="radio"/> Massachusetts | <input type="radio"/> Puerto Rico |
| <input type="radio"/> California | <input type="radio"/> Michigan | <input type="radio"/> Rhode Island |
| <input type="radio"/> Colorado | <input type="radio"/> Minnesota | <input type="radio"/> South Carolina |
| <input type="radio"/> Connecticut | <input type="radio"/> Mississippi | <input type="radio"/> South Dakota |
| <input type="radio"/> Delaware | <input type="radio"/> Missouri | <input type="radio"/> Tennessee |
| <input type="radio"/> District of Columbia | <input type="radio"/> Montana | <input type="radio"/> Texas |
| <input type="radio"/> Florida | <input type="radio"/> Nebraska | <input type="radio"/> US Virgin Islands |
| <input type="radio"/> Georgia | <input type="radio"/> Nevada | <input type="radio"/> Utah |
| <input type="radio"/> Guam | <input type="radio"/> New Hampshire | <input type="radio"/> Vermont |
| <input type="radio"/> Hawaii | <input type="radio"/> New Jersey | <input type="radio"/> Virginia |
| <input type="radio"/> Idaho | <input type="radio"/> New Mexico | <input type="radio"/> Washington |
| <input type="radio"/> Illinois | <input type="radio"/> New York | <input type="radio"/> West Virginia |
| <input type="radio"/> Indiana | <input type="radio"/> North Carolina | <input type="radio"/> Wisconsin |
| <input type="radio"/> Iowa | <input type="radio"/> North Dakota | <input type="radio"/> Wyoming |
| <input type="radio"/> Kansas | <input type="radio"/> Northern Mariana Islands | |

Total Quantities for 2020

Please complete the following information for the total quantities of all CIR, HIR, CCPR, and FDR in 2020.

- * 6. What was your state-wide total quantity of in-place recycling in 2020? (Use best estimate if exact data is not available. Please provide the units in your answer, either weight or volume can be submitted, so examples of units could be Tons, Metric Tons, Cubic Yards, Square Yards @ inches of thickness, and the list goes on...)

Hot In-Place Recycling (HIR)

Cold Central Plant Recycling (CCPR)

Cold In-Place Recycling (CIR)

Full-Depth Reclamation (FDR)



Thank You

7. Would you like a complimentary copy of the final report?

- ☐ Yes
- ☐ No



National Asphalt Pavement Association

6406 Ivy Lane, Suite 350
Greenbelt, Maryland 20770-1441

www.AsphaltPavement.org

napa@AsphaltPavement.org

Toll Free: 888-468-6499

Tel: 301-731-4748

Fax: 301-731-4621

Publication Sales

Login at <https://member.asphaltpavement.org/Shop/Product-Catalog>

Toll Free: 888-600-4474

Tel: 412-741-6314

Fax: 412-741-0609

11th Annual Asphalt Pavement Industry Survey IS 138 — Appendix A



Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2020

IS-138 Appendix B:
State-by-State Use of
Recycled Materials and Warm-Mix Asphalt
In Asphalt Pavement Mixtures



11th Annual Survey

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020

Appendix B

Introduction

Appendix B provides a state-by-state breakdown of data reported in the *Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage* report for the 2020 construction season survey (Williams et al., 2021), including information from Tables 5, 6, 7, 8, 11, 12 and 15. **The accuracy of the state-level data and estimates will vary depending upon the number of companies participating in the survey in a given state and the tonnage produced by each respondent.** Appendix A outlines the methodology used to collect data and to generate estimates.

Appendix B reports data for all 50 U.S. states, as well as the District of Columbia and the five U.S. territories. In instances where fewer than three companies in a state/territory responded to the survey, only estimated total tonnages are reported to protect proprietary company data. Table 1 in the main report, republished below, summarizes the number of respondents from each state and territory. A total of 274 companies representing 1,406 production plants responded to the 2020 construction season survey. Branches, subsidiaries, and operating units are counted as unique companies in Table 1 and throughout the report. Throughout the tables, where percentages and totals are calculated, the numbers may not add up exactly due to rounding.

A degree of fluctuation in year-to-year comparisons of data is influenced by which companies responded to the 2020 construction season survey versus prior-year survey respondents. Approximately 85 percent of 2019 responding companies participated in the 2020 survey, too. Additional factors influencing the reliability of state-level data in this appendix are explained in the Data Estimation Method section of Appendix A.

Table 1: Number of Companies Completing 2020 Construction Season Survey in Each State/Territory

State	Cos.	Prod. Plants	State	Cos.	Prod. Plants	State	Cos.	Prod. Plants
Alabama	4	24	Kentucky	5	25	Ohio	12	98
Alaska	*	*	Louisiana	3	8	Oklahoma	9	26
American Samoa	NCR	NCR	Maine	3	24	Oregon	5	15
Arizona	4	25	Maryland	8	18	Pennsylvania	10	53
Arkansas	6	25	Massachusetts	4	15	Puerto Rico	NCR	NCR
California	5	61	Michigan	9	50	Rhode Island	*	*
Colorado	7	28	Minnesota	5	36	South Carolina	6	23
Connecticut	*	*	Mississippi	7	26	South Dakota	*	*
Delaware	*	*	Missouri	5	16	Tennessee	7	39
District of Columbia	*	*	Montana	*	*	Texas	4	35
Florida	8	47	Nebraska	3	6	U.S. Virgin Islands	NCR	NCR
Georgia	6	58	Nevada	4	6	Utah	9	20
Guam	NCR	NCR	New Hampshire	3	16	Vermont	*	*
Hawaii	*	*	New Jersey	4	20	Virginia	9	46
Idaho	5	18	New Mexico	*	*	Washington	9	49
Illinois	21	64	New York	13	63	West Virginia	3	16
Indiana	7	43	North Carolina	9	83	Wisconsin	5	68
Iowa	4	19	North Dakota	*	*	Wyoming	*	*
Kansas	3	18	No. Mariana Islands	NCR	NCR	Total†	274	1406

NCR = No companies responding

* = Fewer than 3 companies reporting

† = Total includes companies/production plants from states with fewer than 3 companies reporting.

ALABAMA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	3.2	2.5	6.5	7.0
	DOT	1.8	1.4	3.7	3.9
	Other Agency	0.6	0.5	1.1	1.4
	Commercial & Residential	0.8	0.6	1.7	1.7
	No. of Companies Reporting	6	4		
RAP (Tons, Millions)	Accepted	0.8	0.5	1.6	1.5
	Used in HMA/WMA Mixtures	0.8	0.6	1.6	1.7
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.80	0.76	1.62	2.13
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	24.9%	23.3%		
	Average % for Other Agency Mixtures ¹	21.1%	24.3%		
	Average % for Commercial & Residential Mixtures ¹	25.3%	25.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			24.6%	24.3%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	19%	35%		
	% of RAP Mixtures Using Softer Binders	0%	1%		
	% of RAP Mixtures Using Recycling Agents	0%	8%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.2	0.0	0.3	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.2	0.0	0.3	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	15.0	0.0	30.5	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.02%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.01%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	17%	0%		
	% of RAS Mixtures Using Softer Binders	8%	0%		
	% of RAS Mixtures Using Recycling Agents	1%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.7 (Tons, Millions)	0.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.0 (Tons, Millions)	2.3 (Tons, Millions)
	DOT	14%	28%	0.5 (Tons, Millions)	1.1 (Tons, Millions)
	Other Agency	0%	30%	0.0 (Tons, Millions)	0.4 (Tons, Millions)
	Commercial & Residential	9%	48%	0.2 (Tons, Millions)	0.8 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	4%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	96%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	17%	25%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

ALASKA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	5.1	5.1
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

AMERICAN SAMOA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	NCR	0.03	0.02
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial & Residential	*	NCR	*	NCR
	No. of Companies Reporting	*	NCR		
RAP (Tons, Millions)	Accepted	*	NCR	*	NCR
	Used in HMA/WMA Mixtures	*	NCR	*	NCR
	Used as Aggregate	*	NCR	*	NCR
	Used in Cold-Mix Asphalt	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
	Total Tons of RAP Stockpiled at Year-End	*	NCR	*	NCR
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	NCR		
	Average % for Other Agency Mixtures ¹	*	NCR		
	Average % for Commercial & Residential Mixtures ¹	*	NCR		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	NCR
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	NCR		
	% of RAP Fractionated	*	NCR		
	% of RAP Mixtures Using Softer Binders	*	NCR		
	% of RAP Mixtures Using Recycling Agents	*	NCR		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	NCR	*	NCR
	Processed Shingles Accepted	*	NCR	*	NCR
	Used in HMA/WMA Mixtures	*	NCR	*	NCR
	Used as Aggregate	*	NCR	*	NCR
	Used in Cold-Mix Asphalt	*	NCR	*	NCR
	Used in Other	*	NCR	*	NCR
	Landfilled	*	NCR	*	NCR
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	NCR	*	NCR
	Average % for DOT Mixtures ¹	*	NCR		
	Average % for Other Agency Mixtures ¹	*	NCR		
	Average % for Commercial & Residential Mixtures ¹	*	NCR		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	NCR
	% Companies Reporting Using RAS	*	NCR		
	% of RAS Mixtures Using Softer Binders	*	NCR		
	% of RAS Mixtures Using Recycling Agents	*	NCR		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	NCR
	Total Tons Produced With WMA Technology at HMA Temperatures			*	NCR
	DOT	*	NCR	*	NCR
	Other Agency	*	NCR	*	NCR
	Commercial & Residential	*	NCR	*	NCR
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	NCR		
	Additive Foaming, % of Market	*	NCR		
	Plant Foaming, % of Market	*	NCR		
	Organic Additive, % of Market	*	NCR		
	% Companies Reporting Using WMA Technologies	*	NCR		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

ARIZONA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	3.9	4.2	8.4	7.4
	DOT	1.7	0.5	3.7	0.9
	Other Agency	0.1	1.6	0.3	2.8
	Commercial & Residential	2.0	2.1	4.4	3.7
	No. of Companies Reporting	3	4		
RAP (Tons, Millions)	Accepted	0.6	0.4	1.3	0.7
	Used in HMA/WMA Mixtures	0.4	0.3	0.8	0.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.46	0.58	0.99	1.02
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	8.0%	9.3%		
	Average % for Other Agency Mixtures ¹	8.0%	5.0%		
	Average % for Commercial & Residential Mixtures ¹	12.0%	10.7%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			9.2%	6.9%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	13%		
	% of RAP Mixtures Using Softer Binders	2%	15%		
	% of RAP Mixtures Using Recycling Agents	0%	16%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.1 (Tons, Millions)	0.2 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.0 (Tons, Millions)	1.9 (Tons, Millions)
	DOT	2%	0%	0.1 (Tons, Millions)	0.0 (Tons, Millions)
	Other Agency	15%	70%	0.0 (Tons, Millions)	2.0 (Tons, Millions)
	Commercial & Residential	1%	4%	0.0 (Tons, Millions)	0.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	56%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	0%		
	Organic Additive, % of Market	0%	44%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

ARKANSAS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.3	2.9	6.0	6.0
	DOT	1.4	1.8	3.7	3.7
	Other Agency	0.4	0.6	1.1	1.2
	Commercial & Residential	0.5	0.5	1.3	1.0
	No. of Companies Reporting	8	6		
RAP (Tons, Millions)	Accepted	0.2	0.4	0.6	0.9
	Used in HMA/WMA Mixtures	0.3	0.4	0.8	0.8
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.18	0.45	0.46	0.93
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	15.6%	14.8%		
	Average % for Other Agency Mixtures ¹	13.1%	13.6%		
	Average % for Commercial & Residential Mixtures ¹	10.8%	10.5%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			12.9%	13.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	15%	37%		
	% of RAP Mixtures Using Softer Binders	8%	0%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	12.0	0.0	31.3	0.0
	Processed Shingles Accepted	10.6	8.9	27.6	18.5
	Used in HMA/WMA Mixtures	9.6	6.0	25.0	12.3
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	10.8	4.7	28.1	9.6
	Average % for DOT Mixtures ¹	0.41%	0.21%		
	Average % for Other Agency Mixtures ¹	0.41%	0.21%		
	Average % for Commercial & Residential Mixtures ¹	0.44%	0.21%		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.42%	0.21%
	% Companies Reporting Using RAS	50%	17%		
	% of RAS Mixtures Using Softer Binders	2%	0%		
	% of RAS Mixtures Using Recycling Agents	13%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.5 (Tons, Millions)	2.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.1 (Tons, Millions)	1.2 (Tons, Millions)
	DOT	36%	66%	1.3 (Tons, Millions)	2.5 (Tons, Millions)
	Other Agency	7%	55%	0.1 (Tons, Millions)	0.7 (Tons, Millions)
	Commercial & Residential	20%	57%	0.3 (Tons, Millions)	0.6 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	0%	1%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	100%	99%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	38%	67%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

CALIFORNIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	7.9	12.2	25.9	25.4
	DOT	1.5	2.7	4.8	5.6
	Other Agency	1.0	3.2	3.4	6.7
	Commercial & Residential	5.4	6.3	17.7	13.1
	No. of Companies Reporting	3	5		
RAP (Tons, Millions)	Accepted	1.4	2.3	4.7	4.8
	Used in HMA/WMA Mixtures	1.2	1.9	4.1	3.9
	Used as Aggregate	0.0	0.3	0.0	0.6
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.69	2.08	2.29	4.33
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	14.7%	15.0%		
	Average % for Other Agency Mixtures ¹	9.7%	14.0%		
	Average % for Commercial & Residential Mixtures ¹	16.3%	18.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			15.7%	15.3%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	3%	41%		
	% of RAP Mixtures Using Softer Binders	5%	3%		
	% of RAP Mixtures Using Recycling Agents	32%	35%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	3.0	0.0	6.2
	Processed Shingles Accepted	2.4	0.0	7.9	0.0
	Used in HMA/WMA Mixtures	2.0	3.0	6.6	6.2
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	3.3	0.0	10.9	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.03%	0.00%		
	Average % for Other Agency Mixtures ¹	0.03%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.03%	0.04%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.03%	0.02%
RAS (Other Reported Data)	% Companies Reporting Using RAS	33%	20%		
	% of RAS Mixtures Using Softer Binders	15%	20%		
	% of RAS Mixtures Using Recycling Agents	0%	20%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			9.0 (Tons, Millions)	7.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			7.6 (Tons, Millions)	0.4 (Tons, Millions)
	DOT	64%	14%	3.1 (Tons, Millions)	0.8 (Tons, Millions)
	Other Agency	77%	19%	2.6 (Tons, Millions)	1.3 (Tons, Millions)
	Commercial & Residential	62%	45%	11.0 (Tons, Millions)	5.9 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	6%	63%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	94%	37%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	63%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

COLORADO

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	4.4	4.9	8.7	9.0
	DOT	0.8	1.1	1.5	2.0
	Other Agency	1.9	1.9	3.7	3.5
	Commercial & Residential	1.7	1.9	3.5	3.5
	No. of Companies Reporting	5	7		
RAP (Tons, Millions)	Accepted	1.2	1.4	2.5	2.6
	Used in HMA/WMA Mixtures	0.8	0.9	1.7	1.7
	Used as Aggregate	0.3	0.3	0.6	0.6
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.66	0.86	1.32	1.57
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	18.0%	21.1%		
	Average % for Other Agency Mixtures ¹	19.6%	16.8%		
	Average % for Commercial & Residential Mixtures ¹	20.4%	18.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			19.5%	19.0%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	43%	26%		
	% of RAP Mixtures Using Softer Binders	21%	30%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.3 (Tons, Millions)	1.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.7 (Tons, Millions)	5.7 (Tons, Millions)
	DOT	27%	71%	0.4 (Tons, Millions)	1.4 (Tons, Millions)
	Other Agency	27%	70%	1.0 (Tons, Millions)	2.4 (Tons, Millions)
	Commercial & Residential	15%	82%	0.5 (Tons, Millions)	2.9 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	77%	92%		
	Additive Foaming, % of Market	0%	1%		
	Plant Foaming, % of Market	23%	7%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

CONNECTICUT

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.3	*	5.0	4.9
	DOT	0.4	*	0.9	*
	Other Agency	0.9	*	1.9	*
	Commercial & Residential	1.0	*	2.2	*
	No. of Companies Reporting	3	*		
RAP (Tons, Millions)	Accepted	0.5	*	1.1	*
	Used in HMA/WMA Mixtures	0.5	*	1.0	*
	Used as Aggregate	0.0	*	0.0	*
	Used in Cold-Mix Asphalt	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
	Total Tons of RAP Stockpiled at Year-End	0.20	*	0.44	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.0%	*		
	Average % for Other Agency Mixtures ¹	19.4%	*		
	Average % for Commercial & Residential Mixtures ¹	23.1%	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			20.7%	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	*		
	% of RAP Fractionated	20%	*		
	% of RAP Mixtures Using Softer Binders	0%	*		
	% of RAP Mixtures Using Recycling Agents	16%	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	*	0.0	*
	Processed Shingles Accepted	0.4	*	0.9	*
	Used in HMA/WMA Mixtures	0.4	*	0.9	*
	Used as Aggregate	0.0	*	0.0	*
	Used in Cold-Mix Asphalt	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
	Total Tons of RAS Stockpiled at Year-End	0.2	*	0.4	*
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	*		
	Average % for Other Agency Mixtures ¹	0.00%	*		
	Average % for Commercial & Residential Mixtures ¹	0.06%	*		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.02%	*
RAS (Other Reported Data)	% Companies Reporting Using RAS	33%	*		
	% of RAS Mixtures Using Softer Binders	0%	*		
	% of RAS Mixtures Using Recycling Agents	0%	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.1 (Tons, Millions)	*
	Total Tons Produced With WMA Technology at HMA Temperatures			3.3 (Tons, Millions)	*
	DOT	96%	*	0.9 (Tons, Millions)	*
	Other Agency	62%	*	1.2 (Tons, Millions)	*
	Commercial & Residential	62%	*	1.3 (Tons, Millions)	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	6%	*		
	Additive Foaming, % of Market	0%	*		
	Plant Foaming, % of Market	94%	*		
	Organic Additive, % of Market	0%	*		
	% Companies Reporting Using WMA Technologies	66%	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

DELAWARE

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	*	1.3	1.3
	DOT	NCR	*	NCR	*
	Other Agency	NCR	*	NCR	*
	Commercial & Residential	NCR	*	NCR	*
	No. of Companies Reporting	NCR	*		
RAP (Tons, Millions)	Accepted	NCR	*	NCR	*
	Used in HMA/WMA Mixtures	NCR	*	NCR	*
	Used as Aggregate	NCR	*	NCR	*
	Used in Cold-Mix Asphalt	NCR	*	NCR	*
	Used in Other	NCR	*	NCR	*
	Landfilled	NCR	*	NCR	*
	Total Tons of RAP Stockpiled at Year-End	NCR	*	NCR	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	*		
	Average % for Other Agency Mixtures ¹	NCR	*		
	Average % for Commercial & Residential Mixtures ¹	NCR	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	*		
	% of RAP Fractionated	NCR	*		
	% of RAP Mixtures Using Softer Binders	NCR	*		
	% of RAP Mixtures Using Recycling Agents	NCR	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	*	NCR	*
	Processed Shingles Accepted	NCR	*	NCR	*
	Used in HMA/WMA Mixtures	NCR	*	NCR	*
	Used as Aggregate	NCR	*	NCR	*
	Used in Cold-Mix Asphalt	NCR	*	NCR	*
	Used in Other	NCR	*	NCR	*
	Landfilled	NCR	*	NCR	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	*	NCR	*
	Average % for DOT Mixtures ¹	NCR	*		
	Average % for Other Agency Mixtures ¹	NCR	*		
	Average % for Commercial & Residential Mixtures ¹	NCR	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	*
	% Companies Reporting Using RAS	NCR	*		
	% of RAS Mixtures Using Softer Binders	NCR	*		
	% of RAS Mixtures Using Recycling Agents	NCR	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	*
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	*
	DOT	NCR	*	NCR	*
	Other Agency	NCR	*	NCR	*
	Commercial & Residential	NCR	*	NCR	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	*		
	Additive Foaming, % of Market	NCR	*		
	Plant Foaming, % of Market	NCR	*		
	Organic Additive, % of Market	NCR	*		
	% Companies Reporting Using WMA Technologies	NCR	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

DISTRICT OF COLUMBIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	1.3	1.2
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

FLORIDA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	9.7	11.2	16.0	16.8
	DOT	3.5	4.4	5.8	6.6
	Other Agency	1.9	2.1	3.2	3.2
	Commercial & Residential	4.2	4.7	7.0	7.1
	No. of Companies Reporting	9	8		
RAP (Tons, Millions)	Accepted	2.3	3.4	3.9	5.1
	Used in HMA/WMA Mixtures	3.0	3.8	4.9	5.6
	Used as Aggregate	0.1	0.0	0.1	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.1
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	2.24	3.62	3.69	5.43
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	22.9%	28.0%		
	Average % for Other Agency Mixtures ¹	30.4%	33.3%		
	Average % for Commercial & Residential Mixtures ¹	32.6%	36.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			30.5%	33.6%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	15%	14%		
	% of RAP Mixtures Using Softer Binders	64%	69%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.3 (Tons, Millions)	1.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.4 (Tons, Millions)	4.2 (Tons, Millions)
	DOT	29%	46%	1.7 (Tons, Millions)	3.1 (Tons, Millions)
	Other Agency	18%	43%	0.6 (Tons, Millions)	1.4 (Tons, Millions)
	Commercial & Residential	7%	19%	0.5 (Tons, Millions)	1.3 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	100%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	0%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	22%	63%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

GEORGIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	7.4	17.4	13.6
	DOT	*	3.8	*	7.0
	Other Agency	*	2.0	*	3.7
	Commercial & Residential	*	1.6	*	2.9
	No. of Companies Reporting	*	6		
RAP (Tons, Millions)	Accepted	*	2.0	*	3.6
	Used in HMA/WMA Mixtures	*	2.1	*	3.8
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	3.31	*	6.07
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	25.8%		
	Average % for Other Agency Mixtures ¹	*	27.8%		
	Average % for Commercial & Residential Mixtures ¹	*	29.5%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	28.2%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	8%		
	% of RAP Mixtures Using Softer Binders	*	18%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	0.0	*	0.0
	Processed Shingles Accepted	*	0.0	*	0.0
	Used in HMA/WMA Mixtures	*	0.0	*	0.0
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	0.0	*	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.00%		
	Average % for Other Agency Mixtures ¹	*	0.00%		
	Average % for Commercial & Residential Mixtures ¹	*	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	0%		
	% of RAS Mixtures Using Softer Binders	*	0%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	4.1 (Tons, Millions)
	DOT	*	45%	*	3.1 (Tons, Millions)
	Other Agency	*	32%	*	1.2 (Tons, Millions)
	Commercial & Residential	*	12%	*	0.4 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	8%		
	Additive Foaming, % of Market	*	0%		
	Plant Foaming, % of Market	*	92%		
	Organic Additive, % of Market	*	0%		
	% Companies Reporting Using WMA Technologies	*	33%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

GUAM

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	NCR	0.12	0.1
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
	No. of Companies Reporting	NCR	NCR		
RAP (Tons, Millions)	Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
	Total Tons of RAP Stockpiled at Year-End	NCR	NCR	NCR	NCR
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	NCR
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	NCR		
	% of RAP Fractionated	NCR	NCR		
	% of RAP Mixtures Using Softer Binders	NCR	NCR		
	% of RAP Mixtures Using Recycling Agents	NCR	NCR		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	NCR	NCR	NCR
	Processed Shingles Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	NCR	NCR	NCR
	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	NCR
	% Companies Reporting Using RAS	NCR	NCR		
	% of RAS Mixtures Using Softer Binders	NCR	NCR		
	% of RAS Mixtures Using Recycling Agents	NCR	NCR		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	NCR
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	NCR
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	NCR		
	Additive Foaming, % of Market	NCR	NCR		
	Plant Foaming, % of Market	NCR	NCR		
	Organic Additive, % of Market	NCR	NCR		
	% Companies Reporting Using WMA Technologies	NCR	NCR		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

HAWAII

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	0.7	*	0.9	0.8
	DOT	0.3	*	0.4	*
	Other Agency	0.2	*	0.3	*
	Commercial & Residential	0.2	*	0.2	*
	No. of Companies Reporting	4	*		
RAP (Tons, Millions)	Accepted	0.2	*	0.2	*
	Used in HMA/WMA Mixtures	0.1	*	0.2	*
	Used as Aggregate	0.0	*	0.0	*
	Used in Cold-Mix Asphalt	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
	Total Tons of RAP Stockpiled at Year-End	0.15	*	0.19	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.0%	*		
	Average % for Other Agency Mixtures ¹	15.0%	*		
	Average % for Commercial & Residential Mixtures ¹	22.5%	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			18.5%	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	*		
	% of RAP Fractionated	50%	*		
	% of RAP Mixtures Using Softer Binders	0%	*		
	% of RAP Mixtures Using Recycling Agents	0%	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	*	0.0	*
	Processed Shingles Accepted	0.0	*	0.0	*
	Used in HMA/WMA Mixtures	0.0	*	0.0	*
	Used as Aggregate	0.0	*	0.0	*
	Used in Cold-Mix Asphalt	0.0	*	0.0	*
	Used in Other	0.0	*	0.0	*
	Landfilled	0.0	*	0.0	*
	Total Tons of RAS Stockpiled at Year-End	0.0	*	0.0	*
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	*		
	Average % for Other Agency Mixtures ¹	0.00%	*		
	Average % for Commercial & Residential Mixtures ¹	0.00%	*		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	*
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	*		
	% of RAS Mixtures Using Softer Binders	0%	*		
	% of RAS Mixtures Using Recycling Agents	0%	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			(Tons, Millions)	*
	Total Tons Produced With WMA Technology at HMA Temperatures			(Tons, Millions)	*
	DOT	0%	*	(Tons, Millions)	*
	Other Agency	0%	*	(Tons, Millions)	*
	Commercial & Residential	0%	*	(Tons, Millions)	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	0%	*		
	Additive Foaming, % of Market	0%	*		
	Plant Foaming, % of Market	0%	*		
	Organic Additive, % of Market	0%	*		
	% Companies Reporting Using WMA Technologies	0%	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

IDAHO

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	1.5	1.2	2.7	2.9
	DOT	0.8	0.6	1.5	1.5
	Other Agency	0.3	0.3	0.5	0.7
	Commercial & Residential	0.4	0.3	0.7	0.7
	No. of Companies Reporting	5	5		
RAP (Tons, Millions)	Accepted	0.4	0.3	0.8	0.7
	Used in HMA/WMA Mixtures	0.3	0.3	0.6	0.8
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.98	0.65	1.80	1.56
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	25.2%	25.0%		
	Average % for Other Agency Mixtures ¹	21.0%	24.6%		
	Average % for Commercial & Residential Mixtures ¹	25.8%	30.0%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			23.9%	26.1%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	1%		
	% of RAP Mixtures Using Softer Binders	62%	86%		
	% of RAP Mixtures Using Recycling Agents	20%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.5 (Tons, Millions)	0.5 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.1 (Tons, Millions)	1.2 (Tons, Millions)
	DOT	67%	51%	1.0 (Tons, Millions)	0.8 (Tons, Millions)
	Other Agency	77%	72%	0.4 (Tons, Millions)	0.5 (Tons, Millions)
	Commercial & Residential	31%	52%	0.2 (Tons, Millions)	0.4 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	75%	77%		
	Additive Foaming, % of Market	0%	8%		
	Plant Foaming, % of Market	25%	15%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	80%	80%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

ILLINOIS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	1.5	8.4	13.6	14.4
	DOT	0.7	4.0	6.6	6.9
	Other Agency	0.3	1.8	2.7	3.1
	Commercial & Residential	0.5	2.6	4.3	4.5
	No. of Companies Reporting	7	21		
RAP (Tons, Millions)	Accepted	0.4	2.8	3.5	4.8
	Used in HMA/WMA Mixtures	0.3	2.2	3.1	3.7
	Used as Aggregate	0.0	0.2	0.2	0.4
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.1	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.70	2.00	6.33	3.43
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.8%	22.3%		
	Average % for Other Agency Mixtures ¹	20.4%	22.9%		
	Average % for Commercial & Residential Mixtures ¹	24.5%	27.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			22.9%	25.7%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	25%	58%		
	% of RAP Mixtures Using Softer Binders	22%	45%		
	% of RAP Mixtures Using Recycling Agents	0%	1%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	4.1	18.8	37.3	32.2
	Processed Shingles Accepted	0.0	27.8	0.0	47.7
	Used in HMA/WMA Mixtures	5.5	34.1	50.0	58.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.2	14.1	1.8	24.2
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.58%	0.65%		
	Average % for Other Agency Mixtures ¹	0.21%	0.32%		
	Average % for Commercial & Residential Mixtures ¹	0.21%	0.47%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.37%	0.41%
RAS (Other Reported Data)	% Companies Reporting Using RAS	29%	48%		
	% of RAS Mixtures Using Softer Binders	0%	35%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.2 (Tons, Millions)	0.8 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.5 (Tons, Millions)	0.3 (Tons, Millions)
	DOT	17%	8%	1.1 (Tons, Millions)	0.5 (Tons, Millions)
	Other Agency	55%	16%	1.5 (Tons, Millions)	0.5 (Tons, Millions)
	Commercial & Residential	3%	2%	0.1 (Tons, Millions)	0.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	54%	62%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	46%	38%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	43%	43%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

INDIANA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	4.6	7.5	13.0	13.0
	DOT	1.7	2.9	4.9	5.0
	Other Agency	1.7	2.6	4.7	4.5
	Commercial & Residential	1.2	2.0	3.4	3.5
	No. of Companies Reporting	5	7		
RAP (Tons, Millions)	Accepted	0.9	1.4	2.5	2.4
	Used in HMA/WMA Mixtures	0.9	1.8	2.7	3.1
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.16	2.35	3.30	4.07
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	18.4%	23.5%		
	Average % for Other Agency Mixtures ¹	19.8%	23.3%		
	Average % for Commercial & Residential Mixtures ¹	22.4%	25.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			20.8%	23.9%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	57%	61%		
	% of RAP Mixtures Using Softer Binders	21%	4%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	6.4	0.4	18.3	0.7
	Processed Shingles Accepted	8.7	3.6	24.9	6.2
	Used in HMA/WMA Mixtures	18.0	4.1	51.4	7.1
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	16.5	15.9	47.1	27.6
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.60%	0.04%		
	Average % for Other Agency Mixtures ¹	0.30%	0.04%		
	Average % for Commercial & Residential Mixtures ¹	0.30%	0.06%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.40%	0.05%
RAS (Other Reported Data)	% Companies Reporting Using RAS	40%	43%		
	% of RAS Mixtures Using Softer Binders	10%	25%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.0 (Tons, Millions)	3.5 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			6.7 (Tons, Millions)	4.5 (Tons, Millions)
	DOT	71%	71%	3.4 (Tons, Millions)	3.6 (Tons, Millions)
	Other Agency	43%	50%	2.1 (Tons, Millions)	2.3 (Tons, Millions)
	Commercial & Residential	41%	62%	1.4 (Tons, Millions)	2.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	44%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	56%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	20%	43%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

IOWA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	0.9	1.9	3.7	5.2
	DOT	0.5	0.8	2.0	2.2
	Other Agency	0.2	0.8	0.9	2.2
	Commercial & Residential	0.2	0.3	0.7	0.8
	No. of Companies Reporting	3	4		
RAP (Tons, Millions)	Accepted	0.2	0.3	0.8	0.7
	Used in HMA/WMA Mixtures	0.2	0.3	0.7	0.9
	Used as Aggregate	0.0	0.0	0.0	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.34	0.53	1.38	1.45
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	17.3%	15.5%		
	Average % for Other Agency Mixtures ¹	18.7%	16.3%		
	Average % for Commercial & Residential Mixtures ¹	19.7%	18.5%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			18.5%	16.5%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	5%		
	% of RAP Mixtures Using Softer Binders	5%	25%		
	% of RAP Mixtures Using Recycling Agents	3%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.3	0.0	1.2	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	6.2	0.0	25.1	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.05%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.03%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	33%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.0 (Tons, Millions)	0.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.0 (Tons, Millions)	1.0 (Tons, Millions)
	DOT	0%	18%	0.0 (Tons, Millions)	0.4 (Tons, Millions)
	Other Agency	2%	20%	0.0 (Tons, Millions)	0.4 (Tons, Millions)
	Commercial & Residential	2%	21%	0.0 (Tons, Millions)	0.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	0%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	100%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	33%	25%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

KANSAS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	2.4	2.8	3.5
	DOT	*	1.4	*	2.0
	Other Agency	*	0.4	*	0.6
	Commercial & Residential	*	0.6	*	0.9
	No. of Companies Reporting	*	3		
RAP (Tons, Millions)	Accepted	*	0.7	*	1.0
	Used in HMA/WMA Mixtures	*	0.6	*	0.9
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	0.79	*	1.15
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	22.7%		
	Average % for Other Agency Mixtures ¹	*	25.0%		
	Average % for Commercial & Residential Mixtures ¹	*	27.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	25.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	35%		
	% of RAP Mixtures Using Softer Binders	*	75%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	3.0	*	4.4
	Processed Shingles Accepted	*	4.0	*	5.8
	Used in HMA/WMA Mixtures	*	4.5	*	6.6
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	5.5	*	8.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.33%		
	Average % for Other Agency Mixtures ¹	*	0.17%		
	Average % for Commercial & Residential Mixtures ¹	*	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.19%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	67%		
	% of RAS Mixtures Using Softer Binders	*	68%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.8 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	0.7 (Tons, Millions)
	DOT	*	47%	*	1.0 (Tons, Millions)
	Other Agency	*	51%	*	0.3 (Tons, Millions)
	Commercial & Residential	*	28%	*	0.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	54%		
	Additive Foaming, % of Market	*	0%		
	Plant Foaming, % of Market	*	46%		
	Organic Additive, % of Market	*	0%		
	% Companies Reporting Using WMA Technologies	*	67%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

KENTUCKY

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.5	1.7	6.0	4.0
	DOT	1.5	0.7	3.6	1.6
	Other Agency	0.6	0.5	1.5	1.2
	Commercial & Residential	0.4	0.5	0.9	1.2
	No. of Companies Reporting	5	5		
RAP (Tons, Millions)	Accepted	0.4	0.4	0.9	0.8
	Used in HMA/WMA Mixtures	0.4	0.3	0.9	0.7
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.33	0.58	0.80	1.36
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	14.7%	16.5%		
	Average % for Other Agency Mixtures ¹	17.2%	16.0%		
	Average % for Commercial & Residential Mixtures ¹	18.6%	20.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			15.6%	17.6%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	48%	50%		
	% of RAP Mixtures Using Softer Binders	17%	5%		
	% of RAP Mixtures Using Recycling Agents	20%	4%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	7.0	3.0	16.9	7.1
	Processed Shingles Accepted	12.0	6.0	29.0	14.1
	Used in HMA/WMA Mixtures	12.0	6.0	29.0	14.1
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	40.0	10.5	96.5	24.7
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.61%	0.35%		
	Average % for Other Agency Mixtures ¹	0.60%	0.35%		
	Average % for Commercial & Residential Mixtures ¹	0.32%	0.35%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.48%	0.35%
RAS (Other Reported Data)	% Companies Reporting Using RAS	20%	20%		
	% of RAS Mixtures Using Softer Binders	10%	50%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			2.5 (Tons, Millions)	2.3 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.8 (Tons, Millions)	1.2 (Tons, Millions)
	DOT	76%	100%	2.8 (Tons, Millions)	1.6 (Tons, Millions)
	Other Agency	64%	98%	1.0 (Tons, Millions)	1.2 (Tons, Millions)
	Commercial & Residential	64%	63%	0.5 (Tons, Millions)	0.7 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	61%	58%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	39%	42%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	60%	80%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

LOUISIANA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	1.2	1.1	6.8	7.5
	DOT	0.5	0.7	3.0	5.0
	Other Agency	0.4	0.1	2.3	0.5
	Commercial & Residential	0.3	0.3	1.5	2.0
	No. of Companies Reporting	4	3		
RAP (Tons, Millions)	Accepted	0.3	0.2	1.5	1.4
	Used in HMA/WMA Mixtures	0.3	0.2	1.5	1.3
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.19	0.05	1.08	0.35
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	22.3%	18.2%		
	Average % for Other Agency Mixtures ¹	17.8%	12.3%		
	Average % for Commercial & Residential Mixtures ¹	25.2%	21.0%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			22.2%	17.3%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	92%	25%		
	% of RAP Mixtures Using Softer Binders	10%	8%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			5.7 (Tons, Millions)	5.7 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.9 (Tons, Millions)	0.4 (Tons, Millions)
	DOT	100%	79%	3.0 (Tons, Millions)	4.0 (Tons, Millions)
	Other Agency	100%	100%	2.3 (Tons, Millions)	0.5 (Tons, Millions)
	Commercial & Residential	91%	82%	1.3 (Tons, Millions)	1.6 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	0%	0%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	100%	100%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MAINE

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	2.7	1.1	2.7
	DOT	*	0.7	*	0.7
	Other Agency	*	0.1	*	0.1
	Commercial & Residential	*	0.2	*	0.2
	No. of Companies Reporting	*	3		
RAP (Tons, Millions)	Accepted	*	0.4	*	0.4
	Used in HMA/WMA Mixtures	*	0.5	*	0.5
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	0.37	*	0.37
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	17.0%		
	Average % for Other Agency Mixtures ¹	*	17.0%		
	Average % for Commercial & Residential Mixtures ¹	*	17.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	17.2%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	17%		
	% of RAP Mixtures Using Softer Binders	*	0%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	0.0	*	0.0
	Processed Shingles Accepted	*	4.2	*	4.2
	Used in HMA/WMA Mixtures	*	4.2	*	4.2
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	0.1	*	0.1
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.22%		
	Average % for Other Agency Mixtures ¹	*	0.00%		
	Average % for Commercial & Residential Mixtures ¹	*	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.16%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	67%		
	% of RAS Mixtures Using Softer Binders	*	0%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.3 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	0.4 (Tons, Millions)
	DOT	*	86%	*	0.6 (Tons, Millions)
	Other Agency	*	56%	*	0.1 (Tons, Millions)
	Commercial & Residential	*	0%	*	0.0 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	100%		
	Additive Foaming, % of Market	*	0%		
	Plant Foaming, % of Market	*	0%		
	Organic Additive, % of Market	*	0%		
	% Companies Reporting Using WMA Technologies	*	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MARYLAND

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	1.7	4.6	7.0	6.3
	DOT	0.3	1.2	1.1	1.6
	Other Agency	0.6	1.6	2.6	2.2
	Commercial & Residential	0.8	1.8	3.3	2.5
	No. of Companies Reporting	6	8		
RAP (Tons, Millions)	Accepted	0.4	1.7	1.7	2.3
	Used in HMA/WMA Mixtures	0.5	1.3	2.1	1.8
	Used as Aggregate	0.0	0.3	0.0	0.5
	Used in Cold-Mix Asphalt	0.0	0.0	0.2	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.16	2.65	0.68	3.63
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	24.6%	25.6%		
	Average % for Other Agency Mixtures ¹	24.5%	25.3%		
	Average % for Commercial & Residential Mixtures ¹	32.3%	31.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			29.7%	28.3%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	5%		
	% of RAP Mixtures Using Softer Binders	33%	20%		
	% of RAP Mixtures Using Recycling Agents	0%	6%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	7.0	10.0	29.6	13.7
	Used in HMA/WMA Mixtures	0.2	3.1	0.8	4.2
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	7.0	13.0	29.6	17.8
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.15%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.02%	0.08%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.01%	0.07%
RAS (Other Reported Data)	% Companies Reporting Using RAS	17%	25%		
	% of RAS Mixtures Using Softer Binders	18%	100%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			2.4 (Tons, Millions)	1.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.2 (Tons, Millions)	2.3 (Tons, Millions)
	DOT	48%	36%	0.5 (Tons, Millions)	0.6 (Tons, Millions)
	Other Agency	30%	69%	0.8 (Tons, Millions)	1.5 (Tons, Millions)
	Commercial & Residential	39%	73%	1.3 (Tons, Millions)	1.8 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	14%	31%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	86%	69%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	33%	75%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MASSACHUSETTS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.1	2.9	6.5	6.5
	DOT	0.4	0.9	1.3	2.0
	Other Agency	0.7	1.1	2.2	2.5
	Commercial & Residential	1.0	0.9	3.0	2.0
	No. of Companies Reporting	3	4		
RAP (Tons, Millions)	Accepted	0.4	0.5	1.3	1.1
	Used in HMA/WMA Mixtures	0.3	0.4	1.1	1.0
	Used as Aggregate	0.0	0.0	0.0	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.54	0.69	1.65	1.56
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	13.6%	14.8%		
	Average % for Other Agency Mixtures ¹	15.6%	14.3%		
	Average % for Commercial & Residential Mixtures ¹	22.3%	18.5%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			16.4%	15.1%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	7%		
	% of RAP Mixtures Using Softer Binders	35%	4%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	8.9	0.0	27.4	0.0
	Processed Shingles Accepted	4.9	11.2	15.1	25.1
	Used in HMA/WMA Mixtures	2.4	1.1	7.4	2.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	26.3	0.0	58.9
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	22.2	60.9	68.3	136.5
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.18%	0.06%		
	Average % for Commercial & Residential Mixtures ¹	0.18%	0.06%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.11%	0.04%
RAS (Other Reported Data)	% Companies Reporting Using RAS	66%	50%		
	% of RAS Mixtures Using Softer Binders	18%	25%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.9 (Tons, Millions)	3.3 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.7 (Tons, Millions)	0.5 (Tons, Millions)
	DOT	99%	97%	1.3 (Tons, Millions)	2.0 (Tons, Millions)
	Other Agency	36%	62%	0.8 (Tons, Millions)	1.5 (Tons, Millions)
	Commercial & Residential	18%	15%	0.5 (Tons, Millions)	0.3 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	65%	86%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	0%		
	Organic Additive, % of Market	35%	23%		
	% Companies Reporting Using WMA Technologies	66%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MICHIGAN

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	7.9	10.0	15.1	14.8
	DOT	2.5	4.1	4.8	6.1
	Other Agency	2.0	2.3	3.9	3.4
	Commercial & Residential	3.4	3.6	6.4	5.3
	No. of Companies Reporting	5	9		
RAP (Tons, Millions)	Accepted	2.4	2.4	4.6	3.5
	Used in HMA/WMA Mixtures	2.3	2.6	4.3	3.9
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	14.75	14.98	28.12	22.17
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.6%	20.6%		
	Average % for Other Agency Mixtures ¹	22.5%	23.3%		
	Average % for Commercial & Residential Mixtures ¹	32.6%	28.7%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			28.5%	26.4%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	89%		
	% of RAP Fractionated	21%	22%		
	% of RAP Mixtures Using Softer Binders	36%	35%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	1.5	1.0	2.9	1.5
	Processed Shingles Accepted	1.0	5.0	1.9	7.4
	Used in HMA/WMA Mixtures	0.5	5.0	1.0	7.4
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	1.0	1.0	1.9	1.5
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.03%	0.13%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.01%	0.05%
RAS (Other Reported Data)	% Companies Reporting Using RAS	20%	11%		
	% of RAS Mixtures Using Softer Binders	100%	50%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.0 (Tons, Millions)	0.4 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			2.4 (Tons, Millions)	2.6 (Tons, Millions)
	DOT	25%	25%	1.2 (Tons, Millions)	1.5 (Tons, Millions)
	Other Agency	16%	19%	0.6 (Tons, Millions)	0.6 (Tons, Millions)
	Commercial & Residential	9%	15%	0.6 (Tons, Millions)	0.9 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	100%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	0%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	40%	33%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MINNESOTA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	5.6	7.3	11.0	12.2
	DOT	1.9	2.4	3.8	4.0
	Other Agency	2.2	2.1	4.2	3.5
	Commercial & Residential	1.5	2.8	3.0	4.7
	No. of Companies Reporting	3	5		
RAP (Tons, Millions)	Accepted	2.1	2.3	4.1	3.9
	Used in HMA/WMA Mixtures	1.3	1.8	2.6	3.0
	Used as Aggregate	0.4	0.7	0.8	1.2
	Used in Cold-Mix Asphalt	0.0	0.1	0.0	0.2
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.50	3.96	2.93	6.62
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	21.0%	18.8%		
	Average % for Other Agency Mixtures ¹	22.8%	24.8%		
	Average % for Commercial & Residential Mixtures ¹	24.7%	27.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			23.6%	24.4%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	15%	12%		
	% of RAP Mixtures Using Softer Binders	16%	19%		
	% of RAP Mixtures Using Recycling Agents	0%	11%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	9.7	10.0	19.0	16.7
	Used in HMA/WMA Mixtures	10.7	10.0	20.9	16.7
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	12.6	1.0	24.6	1.7
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.06%	0.14%		
	Average % for Other Agency Mixtures ¹	0.24%	0.14%		
	Average % for Commercial & Residential Mixtures ¹	0.24%	0.14%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.19%	0.14%
RAS (Other Reported Data)	% Companies Reporting Using RAS	66%	20%		
	% of RAS Mixtures Using Softer Binders	25%	10%		
	% of RAS Mixtures Using Recycling Agents	0%	2%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			4.3 (Tons, Millions)	6.6 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.1 (Tons, Millions)	1.3 (Tons, Millions)
	DOT	25%	44%	1.0 (Tons, Millions)	1.9 (Tons, Millions)
	Other Agency	74%	69%	3.1 (Tons, Millions)	2.4 (Tons, Millions)
	Commercial & Residential	44%	78%	1.3 (Tons, Millions)	3.5 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	1%	3%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	99%	94%		
	Organic Additive, % of Market	0%	3%		
	% Companies Reporting Using WMA Technologies	33%	60%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MISSISSIPPI

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.2	4.2	2.9	4.3
	DOT	1.6	2.4	2.1	2.5
	Other Agency	0.1	1.0	0.2	1.0
	Commercial & Residential	0.5	0.8	0.6	0.8
	No. of Companies Reporting	4	7		
RAP (Tons, Millions)	Accepted	0.3	0.7	0.4	0.7
	Used in HMA/WMA Mixtures	0.5	0.9	0.7	0.9
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.1	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.43	0.61	0.57	0.63
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.0%	19.4%		
	Average % for Other Agency Mixtures ¹	20.3%	19.4%		
	Average % for Commercial & Residential Mixtures ¹	26.0%	22.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			22.7%	20.2%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	17%		
	% of RAP Mixtures Using Softer Binders	0%	2%		
	% of RAP Mixtures Using Recycling Agents	2%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.0 (Tons, Millions)	2.5 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.1 (Tons, Millions)	1.2 (Tons, Millions)
	DOT	72%	87%	1.5 (Tons, Millions)	2.2 (Tons, Millions)
	Other Agency	100%	81%	0.2 (Tons, Millions)	0.8 (Tons, Millions)
	Commercial & Residential	62%	88%	0.4 (Tons, Millions)	0.7 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	0%	7%		
	Additive Foaming, % of Market	100%	0%		
	Plant Foaming, % of Market	0%	93%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	75%	86%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MISSOURI

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.7	2.4	6.8	10.2
	DOT	0.8	1.0	2.0	4.3
	Other Agency	0.8	0.5	2.0	2.1
	Commercial & Residential	1.1	0.9	2.7	3.8
	No. of Companies Reporting	8	5		
RAP (Tons, Millions)	Accepted	0.6	0.5	1.6	2.3
	Used in HMA/WMA Mixtures	0.7	0.5	1.8	2.3
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.66	0.42	4.13	1.76
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.9%	20.0%		
	Average % for Other Agency Mixtures ¹	21.5%	24.6%		
	Average % for Commercial & Residential Mixtures ¹	30.0%	25.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			26.7%	22.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	88%	100%		
	% of RAP Fractionated	22%	16%		
	% of RAP Mixtures Using Softer Binders	27%	56%		
	% of RAP Mixtures Using Recycling Agents	4%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	10.0	0.0	24.9	0.0
	Processed Shingles Accepted	2.8	0.5	7.0	2.1
	Used in HMA/WMA Mixtures	11.4	1.7	28.4	7.2
	Used as Aggregate	4.0	0.0	10.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	42.5	4.0	105.9	17.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.50%	0.05%		
	Average % for Other Agency Mixtures ¹	0.38%	0.05%		
	Average % for Commercial & Residential Mixtures ¹	0.38%	0.10%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.42%	0.07%
RAS (Other Reported Data)	% Companies Reporting Using RAS	63%	40%		
	% of RAS Mixtures Using Softer Binders	45%	100%		
	% of RAS Mixtures Using Recycling Agents	5%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.1 (Tons, Millions)	1.9 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.4 (Tons, Millions)	2.1 (Tons, Millions)
	DOT	13%	52%	0.3 (Tons, Millions)	2.3 (Tons, Millions)
	Other Agency	7%	30%	0.1 (Tons, Millions)	0.6 (Tons, Millions)
	Commercial & Residential	3%	30%	0.1 (Tons, Millions)	1.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	15%	67%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	85%	33%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	38%	40%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

MONTANA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	4.2	4.1
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEBRASKA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	0.4	2.8	3.0
	DOT	*	0.1	*	0.4
	Other Agency	*	0.2	*	1.1
	Commercial & Residential	*	0.2	*	1.5
	No. of Companies Reporting	*	3		
RAP (Tons, Millions)	Accepted	*	0.1	*	0.8
	Used in HMA/WMA Mixtures	*	0.1	*	0.6
	Used as Aggregate	*	0.0	*	0.2
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	0.12	*	0.90
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	22.0%		
	Average % for Other Agency Mixtures ¹	*	20.0%		
	Average % for Commercial & Residential Mixtures ¹	*	20.0%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	20.3%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	0%		
	% of RAP Mixtures Using Softer Binders	*	0%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	0.0	*	0.0
	Processed Shingles Accepted	*	0.0	*	0.0
	Used in HMA/WMA Mixtures	*	0.0	*	0.0
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	0.0	*	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.00%		
	Average % for Other Agency Mixtures ¹	*	0.00%		
	Average % for Commercial & Residential Mixtures ¹	*	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	0%		
	% of RAS Mixtures Using Softer Binders	*	0%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.2 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	1.3 (Tons, Millions)
	DOT	*	87%	*	0.3 (Tons, Millions)
	Other Agency	*	99%	*	1.2 (Tons, Millions)
	Commercial & Residential	*	0%	*	0.0 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	0%		
	Additive Foaming, % of Market	*	0%		
	Plant Foaming, % of Market	*	100%		
	Organic Additive, % of Market	*	0%		
	% Companies Reporting Using WMA Technologies	*	67%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEVADA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	1.2	3.4	3.5
	DOT	*	0.2	*	0.6
	Other Agency	*	0.7	*	2.0
	Commercial & Residential	*	0.3	*	0.9
	No. of Companies Reporting	*	4		
RAP (Tons, Millions)	Accepted	*	0.2	*	0.6
	Used in HMA/WMA Mixtures	*	0.2	*	0.6
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	0.12	*	0.34
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	13.5%		
	Average % for Other Agency Mixtures ¹	*	16.3%		
	Average % for Commercial & Residential Mixtures ¹	*	25.0%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	17.2%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	0%		
	% of RAP Mixtures Using Softer Binders	*	13%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	0.0	*	0.0
	Processed Shingles Accepted	*	0.0	*	0.0
	Used in HMA/WMA Mixtures	*	0.0	*	0.0
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	0.0	*	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.00%		
	Average % for Other Agency Mixtures ¹	*	0.00%		
	Average % for Commercial & Residential Mixtures ¹	*	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	0%		
	% of RAS Mixtures Using Softer Binders	*	0%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	0.1 (Tons, Millions)
	DOT	*	0%	*	0.0 (Tons, Millions)
	Other Agency	*	1%	*	0.0 (Tons, Millions)
	Commercial & Residential	*	10%	*	0.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	100%		
	Additive Foaming, % of Market	*	0%		
	Plant Foaming, % of Market	*	0%		
	Organic Additive, % of Market	*	0%		
	% Companies Reporting Using WMA Technologies	*	25%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEW HAMPSHIRE

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	1.1	1.3	1.6
	DOT	*	0.4	*	0.6
	Other Agency	*	0.3	*	0.4
	Commercial & Residential	*	0.4	*	0.6
	No. of Companies Reporting	*	3		
RAP (Tons, Millions)	Accepted	*	0.3	*	0.4
	Used in HMA/WMA Mixtures	*	0.2	*	0.3
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAP Stockpiled at Year-End	*	0.32	*	0.46
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	15.0%		
	Average % for Other Agency Mixtures ¹	*	18.3%		
	Average % for Commercial & Residential Mixtures ¹	*	19.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	16.9%
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	100%		
	% of RAP Fractionated	*	0%		
	% of RAP Mixtures Using Softer Binders	*	0%		
	% of RAP Mixtures Using Recycling Agents	*	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	0.0	*	0.0
	Processed Shingles Accepted	*	2.7	*	3.9
	Used in HMA/WMA Mixtures	*	2.7	*	3.9
	Used as Aggregate	*	0.0	*	0.0
	Used in Cold-Mix Asphalt	*	0.0	*	0.0
	Used in Other	*	0.0	*	0.0
	Landfilled	*	0.0	*	0.0
	Total Tons of RAS Stockpiled at Year-End	*	0.0	*	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	0.00%		
	Average % for Other Agency Mixtures ¹	*	0.33%		
	Average % for Commercial & Residential Mixtures ¹	*	0.33%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	0.25%
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	33%		
	% of RAS Mixtures Using Softer Binders	*	0%		
	% of RAS Mixtures Using Recycling Agents	*	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	0.1 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			*	1.4 (Tons, Millions)
	DOT	*	100%	*	0.6 (Tons, Millions)
	Other Agency	*	100%	*	0.4 (Tons, Millions)
	Commercial & Residential	*	85%	*	0.5 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	0%		
	Additive Foaming, % of Market	*	17%		
	Plant Foaming, % of Market	*	72%		
	Organic Additive, % of Market	*	11%		
	% Companies Reporting Using WMA Technologies	*	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEW JERSEY

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	6.8	4.8	11.8	9.8
	DOT	1.5	0.7	2.6	1.4
	Other Agency	3.4	2.3	5.9	4.7
	Commercial & Residential	1.9	1.8	3.3	3.7
	No. of Companies Reporting	4	4		
RAP (Tons, Millions)	Accepted	2.5	1.1	4.3	2.3
	Used in HMA/WMA Mixtures	1.4	0.8	2.4	1.6
	Used as Aggregate	0.5	0.0	0.9	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.1	0.0	0.1
	Total Tons of RAP Stockpiled at Year-End	6.32	2.30	11.04	4.69
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	16.3%	14.0%		
	Average % for Other Agency Mixtures ¹	17.5%	16.0%		
	Average % for Commercial & Residential Mixtures ¹	24.0%	22.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			20.3%	16.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	10%	25%		
	% of RAP Mixtures Using Softer Binders	8%	3%		
	% of RAP Mixtures Using Recycling Agents	8%	24%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.2	0.0	0.3	0.0
	Used in HMA/WMA Mixtures	1.5	0.0	2.6	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.02%	0.00%		
	Average % for Other Agency Mixtures ¹	0.02%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.02%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.02%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	25%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.0 (Tons, Millions)	0.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.9 (Tons, Millions)	1.4 (Tons, Millions)
	DOT	2%	31%	0.1 (Tons, Millions)	0.4 (Tons, Millions)
	Other Agency	5%	5%	0.3 (Tons, Millions)	0.3 (Tons, Millions)
	Commercial & Residential	18%	20%	0.6 (Tons, Millions)	0.7 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	0%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	100%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	50%	25%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEW MEXICO

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	3.7	3.8
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NEW YORK

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	6.7	5.6	17.5	17.5
	DOT	1.6	1.5	4.2	4.7
	Other Agency	2.6	2.4	6.7	7.5
	Commercial & Residential	2.5	1.7	6.6	5.3
	No. of Companies Reporting	14	13		
RAP (Tons, Millions)	Accepted	1.1	0.9	2.8	2.8
	Used in HMA/WMA Mixtures	1.1	1.0	3.0	3.1
	Used as Aggregate	0.0	0.0	0.1	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.20	0.89	3.14	2.79
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	17.0%	17.6%		
	Average % for Other Agency Mixtures ¹	17.1%	16.9%		
	Average % for Commercial & Residential Mixtures ¹	17.0%	18.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			17.0%	17.6%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	7%	17%		
	% of RAP Mixtures Using Softer Binders	3%	2%		
	% of RAP Mixtures Using Recycling Agents	7%	8%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			2.5 (Tons, Millions)	4.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			2.4 (Tons, Millions)	5.0 (Tons, Millions)
	DOT	44%	67%	1.9 (Tons, Millions)	3.1 (Tons, Millions)
	Other Agency	37%	60%	2.5 (Tons, Millions)	4.5 (Tons, Millions)
	Commercial & Residential	9%	26%	0.6 (Tons, Millions)	1.4 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	40%	41%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	60%	59%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	64%	85%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NORTH CAROLINA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	7.7	9.9	15.0	12.0
	DOT	5.9	6.2	11.5	7.5
	Other Agency	0.9	1.0	1.7	1.2
	Commercial & Residential	0.9	2.7	1.8	3.3
	No. of Companies Reporting	6	9		
RAP (Tons, Millions)	Accepted	1.9	3.7	3.6	4.4
	Used in HMA/WMA Mixtures	1.8	3.0	3.6	3.7
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.63	5.60	3.16	6.78
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	24.8%	30.0%		
	Average % for Other Agency Mixtures ¹	20.7%	25.2%		
	Average % for Commercial & Residential Mixtures ¹	23.0%	32.7%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			23.8%	30.6%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	7%	42%		
	% of RAP Mixtures Using Softer Binders	44%	36%		
	% of RAP Mixtures Using Recycling Agents	0%	10%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	33.0	35.0	64.1	42.4
	Processed Shingles Accepted	19.5	27.0	37.9	32.7
	Used in HMA/WMA Mixtures	118.3	74.3	229.9	90.1
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	115.5	179.0	224.4	217.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	2.50%	1.10%		
	Average % for Other Agency Mixtures ¹	1.17%	0.60%		
	Average % for Commercial & Residential Mixtures ¹	1.17%	0.90%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			1.53%	0.75%
RAS (Other Reported Data)	% Companies Reporting Using RAS	67%	44%		
	% of RAS Mixtures Using Softer Binders	75%	100%		
	% of RAS Mixtures Using Recycling Agents	0%	25%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.1 (Tons, Millions)	2.3 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.3 (Tons, Millions)	2.4 (Tons, Millions)
	DOT	3%	51%	0.3 (Tons, Millions)	3.8 (Tons, Millions)
	Other Agency	4%	22%	0.1 (Tons, Millions)	0.3 (Tons, Millions)
	Commercial & Residential	2%	19%	0.0 (Tons, Millions)	0.6 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	74%	100%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	26%	0%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	33%	56%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NORTH DAKOTA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	2.3	2.5
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

NORTHERN MARIANA ISLANDS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	NCR	0.03	0.02
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
	No. of Companies Reporting	NCR	NCR		
RAP (Tons, Millions)	Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
	Total Tons of RAP Stockpiled at Year-End	NCR	NCR	NCR	NCR
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	NCR
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	NCR		
	% of RAP Fractionated	NCR	NCR		
	% of RAP Mixtures Using Softer Binders	NCR	NCR		
	% of RAP Mixtures Using Recycling Agents	NCR	NCR		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	NCR	NCR	NCR
	Processed Shingles Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	NCR	NCR	NCR
	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	NCR
	% Companies Reporting Using RAS	NCR	NCR		
	% of RAS Mixtures Using Softer Binders	NCR	NCR		
	% of RAS Mixtures Using Recycling Agents	NCR	NCR		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	NCR
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	NCR
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	NCR		
	Additive Foaming, % of Market	NCR	NCR		
	Plant Foaming, % of Market	NCR	NCR		
	Organic Additive, % of Market	NCR	NCR		
	% Companies Reporting Using WMA Technologies	NCR	NCR		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

OHIO

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	11.2	11.8	19.4	18.0
	DOT	3.8	4.3	6.6	6.6
	Other Agency	3.9	3.9	6.8	5.9
	Commercial & Residential	3.5	3.6	6.0	5.5
	No. of Companies Reporting	9	12		
RAP (Tons, Millions)	Accepted	4.6	3.3	7.9	5.0
	Used in HMA/WMA Mixtures	3.6	3.4	6.3	5.1
	Used as Aggregate	0.0	0.1	0.1	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	6.37	3.81	11.07	5.81
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	29.4%	25.0%		
	Average % for Other Agency Mixtures ¹	28.9%	29.9%		
	Average % for Commercial & Residential Mixtures ¹	34.8%	32.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			32.2%	28.4%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	13%	19%		
	% of RAP Mixtures Using Softer Binders	31%	46%		
	% of RAP Mixtures Using Recycling Agents	7%	9%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	10.4	6.1	18.1	9.3
	Processed Shingles Accepted	0.0	0.1	0.0	0.2
	Used in HMA/WMA Mixtures	7.0	3.7	12.2	5.6
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	24.4	29.0	42.4	44.2
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.02%	0.02%		
	Average % for Other Agency Mixtures ¹	0.02%	0.05%		
	Average % for Commercial & Residential Mixtures ¹	0.08%	0.06%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.06%	0.03%
RAS (Other Reported Data)	% Companies Reporting Using RAS	33%	25%		
	% of RAS Mixtures Using Softer Binders	33%	100%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			8.6 (Tons, Millions)	10.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.8 (Tons, Millions)	1.1 (Tons, Millions)
	DOT	70%	68%	4.6 (Tons, Millions)	4.5 (Tons, Millions)
	Other Agency	47%	57%	3.2 (Tons, Millions)	3.4 (Tons, Millions)
	Commercial & Residential	43%	59%	2.6 (Tons, Millions)	3.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	1%	7%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	99%	93%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	78%	58%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

OKLAHOMA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.0	3.8	5.5	5.1
	DOT	0.8	1.4	2.2	1.9
	Other Agency	0.4	1.5	1.1	2.0
	Commercial & Residential	0.8	0.9	2.3	1.2
	No. of Companies Reporting	7	9		
RAP (Tons, Millions)	Accepted	0.5	1.1	1.3	1.4
	Used in HMA/WMA Mixtures	0.4	0.7	1.1	1.0
	Used as Aggregate	0.0	0.3	0.1	0.4
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.39	1.20	1.10	1.61
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	19.6%	15.8%		
	Average % for Other Agency Mixtures ¹	20.4%	19.1%		
	Average % for Commercial & Residential Mixtures ¹	18.5%	20.4%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			19.4%	18.7%
RAP (Other Reported Data)	% Companies Reporting Using RAP	86%	100%		
	% of RAP Fractionated	32%	70%		
	% of RAP Mixtures Using Softer Binders	10%	21%		
	% of RAP Mixtures Using Recycling Agents	0%	15%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	2.0	40.0	5.6	53.7
	Processed Shingles Accepted	0.0	10.0	0.0	13.4
	Used in HMA/WMA Mixtures	1.0	26.0	2.8	34.9
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	5.0	75.2	14.1	100.9
	Average % for DOT Mixtures ¹	0.05%	0.00%		
	Average % for Other Agency Mixtures ¹	0.05%	0.78%		
	Average % for Commercial & Residential Mixtures ¹	0.05%	0.89%		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.05%	0.68%
	% Companies Reporting Using RAS	14%	33%		
	% of RAS Mixtures Using Softer Binders	100%	75%		
	% of RAS Mixtures Using Recycling Agents	50%	28%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.9 (Tons, Millions)	1.2 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.7 (Tons, Millions)	1.5 (Tons, Millions)
	DOT	60%	53%	1.3 (Tons, Millions)	1.0 (Tons, Millions)
	Other Agency	42%	56%	0.5 (Tons, Millions)	1.2 (Tons, Millions)
	Commercial & Residential	39%	42%	0.9 (Tons, Millions)	0.5 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	23%	12%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	77%	88%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	43%	56%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

OREGON

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	1.9	2.1	5.3	5.2
	DOT	0.4	0.5	1.0	1.2
	Other Agency	0.8	0.8	2.3	2.0
	Commercial & Residential	0.7	0.8	2.0	2.0
	No. of Companies Reporting	3	5		
RAP (Tons, Millions)	Accepted	0.6	0.5	1.6	1.3
	Used in HMA/WMA Mixtures	0.5	0.6	1.4	1.4
	Used as Aggregate	0.0	0.0	0.1	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.82	0.94	2.25	2.34
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	24.6%	26.0%		
	Average % for Other Agency Mixtures ¹	25.7%	26.4%		
	Average % for Commercial & Residential Mixtures ¹	28.7%	28.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			26.2%	26.5%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	1%	8%		
	% of RAP Mixtures Using Softer Binders	7%	6%		
	% of RAP Mixtures Using Recycling Agents	25%	10%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	13.0	0.0	36.0	0.0
	Used in HMA/WMA Mixtures	12.2	1.6	33.8	4.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	1.0	27.5	2.8	68.1
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.76%	0.02%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.41%	0.10%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.64%	0.08%
RAS (Other Reported Data)	% Companies Reporting Using RAS	33%	20%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	75%	99%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.5 (Tons, Millions)	0.7 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			2.8 (Tons, Millions)	1.2 (Tons, Millions)
	DOT	84%	44%	0.8 (Tons, Millions)	0.5 (Tons, Millions)
	Other Agency	52%	47%	1.2 (Tons, Millions)	0.9 (Tons, Millions)
	Commercial & Residential	60%	27%	1.2 (Tons, Millions)	0.5 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	7%	46%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	93%	54%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

PENNSYLVANIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.6	5.9	20.5	17.8
	DOT	0.9	2.8	6.8	8.4
	Other Agency	0.8	0.9	6.2	2.7
	Commercial & Residential	0.9	2.2	7.5	6.6
	No. of Companies Reporting	5	10		
RAP (Tons, Millions)	Accepted	0.4	1.0	3.3	3.1
	Used in HMA/WMA Mixtures	0.3	1.2	2.7	3.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.40	0.85	3.18	2.57
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	12.6%	16.5%		
	Average % for Other Agency Mixtures ¹	12.6%	15.0%		
	Average % for Commercial & Residential Mixtures ¹	15.0%	22.6%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			13.1%	19.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	80%	90%		
	% of RAP Fractionated	0%	23%		
	% of RAP Mixtures Using Softer Binders	0%	12%		
	% of RAP Mixtures Using Recycling Agents	0%	9%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	30.0	29.0	238.3	87.5
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	25.0	8.3	198.6	25.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	5.0	62.1	39.7	187.4
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.97%	0.14%		
	Average % for Other Agency Mixtures ¹	0.97%	0.14%		
	Average % for Commercial & Residential Mixtures ¹	0.97%	0.14%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.97%	0.14%
RAS (Other Reported Data)	% Companies Reporting Using RAS	20%	30%		
	% of RAS Mixtures Using Softer Binders	0%	33%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			4.9 (Tons, Millions)	8.4 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			7.6 (Tons, Millions)	5.4 (Tons, Millions)
	DOT	98%	76%	6.6 (Tons, Millions)	6.4 (Tons, Millions)
	Other Agency	55%	81%	3.4 (Tons, Millions)	2.2 (Tons, Millions)
	Commercial & Residential	33%	79%	2.5 (Tons, Millions)	5.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	17%	57%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	83%	39%		
	Organic Additive, % of Market	0%	4%		
	% Companies Reporting Using WMA Technologies	100%	90%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

PUERTO RICO

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	NCR	1.4	1.4
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
	No. of Companies Reporting	NCR	NCR		
RAP (Tons, Millions)	Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
	Total Tons of RAP Stockpiled at Year-End	NCR	NCR	NCR	NCR
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	NCR
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	NCR		
	% of RAP Fractionated	NCR	NCR		
	% of RAP Mixtures Using Softer Binders	NCR	NCR		
	% of RAP Mixtures Using Recycling Agents	NCR	NCR		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	NCR	NCR	NCR
	Processed Shingles Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	NCR	NCR	NCR
	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	NCR
	% Companies Reporting Using RAS	NCR	NCR		
	% of RAS Mixtures Using Softer Binders	NCR	NCR		
	% of RAS Mixtures Using Recycling Agents	NCR	NCR		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	NCR
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	NCR
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	NCR		
	Additive Foaming, % of Market	NCR	NCR		
	Plant Foaming, % of Market	NCR	NCR		
	Organic Additive, % of Market	NCR	NCR		
	% Companies Reporting Using WMA Technologies	NCR	NCR		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

RHODE ISLAND

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	1.9	2.2
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
RAS (Other Reported Data)	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

SOUTH CAROLINA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	3.3	3.2	8.9	7.0
	DOT	2.4	2.1	6.3	4.6
	Other Agency	0.6	0.6	1.6	1.3
	Commercial & Residential	0.4	0.5	1.0	1.1
	No. of Companies Reporting	5	6		
RAP (Tons, Millions)	Accepted	0.5	0.9	1.4	2.0
	Used in HMA/WMA Mixtures	0.7	0.7	2.0	1.4
	Used as Aggregate	0.0	0.0	0.0	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.71	1.42	1.91	3.11
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	21.2%	19.6%		
	Average % for Other Agency Mixtures ¹	21.6%	20.0%		
	Average % for Commercial & Residential Mixtures ¹	24.6%	22.2%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			22.0%	20.5%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	46%	27%		
	% of RAP Mixtures Using Softer Binders	0%	28%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	3.0	7.5	8.0	16.4
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.8	3.0	2.1	6.6
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	7.0	15.0	18.7	32.8
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.03%	0.09%		
	Average % for Other Agency Mixtures ¹	0.03%	0.09%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.09%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.02%	0.09%
RAS (Other Reported Data)	% Companies Reporting Using RAS	20%	17%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	100%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			3.1 (Tons, Millions)	1.0 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.0 (Tons, Millions)	1.8 (Tons, Millions)
	DOT	33%	42%	2.1 (Tons, Millions)	1.9 (Tons, Millions)
	Other Agency	50%	48%	0.8 (Tons, Millions)	0.6 (Tons, Millions)
	Commercial & Residential	25%	30%	0.2 (Tons, Millions)	0.3 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	97%	100%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	3%	0%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	83%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

SOUTH DAKOTA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	*	2.6	2.9
	DOT	NCR	*	NCR	*
	Other Agency	NCR	*	NCR	*
	Commercial & Residential	NCR	*	NCR	*
	No. of Companies Reporting	NCR	*		
RAP (Tons, Millions)	Accepted	NCR	*	NCR	*
	Used in HMA/WMA Mixtures	NCR	*	NCR	*
	Used as Aggregate	NCR	*	NCR	*
	Used in Cold-Mix Asphalt	NCR	*	NCR	*
	Used in Other	NCR	*	NCR	*
	Landfilled	NCR	*	NCR	*
	Total Tons of RAP Stockpiled at Year-End	NCR	*	NCR	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	*		
	Average % for Other Agency Mixtures ¹	NCR	*		
	Average % for Commercial & Residential Mixtures ¹	NCR	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	*		
	% of RAP Fractionated	NCR	*		
	% of RAP Mixtures Using Softer Binders	NCR	*		
	% of RAP Mixtures Using Recycling Agents	NCR	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	*	NCR	*
	Processed Shingles Accepted	NCR	*	NCR	*
	Used in HMA/WMA Mixtures	NCR	*	NCR	*
	Used as Aggregate	NCR	*	NCR	*
	Used in Cold-Mix Asphalt	NCR	*	NCR	*
	Used in Other	NCR	*	NCR	*
	Landfilled	NCR	*	NCR	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	*	NCR	*
	Average % for DOT Mixtures ¹	NCR	*		
	Average % for Other Agency Mixtures ¹	NCR	*		
	Average % for Commercial & Residential Mixtures ¹	NCR	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	*
	% Companies Reporting Using RAS	NCR	*		
	% of RAS Mixtures Using Softer Binders	NCR	*		
	% of RAS Mixtures Using Recycling Agents	NCR	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	*
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	*
	DOT	NCR	*	NCR	*
	Other Agency	NCR	*	NCR	*
	Commercial & Residential	NCR	*	NCR	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	*		
	Additive Foaming, % of Market	NCR	*		
	Plant Foaming, % of Market	NCR	*		
	Organic Additive, % of Market	NCR	*		
	% Companies Reporting Using WMA Technologies	NCR	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

TENNESSEE

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	8.2	3.8	10.1	8.9
	DOT	3.2	2.1	4.0	4.9
	Other Agency	1.8	0.8	2.2	1.9
	Commercial & Residential	3.2	0.9	4.0	2.1
	No. of Companies Reporting	5	7		
RAP (Tons, Millions)	Accepted	2.0	0.8	2.4	1.8
	Used in HMA/WMA Mixtures	1.9	0.7	2.4	1.7
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.2	0.0	0.3	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	4.02	1.85	4.94	4.32
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	24.0%	17.1%		
	Average % for Other Agency Mixtures ¹	20.4%	19.6%		
	Average % for Commercial & Residential Mixtures ¹	24.2%	22.7%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			23.5%	19.0%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	15%	34%		
	% of RAP Mixtures Using Softer Binders	0%	22%		
	% of RAP Mixtures Using Recycling Agents	0%	12%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	15.4	0.0	18.9	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	21.3	0.0	26.1	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	8.5	0.0	10.4	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.31%	0.00%		
	Average % for Other Agency Mixtures ¹	0.16%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.17%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.26%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	40%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	50%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.3 (Tons, Millions)	1.4 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			3.7 (Tons, Millions)	0.9 (Tons, Millions)
	DOT	57%	34%	2.3 (Tons, Millions)	1.7 (Tons, Millions)
	Other Agency	8%	15%	0.2 (Tons, Millions)	0.3 (Tons, Millions)
	Commercial & Residential	40%	14%	1.6 (Tons, Millions)	0.3 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	93%	45%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	7%	55%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	60%	57%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

TEXAS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	5.9	5.2	40.0	35.0
	DOT	2.5	2.2	17.0	14.8
	Other Agency	2.1	1.2	14.3	8.1
	Commercial & Residential	1.3	1.8	8.7	12.1
	No. of Companies Reporting	4	4		
RAP (Tons, Millions)	Accepted	0.8	1.0	5.2	6.7
	Used in HMA/WMA Mixtures	0.9	1.0	6.4	6.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.1
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.77	0.99	5.27	6.69
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	13.0%	18.0%		
	Average % for Other Agency Mixtures ¹	16.8%	19.5%		
	Average % for Commercial & Residential Mixtures ¹	21.0%	21.3%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			16.0%	18.5%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	50%	45%		
	% of RAP Mixtures Using Softer Binders	14%	16%		
	% of RAP Mixtures Using Recycling Agents	20%	19%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	32.0	33.7	218.3	226.8
	Processed Shingles Accepted	4.0	0.0	27.3	0.0
	Used in HMA/WMA Mixtures	39.6	20.4	270.2	137.3
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	42.0	23.5	286.5	158.2
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.66%	0.45%		
	Average % for Other Agency Mixtures ¹	0.59%	0.36%		
	Average % for Commercial & Residential Mixtures ¹	0.72%	0.36%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.68%	0.39%
RAS (Other Reported Data)	% Companies Reporting Using RAS	75%	75%		
	% of RAS Mixtures Using Softer Binders	13%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			8.7 (Tons, Millions)	1.8 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			18.6 (Tons, Millions)	17.3 (Tons, Millions)
	DOT	77%	65%	13.1 (Tons, Millions)	9.6 (Tons, Millions)
	Other Agency	65%	67%	9.3 (Tons, Millions)	5.4 (Tons, Millions)
	Commercial & Residential	56%	34%	4.9 (Tons, Millions)	4.1 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	88%	76%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	12%	24%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

U.S. VIRGIN ISLANDS

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	NCR	NCR	0.09	0.1
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
	No. of Companies Reporting	NCR	NCR		
RAP (Tons, Millions)	Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
	Total Tons of RAP Stockpiled at Year-End	NCR	NCR	NCR	NCR
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			NCR	NCR
RAP (Other Reported Data)	% Companies Reporting Using RAP	NCR	NCR		
	% of RAP Fractionated	NCR	NCR		
	% of RAP Mixtures Using Softer Binders	NCR	NCR		
	% of RAP Mixtures Using Recycling Agents	NCR	NCR		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	NCR	NCR	NCR	NCR
	Processed Shingles Accepted	NCR	NCR	NCR	NCR
	Used in HMA/WMA Mixtures	NCR	NCR	NCR	NCR
	Used as Aggregate	NCR	NCR	NCR	NCR
	Used in Cold-Mix Asphalt	NCR	NCR	NCR	NCR
	Used in Other	NCR	NCR	NCR	NCR
	Landfilled	NCR	NCR	NCR	NCR
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	NCR	NCR	NCR	NCR
	Average % for DOT Mixtures ¹	NCR	NCR		
	Average % for Other Agency Mixtures ¹	NCR	NCR		
	Average % for Commercial & Residential Mixtures ¹	NCR	NCR		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			NCR	NCR
	% Companies Reporting Using RAS	NCR	NCR		
	% of RAS Mixtures Using Softer Binders	NCR	NCR		
	% of RAS Mixtures Using Recycling Agents	NCR	NCR		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			NCR	NCR
	Total Tons Produced With WMA Technology at HMA Temperatures			NCR	NCR
	DOT	NCR	NCR	NCR	NCR
	Other Agency	NCR	NCR	NCR	NCR
	Commercial & Residential	NCR	NCR	NCR	NCR
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	NCR	NCR		
	Additive Foaming, % of Market	NCR	NCR		
	Plant Foaming, % of Market	NCR	NCR		
	Organic Additive, % of Market	NCR	NCR		
	% Companies Reporting Using WMA Technologies	NCR	NCR		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

UTAH

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.9	3.8	4.2	4.3
	DOT	0.8	1.1	1.2	1.2
	Other Agency	0.5	1.4	0.7	1.6
	Commercial & Residential	1.6	1.3	2.4	1.5
	No. of Companies Reporting	8	9		
RAP (Tons, Millions)	Accepted	0.8	0.9	1.1	1.1
	Used in HMA/WMA Mixtures	0.8	1.0	1.2	1.1
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.17	0.46	1.66	0.52
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	21.6%	22.7%		
	Average % for Other Agency Mixtures ¹	18.5%	19.3%		
	Average % for Commercial & Residential Mixtures ¹	36.1%	35.8%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			27.8%	25.6%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	13%	8%		
	% of RAP Mixtures Using Softer Binders	52%	50%		
	% of RAP Mixtures Using Recycling Agents	7%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.5 (Tons, Millions)	1.9 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			1.6 (Tons, Millions)	2.1 (Tons, Millions)
	DOT	64%	83%	0.8 (Tons, Millions)	1.0 (Tons, Millions)
	Other Agency	68%	100%	0.4 (Tons, Millions)	1.6 (Tons, Millions)
	Commercial & Residential	84%	97%	2.0 (Tons, Millions)	1.4 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	31%	28%		
	Additive Foaming, % of Market	0%	35%		
	Plant Foaming, % of Market	69%	37%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	75%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

VERMONT

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	1.7	2.0
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

VIRGINIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	5.8	7.3	12.0	10.5
	DOT	2.2	3.8	4.5	5.5
	Other Agency	0.6	1.0	1.2	1.4
	Commercial & Residential	3.0	2.5	6.2	3.6
	No. of Companies Reporting	7	9		
RAP (Tons, Millions)	Accepted	2.3	2.7	4.9	3.8
	Used in HMA/WMA Mixtures	1.6	2.3	3.4	3.2
	Used as Aggregate	0.0	0.3	0.1	0.4
	Used in Cold-Mix Asphalt	0.0	0.1	0.1	0.1
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.73	2.56	3.60	3.68
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	25.6%	27.0%		
	Average % for Other Agency Mixtures ¹	24.9%	25.2%		
	Average % for Commercial & Residential Mixtures ¹	29.1%	34.1%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			28.0%	30.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	27%	31%		
	% of RAP Mixtures Using Softer Binders	19%	13%		
	% of RAP Mixtures Using Recycling Agents	7%	7%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			8.3 (Tons, Millions)	6.9 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			2.3 (Tons, Millions)	0.3 (Tons, Millions)
	DOT	80%	66%	3.6 (Tons, Millions)	3.6 (Tons, Millions)
	Other Agency	86%	61%	1.0 (Tons, Millions)	0.9 (Tons, Millions)
	Commercial & Residential	94%	76%	5.9 (Tons, Millions)	2.7 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	93%	69%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	7%	31%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	71%	78%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

WASHINGTON

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	4.4	5.0	6.3	5.3
	DOT	0.9	1.0	1.2	1.1
	Other Agency	1.8	1.9	2.6	2.0
	Commercial & Residential	1.7	2.1	2.5	2.2
	No. of Companies Reporting	8	9		
RAP (Tons, Millions)	Accepted	1.1	1.4	1.6	1.4
	Used in HMA/WMA Mixtures	1.0	1.2	1.4	1.3
	Used as Aggregate	0.1	0.1	0.1	0.1
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	1.26	1.15	1.79	1.22
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	17.7%	22.5%		
	Average % for Other Agency Mixtures ¹	21.3%	21.5%		
	Average % for Commercial & Residential Mixtures ¹	24.8%	26.0%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			22.5%	24.4%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	23%	18%		
	% of RAP Mixtures Using Softer Binders	27%	40%		
	% of RAP Mixtures Using Recycling Agents	1%	9%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	12.6	14.2	17.9	15.1
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	11.1	8.9	15.8	9.4
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	3.5	9.5	5.0	10.1
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.18%	0.10%		
	Average % for Other Agency Mixtures ¹	0.17%	0.22%		
	Average % for Commercial & Residential Mixtures ¹	0.36%	0.27%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.25%	0.18%
RAS (Other Reported Data)	% Companies Reporting Using RAS	38%	33%		
	% of RAS Mixtures Using Softer Binders	37%	33%		
	% of RAS Mixtures Using Recycling Agents	5%	40%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.4 (Tons, Millions)	1.9 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			2.3 (Tons, Millions)	0.8 (Tons, Millions)
	DOT	35%	41%	0.4 (Tons, Millions)	0.4 (Tons, Millions)
	Other Agency	41%	53%	1.1 (Tons, Millions)	1.1 (Tons, Millions)
	Commercial & Residential	47%	55%	1.2 (Tons, Millions)	1.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	1%	9%		
	Additive Foaming, % of Market	0%	3%		
	Plant Foaming, % of Market	99%	88%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	88%	89%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

WEST VIRGINIA

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	2.3	0.3	4.2	3.8
	DOT	1.7	0.2	3.1	2.5
	Other Agency	0.4	0.1	0.8	0.7
	Commercial & Residential	0.2	0.0	0.3	0.6
	No. of Companies Reporting	3	3		
RAP (Tons, Millions)	Accepted	0.3	0.2	0.5	2.9
	Used in HMA/WMA Mixtures	0.4	0.1	0.7	0.6
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	0.33	0.34	0.60	4.33
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	17.5%	15.3%		
	Average % for Other Agency Mixtures ¹	17.7%	10.0%		
	Average % for Commercial & Residential Mixtures ¹	17.7%	19.7%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			17.6%	16.7%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	0%	0%		
	% of RAP Mixtures Using Softer Binders	0%	0%		
	% of RAP Mixtures Using Recycling Agents	0%	0%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	0.0	0.0	0.0	0.0
	Processed Shingles Accepted	0.0	0.0	0.0	0.0
	Used in HMA/WMA Mixtures	0.0	0.0	0.0	0.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	0.0	0.0	0.0	0.0
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.00%	0.00%		
	Average % for Other Agency Mixtures ¹	0.00%	0.00%		
	Average % for Commercial & Residential Mixtures ¹	0.00%	0.00%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.00%	0.00%
RAS (Other Reported Data)	% Companies Reporting Using RAS	0%	0%		
	% of RAS Mixtures Using Softer Binders	0%	0%		
	% of RAS Mixtures Using Recycling Agents	0%	0%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			0.0 (Tons, Millions)	0.1 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.0 (Tons, Millions)	2.8 (Tons, Millions)
	DOT	0%	80%	0.0 (Tons, Millions)	2.0 (Tons, Millions)
	Other Agency	0%	74%	0.0 (Tons, Millions)	0.5 (Tons, Millions)
	Commercial & Residential	0%	77%	0.0 (Tons, Millions)	0.4 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	0%	0%		
	Additive Foaming, % of Market	0%	93%		
	Plant Foaming, % of Market	0%	7%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	0%	67%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

WISCONSIN

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	8.7	9.6	12.0	12.0
	DOT	5.0	3.8	6.9	4.8
	Other Agency	1.9	2.9	2.6	3.6
	Commercial & Residential	1.8	2.9	2.5	3.6
	No. of Companies Reporting	3	5		
RAP (Tons, Millions)	Accepted	1.6	2.1	2.2	2.6
	Used in HMA/WMA Mixtures	1.8	2.0	2.5	2.5
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAP Stockpiled at Year-End	2.00	2.14	2.77	2.67
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	20.3%	18.8%		
	Average % for Other Agency Mixtures ¹	20.3%	20.8%		
	Average % for Commercial & Residential Mixtures ¹	23.0%	22.4%		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			20.7%	20.8%
RAP (Other Reported Data)	% Companies Reporting Using RAP	100%	100%		
	% of RAP Fractionated	3%	24%		
	% of RAP Mixtures Using Softer Binders	5%	11%		
	% of RAP Mixtures Using Recycling Agents	0%	21%		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	36.0	49.8	49.8	62.3
	Processed Shingles Accepted	28.2	0.0	39.0	0.0
	Used in HMA/WMA Mixtures	38.0	44.0	52.6	55.0
	Used as Aggregate	0.0	0.0	0.0	0.0
	Used in Cold-Mix Asphalt	0.0	0.0	0.0	0.0
	Used in Other	0.0	0.0	0.0	0.0
	Landfilled	0.0	0.0	0.0	0.0
	Total Tons of RAS Stockpiled at Year-End	46.2	50.7	63.9	63.4
RAS (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	0.44%	0.46%		
	Average % for Other Agency Mixtures ¹	0.44%	0.46%		
	Average % for Commercial & Residential Mixtures ¹	0.44%	0.47%		
	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			0.44%	0.46%
RAS (Other Reported Data)	% Companies Reporting Using RAS	100%	100%		
	% of RAS Mixtures Using Softer Binders	75%	30%		
	% of RAS Mixtures Using Recycling Agents	0%	21%		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			1.0 (Tons, Millions)	1.5 (Tons, Millions)
	Total Tons Produced With WMA Technology at HMA Temperatures			0.3 (Tons, Millions)	0.7 (Tons, Millions)
	DOT	11%	21%	0.8 (Tons, Millions)	1.0 (Tons, Millions)
	Other Agency	15%	28%	0.4 (Tons, Millions)	1.0 (Tons, Millions)
	Commercial & Residential	7%	6%	0.2 (Tons, Millions)	0.2 (Tons, Millions)
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	100%	100%		
	Additive Foaming, % of Market	0%	0%		
	Plant Foaming, % of Market	0%	0%		
	Organic Additive, % of Market	0%	0%		
	% Companies Reporting Using WMA Technologies	100%	100%		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting

WYOMING

Material	Sectors	Reported Values		Estimated Values	
		2019	2020	2019	2020
HMA/WMA (Tons, Millions)	Total	*	*	2.3	2.3
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
	No. of Companies Reporting	*	*		
RAP (Tons, Millions)	Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
	Total Tons of RAP Stockpiled at Year-End	*	*	*	*
RAP (Average % Used in Mixtures)	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
	State Average All Mixtures Based on RAP Tons Used in HMA/WMA ²			*	*
RAP (Other Reported Data)	% Companies Reporting Using RAP	*	*		
	% of RAP Fractionated	*	*		
	% of RAP Mixtures Using Softer Binders	*	*		
	% of RAP Mixtures Using Recycling Agents	*	*		
RAS (Tons, Thousands)	Unprocessed Shingles Accepted	*	*	*	*
	Processed Shingles Accepted	*	*	*	*
	Used in HMA/WMA Mixtures	*	*	*	*
	Used as Aggregate	*	*	*	*
	Used in Cold-Mix Asphalt	*	*	*	*
	Used in Other	*	*	*	*
	Landfilled	*	*	*	*
RAS (Average % Used in Mixtures)	Total Tons of RAS Stockpiled at Year-End	*	*	*	*
	Average % for DOT Mixtures ¹	*	*		
	Average % for Other Agency Mixtures ¹	*	*		
	Average % for Commercial & Residential Mixtures ¹	*	*		
RAS (Other Reported Data)	State Average All Mixtures Based on RAS Tons Used in HMA/WMA ²			*	*
	% Companies Reporting Using RAS	*	*		
	% of RAS Mixtures Using Softer Binders	*	*		
	% of RAS Mixtures Using Recycling Agents	*	*		
WMA	Total Tons Produced With WMA Technology at Reduced Temperature			*	*
	Total Tons Produced With WMA Technology at HMA Temperatures			*	*
	DOT	*	*	*	*
	Other Agency	*	*	*	*
	Commercial & Residential	*	*	*	*
WMA Technologies (Other Reported Data)	Chemical Additive, % of Market	*	*		
	Additive Foaming, % of Market	*	*		
	Plant Foaming, % of Market	*	*		
	Organic Additive, % of Market	*	*		
	% Companies Reporting Using WMA Technologies	*	*		

¹ Average percent based on contractor's reported percentage for each sector, adjusted based upon reported tonnage.

² Average percent based on total reported tons of RAP or RAS used in HMA/WMA divided by reported total tons HMA/WMA produced.

NCR = No companies responding

* = Fewer than 3 companies reporting



National Asphalt Pavement Association

6406 Ivy Lane, Suite 350
Greenbelt, Maryland 20770-1441

www.AsphaltPavement.org
napa@AsphaltPavement.org

Toll Free: 888-468-6499
Tel: 301-731-4748
Fax: 301-731-4621

Publication Sales

Login at <https://member.asphaltpavement.org/Shop/Product-Catalog>

Toll Free: 888-600-4474
Tel: 412-741-6314
Fax: 412-741-0609

11th Annual Asphalt Pavement Industry Survey IS 138 — Appendix B



Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage 2020

IS-138 Appendix C:
Methodology for Calculating Energy and
Greenhouse Gas Emission Benefits
From Production of WMA and Use of RAP



11th Annual Survey

Asphalt Pavement Industry Survey on Recycled Materials and Warm-Mix Asphalt Usage: 2020

Appendix C

Introduction

Appendix C provides a detailed overview of the methodology and assumptions used to calculate energy and greenhouse gas (GHG) emission benefits from production of WMA at reduced temperature and use of RAP in new asphalt mixtures. These calculations are based on publicly available data published by government agencies, industry, and non-governmental organizations. For many of these calculations, multiple data sources exist for the underlying emission factors. In such cases, the most recent and comprehensive data sources were selected.

Methodology for Calculating Energy and GHG Emissions Reduction from Production of WMA at Reduced Temperature

To estimate reductions in energy consumption and GHG emissions associated with the production of WMA at reduced temperature, we start by estimating the average temperature reduction achieved by plants that reduce mix production temperature when using WMA technologies. We then estimate the expected energy savings (Btu) from reduced temperature, convert that to fuel volume (natural gas), and use emission factors to estimate the well-to-combustion GHG emissions reduction from producing WMA at reduced temperature.

Temperature Reduction

The survey classifies reduced-temperature WMA as having a temperature reduction of at least 10° F. This represents a conservative low-end estimate for the average temperature reduction achieved. Since the survey does not collect data on actual temperature reductions achieved, we assign an optimistic estimate for average temperature reduction of 40° F. As a point of reference, the average temperature reduction achieved by plants tested in NCHRP Report 779 was 48° F (National Academies of Science, Engineering, and Medicine (NASEM), 2014), suggesting that the 40° F optimistic scenario is reasonable.

Energy Savings

NCHRP Report 779 provides an estimated energy savings of 1,100 Btu/°F per ton of WMA produced (NASEM, 2014). Here, we use a slightly more conservative value of 1,000 Btu/°F/ton, which is the same value used for NAPA's GHG Calculator tool. It should be noted that this estimate only accounts for reduced burner fuel combustion and does not account for the electricity savings associated with the improved efficiency of baghouse fans handling WMA exhaust gas at reduced temperature.

GHG Emissions Reduction

We assume that all of the plants burn natural gas for their burner fuel and utilize emission factors published by NREL (Deru & Torcellini, 2007), which provides both pre-combustion and on-site combustion emission factors. Together, these emission factors provide a holistic well-to-combustion scope. The pre-combustion emission factors account for the energy required to extract, process, and deliver the fuel. On-site combustion emission factors are simply the emissions released during combustion of fuel in the burner. The sum of the pre-combustion and on-site combustion emission factors for natural gas burned in a commercial boiler is 150.8 lb CO₂e/1000 ft³ natural gas, which can be converted to 65.96 kg CO₂e/MMBtu natural gas, assuming that natural gas has a higher heating value of 1,037 Btu/ft³ (EIA, 2020).

The following information would help constrain the estimate of GHG emissions reduction for WMA produced at reduced temperature:

- Actual reductions in mix temperature achieved by plants that produce WMA at reduced temperature,
- Characterization of the types and relative amounts of burner fuel consumed by asphalt plants, and
- Reliable estimates of electricity savings associated with the improved efficiency of baghouse fans handling WMA exhaust gas at reduced temperature.

WMA GHG Burdens – General Considerations

WMA production requires the use of additional materials, such as water or chemical additives, that are not typically used for asphalt mixture production. GHG emissions associated with extracting, processing, and transporting those materials are referred to as the upstream WMA GHG burdens. The magnitude of these burdens depends on the type of WMA technology utilized and application-specific parameters. For foamed asphalt WMA technologies, the primary upstream GHG burden is associated with extracting, treating (if applicable), and delivering water to the facility. For chemical and organic additives, the upstream GHG burdens stem from extracting, processing, and transporting the chemical or organic additives to the asphalt plant.

GHG Burdens from Foamed Asphalt Water Consumption

Foamed asphalt consumes approximately 1-2 percent water by weight of virgin asphalt binder. For this analysis, we use a conservative estimate of 2 percent. If we assume the average binder content of foamed asphalt WMA mixtures is 5 percent, approximately 45,800 tons of water are consumed to produce WMA at reduced temperature. This can be converted to 11.0 million gallons (MG) assuming 8.33 lbs of water per gallon.

To our knowledge, no federal agencies have published nationwide data regarding the carbon footprint of supplying water. However, Griffiths-Sattenspiel and Wilson (2009) provide a sector-specific analysis of water consumption and related greenhouse gas emissions. Based on the data reported by Griffiths-Sattenspiel and Wilson (2009), municipal water supply has the highest carbon intensity at 1.25 tonne CO₂e/MG water. Industrial and mining water supplies have carbon intensities of 0.33 and 0.25 tonne CO₂e/MG water, respectively. Information on which type of water supply asphalt plants use is not collected in the industry survey, but it's likely a mix of municipal, industrial, and mining water supply sources. For this report, we use the more conservative estimate for municipal water supply carbon intensity, which likely over-estimates the carbon intensity for supplying water to asphalt plants, perhaps by as much as a factor of four or five.

The GHG burden for supplying water for foamed WMA produced at reduced temperature is estimated to be 14 tonne CO₂e/year, which is less than a tenth of a percent of the most conservative estimate of GHG emissions reduction for WMA produced at reduced temperature. Thus, the upstream GHG burdens for foamed water consumption are negligible.

GHG Burdens from Chemical and Organic Additives

Estimating the upstream emissions for producing chemical and organic WMA additives is more complex than doing so for water. There are numerous suppliers for these additives, each of which uses different chemical compositions and proprietary manufacturing processes, with dosage rates that vary by type of additive and application-specific parameters. Collecting the necessary data to constrain these variables would be a substantial effort and is outside the scope of this survey. Some additives are used for other purposes, such as anti-strip or recycling agents, and the WMA functionality is a co-benefit, creating additional challenges with respect to allocation of burdens to WMA.

Even if the types and quantities of WMA additives could be estimated, there is very little publicly available information about the upstream GHG emissions associated with manufacturing and transporting WMA additives. Recently, Ingevity published an analysis of the environmental impacts and benefits of producing its Evotherm M1 WMA additive (ERM, 2020). To our knowledge, this is the only publicly available data that offers insight into the upstream GHG burdens for WMA additives.

It would not be prudent to extrapolate the Ingevity data to the entire population of WMA produced at reduced temperature using chemical and organic additives. Thus, the upstream GHG burdens from WMA additives are not included in Table 17 of the report. However, there is an opportunity to calculate an order-of-magnitude estimate

based on the Ingevity data to provide some insight to the upstream burdens.¹ The order-of-magnitude estimate suggests that upstream WMA GHG burdens for chemical additives can be significant, although they are likely to be lower than even the most conservative estimate for GHG emission reduction for WMA produced at reduced temperature. The following information would allow for a more accurate estimate of upstream WMA GHG emissions:

- Characterization and quantification of the types and amounts of chemical and organic WMA additives that are used,
- More robust data regarding the upstream GHG emissions for commonly used WMA additives, and
- Development of an allocation procedure to address co-benefits of WMA additives such as anti-strip and recycling agent functionalities.

Methodology for Calculating GHG Emissions Reduction from Use of RAP in New Asphalt Mixtures

GHG emissions reduction from use of RAP in new asphalt mixtures is quantified by estimating the avoided upstream emissions that would be associated with extracting, processing, and transporting virgin materials (aggregate and asphalt binder) that the RAP replaces in asphalt mixtures. To quantify the GHG emission burdens from using RAP, the emissions associated with transporting and processing RAP are estimated. Considerations regarding the use of recycling agents and softer binders is also discussed. This approach relies on several assumptions to address the impacts of recycled and secondary materials from an emissions accounting perspective:

- Emissions associated with materials production, transportation, construction, maintenance, use, and end-of-life (including milling or excavation) of the original pavement from which the RAP was sourced are outside the system boundary and are not included in this analysis. This cut-off method for recycled materials is consistent with Mukherjee (2016) and the Product Category Rules (PCR) for Asphalt Mixtures (NAPA, 2017).
- The average asphalt binder content of RAP is 5 percent, consistent with calculations used elsewhere in this report. The asphalt binder in the RAP is completely mixed and utilized, allowing for a comparable reduction in the use of virgin asphalt binder.
- The use of RAP does not significantly affect asphalt plant energy consumption and related GHG emissions.

GHG Emission Reduction from Avoided Use of Asphalt Binder

Starting with an estimated 87.0 million tons of RAP utilized in asphalt mixtures, approximately 4.35 million tons of virgin asphalt binder is avoided, assuming an average binder content of 5 percent.

Several studies have estimated the carbon footprint associated with extracting, processing, and transporting virgin asphalt binder, and the differences between them are substantial. For this analysis, we use an estimate of 577.9 kg CO₂e/ton as published in the Asphalt Institute's Life Cycle Assessment (LCA) of Asphalt Binder (Wildnauer et al., 2019), which relies on a thermodynamic allocation approach for refinery operations and a bottom-up approach for crude slate allocation based on refinery data specific to asphalt binder production. The LCA of Asphalt Binder also includes the emissions associated with terminal operations, which is not included in many of the other available datasets. The avoided GHG emissions from asphalt binder replacement through the use of RAP is estimated to be 2.51 million tonne CO₂e.

¹ Assuming a 5 percent binder content for WMA produced at reduced temperature using a chemical additive and a dosage rate of 0.5 percent Evothrm M1 by weight of binder, 10,846 tons of WMA additive would be utilized under this hypothetical but unrealistic scenario. Using Ingevity's published value of 4.4 kg CO₂e/kg Evothrm M1, the upstream GHG emissions would be approximately 0.043 million tonne CO₂e if it were the only additive used to produce WMA using a chemical additive at reduced temperature. This value is approximately 70% of the estimated GHG emission reduction in the conservative scenario of a 10° F average temperature differential for mix produced at reduced temperature using chemical additive WMA technologies.

GHG Emission Reduction from Avoided Use of Aggregates

Starting with an estimated 87.0 million tons of RAP utilized in asphalt mixtures, approximately 82.65 million tons of virgin aggregate is avoided, assuming an average aggregate content of 95 percent.

The estimate for the carbon footprint of crushed stone extraction and processing is derived from the Life Cycle Inventory of Portland Cement Concrete (Marceau et al., 2007), who provide a detailed breakdown of the energy sources and quantities for crushed stone production. Emission factors for each energy source were derived from Deru & Torcellini (2007). A summary of the energy and emissions associated with crushed aggregate production in the U.S. is provided in Table C1.

Table C1: Crushed Stone GHG Emission Factor

Energy Source	Energy Used (unit/ton aggregate) ¹	Energy Emission Factor (kg CO ₂ e/unit) ²	GHG Emissions (kg CO ₂ e/ton aggregates) ³
Coal, ton	0.0000275	2,657 ⁴	0.073072
Distillate Fuel Oil, gal	0.0932	12.16 ⁵	1.132966
Residual Fuel Oil, gal	0.0145	13.64 ⁶	0.197773
Natural Gas, 1000 ft ³	0.00345	150.80 ⁶	0.52026
Gasoline, gal	0.00939	9.57 ⁵	0.08987
Electricity, 1000 kWh	0.00296	758 ⁷	2.24368
Total			4.26

¹ Source: Marceau et al. (2007)

² Source: Deru and Torcellini (2007)

³ GHG Emissions is the product of Energy Used and the respective Energy Emission Factor

⁴ From bituminous coal values in Tables 6 and 8 of Deru and Torcellini (2007)

⁵ From Tables 6 and 10 of Deru and Torcellini (2007), assuming combustion in a stationary reciprocating engine

⁶ From Tables 6 and 8 of Deru and Torcellini (2007)

⁷ From the national average in Table 4 of Deru and Torcellini (2007)

Using the emission factor of 4.26 kg CO₂e/ton aggregates, the avoided GHG emissions from aggregate replacement through the use of RAP is approximately 0.35 million tonne CO₂e.

GHG Emission Reduction from Avoided Transportation of Asphalt Binder and Aggregates

The emission factors for asphalt binder and aggregates derived from Wildnauer et al. (2019) and Marceau et al. (2007) are based on a cradle-to-gate scope, which does not include transportation to the asphalt plant. To estimate the avoided emissions for transporting asphalt binder and aggregates to the asphalt plant, we assume the average haul distance for virgin asphalt binder and aggregates to be 3.9 and 21.5 ton·miles/ton of mix produced, respectively (Mukherjee, 2016). Using the total RAP quantity of 87.0 million tons as the basis for the amount of virgin mix offset by the use of RAP, this yields a combined of 2.21 billion ton·miles of avoided transport.

The emission factors for transportation and distribution via medium- and heavy-duty truck published by the U.S. EPA (2018) for CO₂, CH₄, and N₂O have a combined value of 0.202497 kg CO₂e /ton·mile. This emission factor is multiplied by the estimate of 2.21 billion ton·miles of avoided transport to yield a GHG emission reduction of approximately 0.45 million tonne CO₂e.

GHG Emission Burdens from Use of RAP – General Considerations

Potential GHG emission burdens from use of RAP include a variety of factors, the most straightforward of which are the emissions associated with transporting and processing RAP. For this report, the system boundary begins with transportation of RAP. Activities that occur prior to transportation, such as milling or excavation, are considered part of the end-of-life of phase for the previous pavement and are not included in this estimate.

GHG Emission Burdens from RAP Processing

RAP is often processed by crushing and screening prior to use in asphalt mixture production to improve the quality and consistency of the finished product. The energy required to process the RAP is estimated to be 0.1 gallons of distillate fuel per ton of RAP processed (Mukherjee 2016). Approximately 8.70 million gallons of distillate fuel oil are

consumed to process 87.0 million tons of RAP. Using the combined pre-combustion and combustion emission factor of 12.16 kg CO₂e per gallon of distillate fuel oil (Table C1), GHG emissions from RAP processing are estimated to be approximately 0.11 million tonne CO₂e. This estimate assumes that all RAP is processed prior to use, and the processing equipment is powered by a diesel engine.

GHG Emission Burdens from Transportation of RAP

Transportation of RAP from the jobsite to the asphalt plant is included in the system boundary. To estimate the emissions for transporting RAP to the asphalt plant, we assume the average haul distance for RAP to be 50 miles, which is consistent with the typical market area for an asphalt plant (Mukherjee, 2016). The 50-mile haul distance is multiplied by 87.0 million tons to yield 4.35 billion ton·miles. Using the emission factor of 0.202497 kg CO₂e/ton·mile (U.S. EPA, 2018), GHG emissions for transporting RAP to the plant are estimated to be approximately 0.88 million tonne CO₂e.

GHG Emission Burdens from Use of Softer Binders and Recycling Agents

Asphalt plants sometimes use recycling agents or softer binders to improve the quality of asphalt mixtures that contain RAP. On average, survey respondents reported that 23% of RAP mixes used a softer binder and 6% of RAP mixes used a recycling agent in 2020 (Table 8). Specific data regarding the PG grade of binders used and the types and quantities of recycling agents used are not collected in the survey. Additionally, there is no publicly available data regarding the carbon footprint of specific binder grades or recycling agents. The data provided in the Asphalt Institute's LCA of Asphalt Binder (Wildnauer et al., 2019) is an average of all asphalt binder produced and does not provide a separate values for different PG grades. Thus, GHG emission burdens from use of softer binders and recycling agents are not estimated in this report.

References

- Deru, M. & P. Torcellini (2007). *Source Energy and Emission Factors for Energy Use in Buildings*. Technical Report NREL/TP-550-38617. National Renewable Energy Laboratory.
- EIA (2020). Heat Content of Natural Gas Consumed [website]. U.S. Energy Information Administration, Washington, D.C. https://www.eia.gov/dnav/ng/ng_cons_heat_a_EPG0_VG_TH_btucf_a.htm [accessed 19 August 2020].
- ERM (2020). *Ingevity Net Product Benefits: Project Summary - Evotherm M1 Asphalt Additive*. ERM, Annapolis, Maryland. <https://www.ingevity.com/uploads/page-pdfs/Evotherm-Product-Benefits-Study-Summary.pdf>
- Griffiths-Sattenspiel, B. & W. Wilson (2009). *The Carbon Footprint of Water*. River Network, Portland, Oregon. <https://www.csu.edu/cerc/researchreports/documents/CarbonFootprintofWater-RiverNetwork-2009.pdf>
- Marceau, M.L., M.A. Nisbet, & M.G. VanGeem (2007). *Life Cycle Inventory of Portland Cement Concrete*. Report SN3011. Portland Cement Association, Skokie, Illinois.
- Mukherjee, A. (2016). *Life Cycle Assessment of Asphalt Mixtures in Support of an Environmental Product Declaration*. National Asphalt Pavement Association, Lanham, Maryland.
- NAPA (2017). *Product Category Rules (PCR) for Asphalt Mixtures*. National Asphalt Pavement Association, Lanham, Maryland
- NASEM (2014). *Field Performance of Warm Mix Asphalt Technologies*. Washington, DC: The National Academies Press. doi:10.17226/22272.
- U.S. EPA (2018). *Emission Factors for Greenhouse Gas Inventories*. Center for Corporate Climate Leadership. https://www.epa.gov/sites/production/files/2018-03/documents/emission-factors_mar_2018_0.pdf.
- Wildnauer, M., E. Mulholland, & J. Liddie (2019). *Life Cycle Assessment of Asphalt Binder*. Asphalt Institute, Lexington, Kentucky. <http://www.asphaltinstitute.org/engineering/lca-study-on-asphalt-binders/>



National Asphalt Pavement Association

6406 Ivy Lane, Suite 350

Greenbelt, Maryland 20770-1441

www.AsphaltPavement.org

napa@AsphaltPavement.org

Toll Free: 888-468-6499

Tel: 301-731-4748

Fax: 301-731-4621

Publication Sales

Login at <https://member.asphaltpavement.org/Shop/Product-Catalog>

Toll Free: 888-600-4474

Tel: 412-741-6314

Fax: 412-741-0609

11th Annual Asphalt Pavement Industry Survey IS 138 — Appendix C

